



# Submerged Arc Welding Consumables

# ITW Welding - Your Route to Full Performance Submerged Arc Welding



At ITW Welding we are passionate about the submerged arc welding process and this is reflected by our unique offering to the market. When you use Hobart's best in class welding consumables or Miller's cutting edge equipment, you will enjoy the most advanced and productive submerged arc products.

The interaction of two consumables – flux and wire – and the availability of a variety of process variants make submerged arc welding a complex arc welding process and fabricators may not always utilize its full potential.



Partnering with ITW Welding, you will have the deep knowledge and experience of our engineers at your side, along with fully equipped laboratories for dedicated application research.

Testing facilities include multi-wire installations to simulate and develop productive welding procedures for industrial segments such as longitudinal and spiral pipe mills, wind tower production, pressure vessel fabrication and shipbuilding. Often an audit by ITW Welding specialists at our customers' facilities precedes a route that leads to full performance submerged arc welding at lower bottom-line cost.



Our flux manufacturing utilizes the latest technology, producing high performance SAW fluxes with consistent quality and supplied in innovative packaging solutions for safe and cost efficient storage and handling.

ITW Welding is a total solutions provider for the submerged arc welding process, including welding heads, tractors, column & booms, flux drying & handling equipment and preheating equipment. The offer includes engineering and automation and turnkey solutions, making us the ideal partner for one-stop-shopping.



Contact us and discover ways to implement submerged arc welding or optimize your existing processes to their full potential.



# Table of Contents

## Selection tables

Flux selection guide by industrial application . . . . .	5
Flux selection quick guide . . . . .	6
SubCOR metal cored wire selection quick guide . . . . .	7
SubCOR SL cored wire selection quick guide . . . . .	8
SAW solid wire and strip range . . . . .	9
Flux selection by SDX solid wire . . . . .	10
Flux selection by SubCOR cored wire . . . . .	10
Flux selection by AWS wire classification . . . . .	11

## Consumables

SWX 110 - EN ISO 14174: S A AB 1 67 AC H5 . . . . .	12
SWX 120 - EN ISO 14174: S A AB 1 57 AC H5 . . . . .	14
SWX 130 - EN ISO 14174: S A AB 1 67 AC H5 . . . . .	16
SWX 135 - EN ISO 14174: S A AB 1 67 AC H5 . . . . .	18
SWX 140 - EN ISO 14174: S A FB 1 57 AC H5 . . . . .	20
SWX 150 - EN ISO 14174: S A FB 1 55 AC H5 . . . . .	22
SWX 220 - EN ISO 14174: S A AF 2 DC . . . . .	26
SWX 282 - EN ISO 14171: S A AF 2 DC . . . . .	28
SWX 305 - EN ISO 14174: S A AAS 2B DC . . . . .	29
SWX 330 - EN ISO 14174: ES A FB 2B DC . . . . .	30
SWX 382 - EN ISO 14174: ES A AF 2B DC . . . . .	31
SWX 010 - Powder backing for one-sided welding . . . . .	32
Approval certificates . . . . .	33
Packaging solutions . . . . .	34
Storage and handling recommendations . . . . .	35
Full performance submerged arc welding pays back . . . . .	36
Hobart SubCOR cored wires for submerged arc welding . . . . .	38
Improved productivity from SubCOR metal-cored wires . . . . .	40
Flux cored micro injection . . . . .	42
Classification standards . . . . .	44
Submerged arc welding process . . . . .	51
Submerged arc power sources and AC wave balance . . . . .	60
SAW and ESW strip cladding . . . . .	64
Trouble shooting . . . . .	66

**NOTE:** With this catalogue, ITW Welding introduces its all new, global range of Hobart submerged arc welding consumables under the new product names SWX for fluxes, SDX for solid wires and SubCOR for cored wires. Earlier products marketed in individual countries under brand names like Hobart, Elga and Tien Tai remain to be available until further notice.

**Disclaimer:** The information contained herein is furnished for reference purposes only and is believed to be accurate and reliable. Typical data are those obtained when welding and testing are performed in accordance with prescribed standards and guidelines. Other tests may produce different results and typical data should not be assumed to yield similar results in a particular application or weldment. ITW Welding does not assume responsibility for any results obtained by persons over whose methods it has no control. It is the user's responsibility to determine the suitability of any products or methods mentioned herein for a particular purpose. In light of the foregoing, ITW Welding specifically disclaims all warranties, express or implied, including warranties of merchantability and fitness for a particular purpose, and further disclaims any liability for consequential or incidental damages of any kind, including lost profits.

# Best-in-Class Submerged Arc Welding Consumables from a Trusted Source

Since 1917, the Hobart name enjoys a solid reputation for quality, innovation and know-how. Under this brand, ITW Welding now brings together a wealth of submerged arc welding expertise and consumables with unequalled welding performance.

This catalogue features best in class products for the welding of all commonly applied construction steels, stainless steels and high-alloyed Ni-base alloys, including solutions for SAW and ESW strip cladding.

Special flux/wire combinations have been developed to meet specific requirements of demanding industries, such as offshore construction, pressure vessel fabrication and pipe mills.

Hobart submerged arc welding consumables are manufactured using state-of-the-art production technology. They carry the name SWX for agglomerated submerged arc fluxes, SDX for solid wires, SubCOR for the advanced range of low-hydrogen cored wires and Cromastrip for strips for submerged arc and electroslog cladding.

Hobart submerged arc products are brought on the market supported by a dedicated team of specialists, capable of providing integrated submerged arc welding solutions.





# Flux Selection Guide by Industrial Application

		Joining						Strip cladding				
		Non- & low-alloyed						Stain- less	SAW		ESW	
	Depending on requirements	SWX 110	SWX 120	SWX 130	SWX 135	SWX 140	SWX 150	SWX 220	SWX 282	SWX 305	SWX 330	SWX 382
Civil construction	Beams, bridges, buildings	✓										
Cranes	Normal strength steel	✓										
	High strength steel					✓	✓					
Offshore	Constructions	✓				✓	✓					
	Process equipment							✓	✓			
Pipelines	Double jointing	✓				✓	✓					
Pipe mills	Longitudinal			✓				✓				
	Spiral	✓			✓							
Power generation	Boilers	✓				✓	✓	✓		✓	✓	✓
	Nuclear						✓	✓		✓	✓	
	Tube to fin	✓										
Pressure vessels	Joining	✓	✓			✓	✓	✓				
	Surfacing									✓	✓	✓
Process industry	Hydrocrackers						✓					
	Pulp & paper							✓	✓			
Shipbuilding	Butt and fillet welding	✓										
	Handling equipment					✓						
Storage tanks	Chemical tanks							✓				
	LPG tanks							✓				
	Oil tanks	✓	✓									
Transport	Beams for trucks and rail cars	✓										
	Heavy equipment	✓	✓									
	Wheels	✓										
Wind energy	Monopiles, tri-pods, jackets		✓				✓					
	Towers		✓									



# Flux Selection Quick Guide

<b>SWX 110</b>	<b>Multi-purpose flux applied in a variety of industries</b>
	Medium basic general purpose flux allowing high travel speeds
	Covers a wide range of applications
	Can be used with a range of wires to cover mild steel and medium tensile fine-grained steel with impact toughness requirements down to -40°C (-40°F)
<b>SWX 120</b>	<b>Flux for wind tower fabrication</b>
	Suitable for circumferential and longitudinal multi-layer welds
	Productive flux with good impact toughness down to -50°C (-58°F), using standard quality S2 and S2Si solid wires
	Single- and multi-wire operations
<b>SWX 130</b>	<b>Flux for longitudinal pipe mills</b>
	High current carrying capacity
	High welding speed and good mechanical properties in two-run welding with up to five wires
	Flat and wide bead profile with smooth wetting
<b>SWX 135</b>	<b>Flux for spiral pipe mills</b>
	High welding speed and good mechanical properties in two-run welding with up to three wires
	Fast freezing slag
	Flat and wide bead profile with smooth wetting
<b>SWX 140</b>	<b>Multi-purpose flux for applications with increased toughness demands</b>
	Versatile and productive basic flux for applications with increased low-temperature toughness demands down to -50°C (-58°F)
	Meets toughness requirements down to -60°C (-76°F) with SubCOR cored wires
	Single- and two-run welds, multi-layer welds
	Single- and multi-wire set-ups
<b>SWX 150</b>	<b>High basicity flux for demanding applications</b>
	For demanding applications, such as offshore, pressure vessel, cryogenic and nuclear fabrication
	Excellent impact toughness down to -60°C (-76°F) + CTOD
	Wide range of flux/wire combinations, including for high strength, low-temperature and creep resistant applications
	Single- and multi-wire operations
	Narrow gap welding
<b>SWX 220</b>	<b>Stainless steel joining flux</b>
	Joining of austenitic, duplex and super duplex stainless steels, dissimilar joints and higher alloyed stainless steel grades
	Excellent slag detachability in multi-run welds
	Suitable for a wide range of stainless steel applications at standard welding speed
<b>SWX 282</b>	<b>Flux for joining Ni-base alloys</b>
	Joining of Ni-base alloys, such as Alloy 82, Alloy 600 and Alloy 625
	Single- or multi-run operation
	Excellent impact toughness down to -196°C (-320°F)
<b>SWX 305</b>	<b>SAW strip cladding flux</b>
	Submerged arc strip cladding with stainless strips
	Austenitic clad layer compositions on mild and low-alloyed steel
	Smooth bead appearance and easy slag removal
<b>SWX 330</b>	<b>ESW strip cladding flux</b>
	ESW strip cladding flux
	Austenitic stainless composition in one layer
	High current carrying capacity
<b>SWX 382</b>	<b>ESW strip cladding flux, Ni-base</b>
	Electroslag strip cladding with Ni-base strips
	Ni-base clad composition in one or two layers
<b>SWX 010</b>	<b>Powder backing for one-sided welding on copper weld metal supports</b>
	Has no influence on weld metal properties
	Gives a regular, smooth root pass



# SubCOR metal cored wire selection quick guide

Product	Features
<b>SubCOR EM12K-S</b>	General purpose cored wire electrode for submerged arc welding of non-alloyed steels Higher deposition rate than solid wires Similar in chemistry to AWS A5.17: EM12K Suitable fluxes: SWX 110, SWX 120, SWX 140 and SWX150
<b>SubCOR EM13K-S</b>	General purpose cored wire electrode for submerged arc welding of non-alloyed steels Higher deposition rate than solid wires and at the same time improved impact toughness properties Similar in chemistry to AWS A5.17: EM13K Suitable fluxes: SWX 110, SWX 120 and SWX150
<b>SubCOR EM13K-S MOD</b>	General purpose cored wire electrode for submerged arc welding of non-alloyed steels with PWHT Higher deposition rate than solid wires Similar in chemistry to AWS A5.17: EM13K Suitable fluxes: SWX 110, SWX 120, SWX 140 and SWX 150
<b>SubCOR 92-S</b>	Low-alloyed cored wire electrode for high strength applications: AWS A5.23 chemistry M1 Designed for tensile strength levels above 550 MPa (80ksi) Like all SubCOR wires it provides improved deposition rates compared to solid wires Suitable fluxes: SWX 140 and SWX 150
<b>SubCOR F2-S</b>	Low-alloyed wire for high strength applications: AWS A5.23 chemistry F2 Designed for tensile strength levels over 620 MPa (90 ksi) Suitable flux: SWX 150
<b>SubCOR 100F3-S</b>	Low-alloyed wire for high strength applications: AWS A5.23 chemistry F3 Designed for tensile strength levels over 690 MPa (100 ksi) Suitable fluxes: SWX 140 and SWX 150
<b>SubCOR 120-S</b>	Low-alloyed cored wire electrode for high strength applications: AWS A5.23 chemistry M4 Designed for tensile strength levels above 760 MPa (110 ksi) Like all SubCOR wires it provides improved deposition rates compared to solid wires Suitable flux: SWX 150
<b>SubCOR N1-S</b>	Low-alloyed cored wire electrode where a 1% nickel deposit is required: AWS A5.23 chemistry Ni1 Designed for tensile strengths above 480 MPa (70 ksi) Suitable fluxes include SWX 150
<b>SubCOR W-S</b>	Low-alloyed wire for copper alloyed weathering steels Very good impact properties down to - 50 °C (- 60 °F ) Suitable flux: SWX 150
<b>SubCOR B2-S</b>	Cr-Mo alloyed wire for creep resistant steels. Chemistry- AWS A5.23 B2 Like all SubCOR wires it provides improved deposition rates compared to solid wires Suitable flux: SWX 150
<b>SubCOR B3-S</b>	Cr-Mo alloyed wire for creep resistant steels. Chemistry- AWS A5.23 B3 Like all SubCOR wires it provides improved deposition rates compared to solid wires Suitable flux: SWX 150

# SubCOR SL cored wire selection quick guide

Product	Features
<b>SubCOR SL 731</b>	General purpose cored wire electrode for submerged arc welding of non alloyed steels Higher deposition rate than solid wires and at the same time improved impact toughness properties Recommended instead of SDX S2, SDX S2Si-EM12K, SDX S2Mo-EA2 or SDX S3Si-EH12K solid wires Suitable fluxes SWX 110, SWX 120 and SWX150
<b>SubCOR SL 840 HC</b>	Specifically designed for offshore construction, pressure vessels and double jointing for pipelines Gives excellent impact toughness properties also in stress relieved condition Suitable flux SWX 140
<b>SubCOR SL 735 1W-5W</b>	For Flux Cored Micro Injection (FMI) in combination with other cored and/or solid wires Available in 5 versions with specific chemistry for single, tandem and up to 5 wire set ups For significantly enhanced impact properties both in single and two run applications Suitable fluxes SWX 130 and SWX 135
<b>SubCOR SL 741</b>	Low alloyed cored wire electrode for high strength applications Designed for yield strength levels up to 550 MPa (80 ksi) Like all SubCOR wires it provides improved deposition rates compared to solid wires Suitable fluxes SWX 140 and SWX 150
<b>SubCOR SL 742</b>	Low alloyed wire for high strength applications Designed for yield strength levels up to 690 MPa (100 ksi) Suitable flux SWX 150
<b>SubCOR SL 745</b>	Low alloyed wire for high strength applications Designed for yield strength levels up to 890 MPa (130 ksi) Suitable flux SWX 150
<b>SubCOR SL 281 Cr</b>	Low alloyed wire for copper alloyed weathering steels Very good impact properties down to -40°C (-40°F) Suitable flux SWX 110
<b>SubCOR SL P1</b>	Low alloyed cored wire electrode for creep resisting steels Comparable strength level but significantly higher impact toughness than SDXS2Mo-EA2 solid wire Suitable flux SWX 150
<b>SubCOR SL P1 MOD</b>	The same basic features as SubCOR SL P1 but with an addition of vanadium Like all SubCOR wires it provides improved deposition rates compared to solid wires Suitable flux SWX 150
<b>SubCOR SL P11</b>	Low alloyed wire for creep resisting steels Comparable strength level but significantly higher impact toughness than SDX CrMo1-EB2R solid wire Suitable flux SWX 150
<b>SubCOR SL P12 MOD</b>	Low alloyed wire for creep resisting steels For joining of CrMoV-steels up to 550 °C (1020 °F) Suitable flux SWX 150
<b>SubCOR SL P36</b>	For economic joining of Mo alloyed creep resisting steels up to 500 °C (930°F) Ideal for production and repair welding Suitable flux SWX 150
<b>SubCOR SL P22</b>	For joining of creep resisting and pressure-hydrogen-resisting 2¼Cr1Mo-steels Meets requirements of step cooling due to very low weld metal contaminations Suitable flux SWX 150
<b>SubCOR SL P24</b>	For joining of creep resisting and pressure-hydrogen-resisting 2¼Cr1MoV-steels Meets requirements of step cooling due to very low weld metal contaminations Suitable flux SWX 150
<b>SubCOR SL P5</b>	High-alloy cored wire electrode for creep resisting steels For surfacing and joining of similar creep-resisting and pressure-hydrogen-resisting boiler tube steels Creep and scale resisting up to 600 °C (1100 °F) Suitable flux SWX 150
<b>SubCOR SL P9</b>	For surfacing and joining of similar creep-resisting and pressure-hydrogen-resisting boiler tube steels Creep and scale resisting up to 600 °C (1100 °F) Suitable flux SWX 150
<b>SubCOR SL P91</b>	For surfacing and joining of similar creep-resisting and pressure-hydrogen-resisting boiler tube steels Creep and scale resisting up to 600 °C (1100 °F) Suitable flux SWX 150
<b>SubCOR SL P92</b>	For surfacing and joining of similar creep-resisting and pressure-hydrogen-resisting boiler tube steels Creep and scale resisting up to 650 °C (1200 °F) Suitable flux SWX 150



# SAW Solid Wire and Strip Range

Typical chemical composition (%)												
Non- & low-alloyed solid wires			C	Si	Mn	P	S	Cr	Ni	Mo	Cu	Other
Product name	EN ISO	AWS										
SDX S1-EL12	EN ISO 14171: S1	AWS A5.17: EL12	0.08	0.07	0.49	0.010	0.013	0.05	0.03	0.01	0.06	
SDX EM13K		AWS A5.17: EM13K	0.08	0.57	1.10	0.011	0.012	0.06	0.03	0.02	0.05	
SDX S2	EN ISO 14171: S2		0.10	0.11	0.97	0.010	0.011	0.05	0.05	0.02	0.04	
SDX S2Si-EM12K	EN ISO 14171: S2Si	AWS A5.17: EM12K	0.09	0.22	1.12	0.009	0.011	0.04	0.04	0.01	0.03	
SDX S2Mo-EA2	EN ISO 14171: S2Mo	AWS A5.23: EA2	0.09	0.12	1.09	0.010	0.012	0.05	0.04	0.50	0.04	
SDX S3	EN ISO 14171: S3		0.11	0.12	1.55	0.010	0.009	0.04	0.03	0.01	0.05	
SDX S3Si-EH12K	EN ISO 14171: S3Si	AWS A5.17: EH12K	0.11	0.29	1.69	0.009	0.010	0.05	0.05	0.02	0.06	
SDX S3Mo-EA4	EN ISO 14171: S3Mo	AWS A5.23: EA4	0.12	0.10	1.45	0.010	0.012	0.04	0.03	0.52	0.05	
SDX S4-EH14	EN ISO 14171: S4	AWS A5.17: EH14	0.13	0.07	1.95	0.009	0.010	0.03	0.03	0.01	0.04	
SDX CrMo1-EB2R	EN ISO 24598: S CrMo1	AWS A5.23: EB2R	0.10	0.15	0.88	0.006	0.004	1.15	0.04	0.55	0.03	X<12
SDX CrMo2-EB3R	EN ISO 24598: S CrMo2	AWS A5.23: EB3R	0.11	0.14	0.60	0.004	0.005	2.45	0.05	1.02	0.04	X<12
SDX S2Ni1-ENi1	EN ISO 14171: S2Ni1	AWS A5.23: ENi1	0.09	0.12	0.96	0.09	0.07	0.04	0.97	0.02	0.05	
SDX S2Ni2-ENi2	EN ISO 14171: S2Ni2	AWS A5.23: ENi2	0.09	0.15	1.00	0.007	0.006	0.04	2.29	0.02	0.05	
SDX S2Ni1Cu	EN ISO 14171: S2Ni1Cu		0.10	0.22	0.99	0.010	0.009	0.25	0.79	0.02	0.49	
SDX S3Ni1Mo0.2-ENi5	EN ISO 14171: S3Ni1Mo0.2	AWS A5.23: ENi5	0.10	0.21	1.44	0.009	0.009	0.03	0.96	0.21	0.04	
SDX S3Ni1Mo-EF3	EN ISO 14171: S3Ni1Mo	AWS A5.23: EF3	0.12	0.11	1.72	0.010	0.008	0.03	0.92	0.55	0.05	
SDX S3Ni2.5CrMo	EN ISO 26304: S3Ni2.5CrMo		0.12	0.15	1.47	0.010	0.011	0.63	2.28	0.53	0.03	
SDX S3TiB			0.08	0.27	1.50	0.007	0.006	0.02	0.03	0.01	0.04	Ti 0.16. B 0.012
SDX S3MoTiB			0.07	0.25	1.30	0.009	0.007	0.03	0.03	0.53	0.05	Ti 0.15. B 0.013
Stainless solid wires			C	Si	Mn	P	S	Cr	Ni	Mo	N	Other
SDX 308L	EN ISO 14343: S 19 9 L	AWS A5.9: ER308L	0.02	0.48	1.80	0.012	0.010	20.2	10.3	0.2	0.04	
SDX 347	EN ISO 14343: S 19 9 Nb	AWS A5.9: ER347	0.03	0.42	1.72	0.013	0.012	19.8	9.8	0.1	0.07	Nb 0.7
SDX 316L	EN ISO 14343: S 19 12 3 L	AWS A5.9: ER316L	0.01	0.49	1.77	0.015	0.011	18.6	12.2	2.7	0.05	
SDX 317L	EN ISO 14343: S 19 13 4 L	AWS A5.9: ER317L	0.01	0.42	1.78	0.014	0.013	19.0	13.7	3.5	0.05	
SDX 309L	EN ISO 14343: S 23 12 L	AWS A5.9: ER309L	0.01	0.45	1.85	0.016	0.012	23.7	12.9	0.1	0.06	
SDX 309LMo	EN ISO 14343: S 23 12 2 L		0.01	0.37	1.49	0.016	0.015	23.4	13.2	2.6	0.04	
SDX 410NiMo		AWS A5.9: ER410NiMo	0.05	0.42	0.51	0.014	0.011	12.1	4.5	0.6	0.05	
SDX 2209	EN ISO 14343: S 22 9 3 N L	AWS A5.9: ER2209	0.01	0.48	1.50	0.016	0.010	22.9	8.3	3.2	0.15	
SDX 2594	EN ISO 14343: S 25 9 4 N L	AWS A5.9: ER2594	0.01	0.45	0.44	0.015	0.016	24.9	9.4	3.8	0.26	
Nickel base solid wires			C	Si	Mn	P	S	Cr	Ni	Mo	N	Other
SDX NiCrMo-3	EN ISO 18274: S Ni6625	AWS A5.14: ERNiCrMo-3	0.06	0.22	0.27	0.014	0.013	21.9	Bal.	9.1		Nb: 3.3 Fe: 1.1
SDX NiCr-3	EN ISO 18274: S Ni6082	AWS A5.14: ERNiCr-3	0.05	0.25	3.10	0.017	0.009	19.80	Bal.	0.13		Nb: 2.8 Fe: 1.0
Stainless strips			C	Si	Mn	P	S	Cr	Ni	Mo	N	Other
For SAW												
Cromastrip 308L	EN ISO 14343: B 19 9 L	AWS A5.9: EQ308L	0.01	0.4	1.7	0.014	0.001	20.3	10.3	0.1	0.05	
Cromastrip 347	EN ISO 14343: B 19 9 Nb	AWS A5.9: EQ347	0.02	0.4	1.7	0.014	0.001	19.7	10.5	0.0	0.05	Nb 0.5
Cromastrip 316L	EN ISO 14343: B 19 12 3 L	AWS A5.9: EQ316L	0.02	0.4	1.6	0.020	0.001	18.3	12.6	2.8	0.05	
Cromastrip 309L	EN ISO 14343: B 23 12 L	AWS A5.9: EQ309L	0.01	0.4	1.6	0.011	0.001	24.0	13.2	0.1	0.05	
Cromastrip 309LNb	EN ISO 14343: B 23 12 L Nb		0.02	0.4	2.1	0.014	0.001	23.8	12.5	0.2	0.05	Nb 0.6
For ESW												
Cromastrip 21.11 L	EN ISO 14343: B 21 11 L		0.02	0.3	1.7	0.014	0.001	21.2	11.2	0.1	0.03	
Cromastrip 21.13.3 L			0.01	0.4	1.7	0.017	0.001	20.3	14.3	2.8	0.04	
Cromastrip 21.11 LNb	EN ISO 14343: B 21 11 L Nb		0.01	0.3	1.7	0.015	0.001	21.3	11.1	0.1	0.05	Nb 0.6
Nickel base strips			C	Si	Mn	P	S	Cr	Ni	Mo	N	Other
Cromastrip NiCrMo-3	EN ISO 18274: Ni6625	AWS A5.14: EQNiCrMo-3	0.05	0.1	0.3	0.011	0.002	22.0	Bal.	9.0	0.05	Nb 3.5 Fe 0.4
Cromastrip NiCr-3	EN ISO 18274: Ni6082	AWS A5.14: EQNiCr-3	0.05	0.2	3.0	0.013	0.002	22.0	Bal.	0.1	0.05	Nb 2.5 Fe <1.0

## Flux selection by SDX solid wire

SDX solid wire	SWX 110	SWX 120	SWX 130	SWX 135	SWX 140	SWX 150
SDX S2Si-EM12K	F7A4-EM12K	F7A6-EM12K	F7A4-EM12K	F7A4-EM12K	F7A6-EM12K	F7A6-EM12K
SDX EM13K-S	F7A4-EM13K	F7A4-EM13K			F7A4-EM13K	F7A4-EM13K
SDX S3Si-EH12K	F7A6-EH12K		F7A6-EH12K			F7A8-EH12K
SDX S3Si-EH12K	F7P6-EH12K					F7P8-EH12K
SDX S2Mo-EA2	F7A4-EA2-A4	F7A6-EA2-A4	F7A4-EA2-A4	F7A4-EA2-A4	F7A6-EA2-A4	F7A6-EA2-A2
SDX S2Mo-EA2	F7P4-EA2-A4	F7P6-EA2-A4	F7P4-EA2-A4	F7P4-EA2-A4	F7P6-EA2-A4	F7P6-EA2-A2
SDX CrMo1-EB2R						F8P2-EB2R-B2
SDX CrMo2-EB3R						F8P0-EB3R-B3
SDX S2Ni1-ENi1						F7A8-ENi1-N1
SDX S2Ni1-ENi1						F7P8-ENi1-N1
SDX S2Ni2-ENi2						F8A10-ENi2-Ni2
SDX S2Ni2-ENi2						F8P10-ENi2-Ni2
SDX S3Ni1Mo0.2-ENi5	F8A6-ENi5-Ni5					F8A8-ENi5-Ni5
SDX S3Ni1Mo0.2-ENi5						F8P6-ENi5-Ni5
SDX S3Ni1Mo-EF3						F10A8-EF3-F3

## Flux selection by SubCOR cored wire

SubCOR cored wire	SWX 110	SWX 120	SWX 130	SWX 135	SWX 140	SWX 150
SubCOR EM12K-S	F7A4-EC1	F7A6-EC1	F7A6-EC1	F7A4-EC1	F7A6-EC1	F7A4-EC1
SubCOR EM13K-S	F7A6-EC1	F7A8-EC1	F7A6-EC1	F7A6-EC1	F7A8-EC1	F7A8-EC1
SubCOR EM13K-S	F7P6-EC1	F6P8-EC1	F7P6-EC1	F7P6-EC1		F6P8-EC1
SubCOR EM13K-S MOD	F7A6-EC1	F7A8-EC1	F7A6-EC1	F7A6-EC1	F7A10-EC1	F7A8-EC1
SubCOR EM13K-S MOD	F7P6-EC1	F7P8-EC1	F7P8-EC1	F7P8-EC1	F7P8-EC1	F7P8-EC1
SubCOR B2-S						F9P2-ECB2-B2
SubCOR B3-S						F9P2-ECB3-B3
SubCOR 92-S		F8A10-ECM1-M1			F8A10-ECM1-M1	F8A10-ECM2-M2
SubCOR 92-S		F8P8-ECM1-M1			F8P8-ECM1-M1	F8P8-ECM2-M2
SubCOR F2-S						F10A10-ECF2-F2
SubCOR F2-S						F10P10-ECF2-F2
SubCOR 100F3-S					F10A10-ECF3-F3	F10A10-ECF3-F3
SubCOR 100F3-S					F10P8-ECF3-F3	F10P10-ECF3-F3
SubCOR 120-S						F11A10-ECM4-M4
SubCOR Ni1-S						F7A8-ECNi1-Ni1
SubCOR Ni1-S						F7P10-ECNi1-Ni1
SubCOR W-S						F7A6-ECW



# Flux Selection by AWS wire classification

Alloy	Electrode/Flux Classification	Electrode Trade Name Tradename	Flux					
			SWX 110	SWX 120	SWX 130	SWX 135	SWX 140	SWX 150
Carbon steel solid wire electrodes – AWS A5.17								
	F7A4-EM12K	SDX S2Si-EM12K	✓		✓	✓		
	F7A4-EM13K	SDX EM13K	✓	✓			✓	✓
	F7A6-EM12K	SDX S2Si-EM12K		✓			✓	✓
	F7A6-EH12K	SDX S3Si-EH12K	✓		✓			
	F7P6-EH12K	SDX S3Si-EH12K	✓					
	F7A8-EH12K	SDX S3Si-EH12K						✓
	F7P8-EH12K	SDX S3Si-EH12K						✓
Carbon steel metal-cored (composite) electrodes – AWS A5.17								
	F6P8-EC1	SubCOR EM13K-S		✓			✓	✓
	F7A4-EC1	SubCOR EM12K-S	✓			✓		✓
	F7A6-EC1	SubCOR EM12K-S		✓	✓		✓	
		SubCOR EM13K-S	✓		✓	✓		
		SubCOR EM13K-S MOD	✓		✓	✓		
	F7P6-EC1	SubCOR EM13K-S	✓		✓	✓		
		SubCOR EM13K-S MOD	✓					
	F7A8-EC1	SubCOR EM13K-S		✓			✓	✓
		SubCOR EM13K-S MOD		✓				✓
	F7P8-EC1	SubCOR EM13K-S MOD		✓	✓	✓	✓	✓
	F7A10-EC1	SubCOR EM13K-S MOD					✓	
Low-alloy solid wire electrodes – AWS A5.23								
A2	F7A4-EA2-A4	SDX S2Mo-EA2	✓		✓	✓		
	F7P4-EA2-A4	SDX S2Mo-EA2	✓		✓	✓		
	F7A6-EA2-A4	SDX S2Mo-EA2		✓			✓	
	F7A6-EA2-A2	SDX S2Mo-EA2						✓
	F7P6-EA2-A4	SDX S2Mo-EA2		✓			✓	
	F7P6-EA2-A2	SDX S2Mo-EA2						✓
Ni	F7A8-ENi1-Ni1	SDX S2Ni1-ENi1						✓
	F7P8-ENi1-Ni1	SDX S2Ni1-ENi1						✓
	F8A6-ENi5-Ni5	SDX S3Ni1Mo0.2-ENi5	✓					
	F8P6-ENi5-Ni5	SDX S3Ni1Mo0.2-ENi5						✓
	F8A8-ENi5-Ni5	SDX S3Ni1Mo0.2-ENi5						✓
	F8A10-ENi2-Ni2	SDX S2Ni2-ENi2						✓
	F8P10-ENi2-Ni2	SDX S2Ni2-ENi2						✓
B	F8P0-EB3R-B3	SDX CrMo2-EB3R						✓
	F8P2-EB2R-B2	SDX CrMo1-EB2R						✓
F	F10A8-EF3-F3	SDX S3Ni1Mo-EF3						✓
Low-alloy metal-cored (composite) electrodes – AWS A5.23								
W	F7A6-ECW-W	SubCOR W-S						✓
Ni	F7A8-ECNi1-Ni1	SubCOR N1-S						✓
	F7P10-ECNi1-Ni1	SubCOR N1-S						✓
M1	F8P8-ECM1-M1	SubCOR 92-S		✓			✓	✓
	F8A10-ECM1-M1	SubCOR 92-S		✓			✓	✓
B	F9P2-ECB2-B2	SubCOR B2-S						✓
	F9P3-ECB3-B3	SubCOR B3-S						✓
F	F10P8-ECF3-F3	SubCOR 100F3-S					✓	
	F10A10-ECF3-F3	SubCOR 100F3-S					✓	✓
	F10P10-ECF3-F3	SubCOR 100F3-S						✓
	F10A10-ECF2-F2	SubCOR F2-S						✓
	F10P10-ECF2-F2	SubCOR F2-S						✓
M4	F11A10-ECM4-M4	SubCOR 120-S						✓

# SWX 110

EN ISO 14174: S A AB 1 67 AC H5

Flux /wire combinations for the submerged arc welding of non-and low-alloyed steels

## Description

Hobart SWX 110 is a versatile and universally applied agglomerated welding flux. It has a carefully chosen aluminate-basic formulation - with a basicity between neutral and basic - providing a set of welding characteristics that makes the flux suited for a wide range of submerged arc welding applications in a variety of industries. It combines high travel speeds and excellent slag detachability with good low-temperature impact toughness down to -40°C (-40°F). Suited for single- and multi-run welding with smooth weld bead appearance and self detaching slag. It has a wide parameter box and performs equally well in single-wire, twin- and tandem welding, making it the perfect choice for productive welding of heavy sections. All of this makes SWX 110 an excellent multi-application flux

on the shop floor. SWX 110 can be used with a range of wires to cover mild steel and medium tensile fine-grained steel. SWX 110 is applied in general construction, machine and heavy equipment building, pressure vessel fabrication, shipbuilding and water and sewage pipes. Typical shipbuilding applications are the single- or double-sided welding of ship panels. Use of the flux in combination with Hobart cored wires offers further opportunities to improve weld metal quality, making use of unique cored wire properties. The flux is delivered in Hobart humidity proof packaging - EAE bag or DoubleBag - eliminating the need to re-dry the flux.

- General construction
- Double jointing
- Heavy equipment
- Bridge building
- Shipbuilding
- Pressure vessels
- Heavy beams
- Tank building
- Water and sewage pipes

## Flux characteristics

Flux type	Aluminate-Basic
Basicity index	1.4 (Boniszewski)
Alloy transfer	Slightly Si and Mn alloying
Density	1.2 kg/litre
Grain size	0.2-1.6 mm /12-65 mesh
HDM	< 5 ml/100 g weld metal
Current	DC+/AC
Re-drying unopened bag	Not required
Re-drying opened bag	See storage and handling recommendations


## Flux main components

AL <sub>2</sub> O <sub>3</sub> + MnO	CaO + MgO	SiO <sub>2</sub> + TiO <sub>2</sub>	CaF <sub>2</sub>
~ 35%	~ 25%	~ 20%	~ 15%

## Metallurgical behaviour

The diagrams show the typical weld metal analysis in relation to wire analysis for silicon and manganese.

Single wire, ø 4.0 mm (5/32"), DC+, 30 V, 60 cm/min (24"/min)

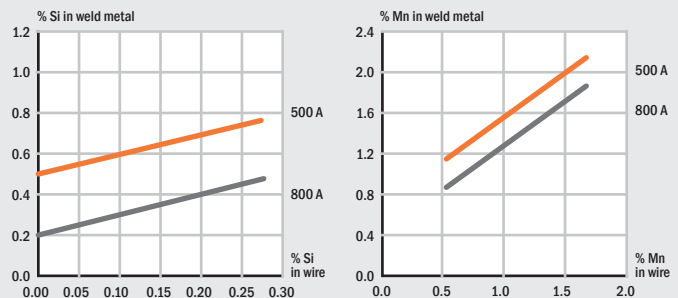

Flux SWX 110 - Classifications				Mechanical properties																
With wire		EN ISO	AWS	Re/Rp0.2 MPa	Rm MPa	A %	CVN J					YS ksi	TS ksi	E %	CVN ft-lbf					
								0°C	-20°C	-30°C	-40°C	-46°C								
SDX EM13K	AW	A5.17: F7A4-EM13K										75	87	28	22					
SDX S2	AW	14171-A: S 38 4 AB S2		420	500	26	130	110	65											
SDX S2Si-EM12K	AW	14171-A: S 38 4 AB S2Si		A5.17: F7A4-EM12K	420	500	26	130	100	60				71	83	29	48	35		
SDX S3Si-EH12K*	AW	14171-A: S 42 4 AB S3Si		A5.17: F7A6-EH12K	450	560	28	110		65	50	76					88	27	54	38
	SR <sup>1</sup>			A5.17: F7P6-EH12K	440	550	28	100		55	40	67					83	28	58	29
SDX S2Mo-EA2	AW	14171-A: S 46 2 AB S2Mo		A5.23: F7A4-EA2-A4	510	590	24	90	70	50				80	90	26	58	33		
	SR <sup>1</sup>			A5.23: F7P4-EA2-A4	470	560	24	70	40					74	86	27	49	33		
	TR	14171-A: S 4T 2 AB S2Mo						50												
SDX S3Ni1Mo0.2-ENi5	AW	14171-A: S 50 4 AB S3Ni1Mo0.2		A5.23: F8A6-ENi5-Ni5	570	640	24	90		75	65	40	88	97	25	63	37			
SDX S2Ni1Cu	AW	14171-A: S 46 3 AB S2Ni1Cu		485				570	26	70		55								
SubCOR EM12K-S	AW	A5.17: F7A4-EC1										60	71	30	45					
SubCOR EM13K-S	AW	A5.17: F7A6-EC1										64	73	28	97			75		
	SR <sup>1</sup>	A5.17: F7P6-EC1										64	77	32	264			127		
SubCOR EM13K-S MOD	AW	A5.17: F7A6-EC1										76	84	29	115			50		
	SR <sup>1</sup>	A5.17: F7P6-EC1										68	80	31	143			105		
SubCOR SL 731	AW	14171-A: S 46 4 AB T3		490	600	29	150		115											
	SR <sup>1</sup>			490	600	29	150		115											
SubCOR SL 281 Cr	AW	14171-A: S 46 4 AB TZ		490	590	25	100		80											

AW: as welded, all weld metal. SR: stress relieved, all weld metal. TR: two-run. SR<sup>1</sup>: PWHT 1150°F (620°C)/1 h.

\* Use with precaution. In certain applications, the manganese content may reach critical levels, leading to hot cracking.



# SWX 110 (continued)

EN ISO 14174: S A AB 1 67 AC H5

Flux/wire combinations for the submerged arc welding of non-and low-alloyed steels

## Flux SWX 110 - Chemical composition all weld metal, typical values

With wire	%C	%Si	%Mn	%Mo	%Ni	%Cu	%Cr
SDX EM13K	0.06	0.3	1.2				
SDX S2	0.06	0.3	1.2				
SDX S2Si-EM12K	0.06	0.5	1.3				
SDX S3Si-EH12K	0.07	0.5	1.9				
SDX S3Ni1Mo0.2	0.09	0.25	1.4	0.2	0.9		
SDX S2Ni1Cu	0.08	0.4	1.3		0.7	0.5	
SDX S2Mo-EA2	0.06	0.3	1.3	0.5			
SubCOR EM12K-S	0.05	0.2	1.2				
SubCOR EM13K-S	0.06	0.3	1.2				
SubCOR EM13K-S MOD	0.07	0.4	1.3				
SubCOR SL 731	0.05	0.3	1.5				
SubCOR SL 281 Cr	0.12	0.6	1.3		0.6	0.5	0.5

## Materials to be welded

Steel group	Typical examples of steel types	Impact requirement ≥47 J (≥20 ft-lbf)	Flux SWX 110 with wire:
<b>Normal strength steel</b>			
Rel ≤ 355 MPa	S235JR, S275JR, A106 Gr. B, A333 Gr. 6, P235GH, S275JO, P295GH	-20°C	SDX S2
		-40°C	SDX S2, SDX S2Si-EM12K
Rel ≥ 355 MPa	S420N, S460ML, P420ML2, S420MCD, S420G2+M, X60, L450	-20°C	SDX S2Mo-EA2
		-40°C	SDX S2, SDX S2Si-EM12K,
TS > 58 ksi	A36, A709 Gr. 36,	-40°F	SubCOR EM12K-S
		-100°F	SubCOR EM13K-S, SubCOR EM13K-S MOD
TS > 65 ksi	A572 Gr.50, A709 Gr. 50, A709 Gr. 50S, A992	-40°F	SubCOR EM12K-S
		-100°F	SubCOR EM13K-S, SubCOR EM13K-S MOD
TS > 70 ksi	A588, A516 Gr.70	-40°F	SubCOR EM12K-S
		-100°F	SubCOR EM13K-S, SubCOR EM13K-S MOD
<b>High strength steel</b>			
Rel ≥ 420 MPa	S420N, S460ML, P420ML2, S420MCD, S420G2+M, X60, L450	-20°C	SDX S2Mo-EA2, SDX S2Mo-EA2
		-40°C	SDX S3Si-EH12K, SubCOR SL 731
Rel ≥ 460 MPa	S460M, S460ML, S460ML2, S460MCD, S460G2+M, X65, L450	-20°C	SDX S2Mo-EA2
		-40°C	SubCOR SL 731
Rel ≥ 500 MPa	S500QL, S500QL1, P500QL1, P500QL2, X70, S500G2+M	-40°C	SDX S3Ni1Mo0.2-ENi5
<b>Shipbuilding steel</b>			
	A to D, AH36 to EH36	-20°C	SDX S2Mo-EA2
		-40°C	SDX S2, SDX S2Si-EM12K
			SDX S3Si-EH12K, SubCOR SL 731
<b>Weather resistant steel</b>			
Rel ≤ 355	S235JOW, S355J2WP, S355J2G2W, COR-TEN, A242-type1, A588	-20°C	SDX S2Ni1Cu, SubCOR SL 281 Cr

## Approvals

With wire	CE	CWB	TÜV
SDX S2	✓		✓
SDX S2Si-EM12K	✓	F49A4-EM12K*	✓
SDX S2Mo-EA2	✓	F8A6-EA2-A4*	✓
SDX S3Si-EH12K	✓	F49A6-EH12K*	✓
SubCOR EM13K-S Mod	✓	F49A6-EC1*	✓
SubCOR SL 731	✓		
SubCOR SL 281 Cr	✓		

For the complete approval list please see Product Data Sheet or contact the ITW Welding sales office. \* Pending

## Packaging data

Flux unit net weight	Kg	Lbs
Aluminium/PE Bag EAE*	25	55
DoubleBag	1000	2200

\*EAE Excess Air Evacuation

# SWX 120

EN ISO 14174: S A AB 1 57 AC H5

Flux/wire combinations for the submerged arc welding of non-and low-alloyed steels

## Description

Hobart SWX 120 is specifically designed for the wind tower manufacturing industry where high integrity longitudinal and circumferential welds are the challenge and productive welding a prerequisite. The formulation of this aluminate-basic flux has been adapted towards a higher basicity while maintaining the good welding characteristics of a lower basicity flux. The result is a "production" flux that yields remarkably good low-temperature impact toughness down to -50°C (-58°F), using SDX S2 or SDX S2Si-EM12K welding wires. This flux guarantees uniform chemistry and mechanical properties throughout the heavy, multi-layer welds that are familiar to this industry. SWX 120 has a high current carrying capacity and allows high travel speeds. The slag is easily removed

from the first layers in commonly applied narrow Y-joints and self-detaching in subsequent filler and capping layers. Very well suited for single, twin, tandem and tandem-twin wire welding offering higher welding productivity and increased efficiency. Other industries with similar requirements, such as pressure vessel fabrication and general construction, will benefit equally well from this outstanding welding flux. Use of the flux in combination with Hobart cored wires offers further opportunities to improve weld metal quality, making use of unique cored wire properties.

The flux is delivered in Hobart humidity proof packaging - EAE bag or DoubleBag - eliminating the need to re-dry the flux.

- Wind towers
- Pressure vessels
- General construction
- Tank building

## Flux characteristics

Flux type	Aluminate-Basic
Basicity index	1.9 (Boniszewski)
Alloy transfer	Slightly Mn alloying
Density	~1.2 kg/litre
Grain size	0.2-1.6 mm / 12-65 mesh
HDM	< 5 ml/100 g weld metal
Current	DC+/AC
Re-drying unopened bag	Not required
Re-drying opened bag	See storage and handling recommendations


## Flux main components

AL <sub>2</sub> O <sub>3</sub> + MnO	CaO + MgO	SiO <sub>2</sub> + TiO <sub>2</sub>	CaF <sub>2</sub>
~ 35%	~ 25%	~ 20%	~ 20%

## Metallurgical behaviour

The diagrams show the typical weld metal analysis in relation to wire analysis for silicon and manganese.

Single wire, ø 4.0 mm (5/32"), DC+, 30 V, 60 cm/min (24"/min)

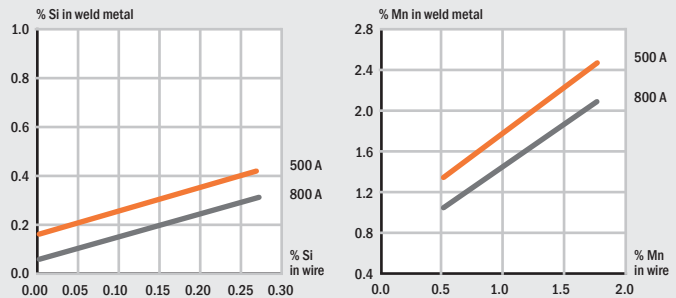

## Flux SWX 120 - Classifications

With wire		EN ISO	AWS	Re/Rp0.2 MPa	Rm MPa	A %	CVN J					YS ksi	TS ksi	E %	CVN ft-lbf	
-20°C -40°C -50°C -60°C											0°F -20°F -40°F -60°F -80°F -100°F					
SDX EM13K	AW	A5.17: F7A4-EM13K									77	87	29	40		
SDX S2	AW	14171-A: S 38 5 AB S2		420	500	26	120	95	70	45						
SDX S2Si-EM12K	AW	14171-A: S 38 5 AB S2Si		A5.17: F7A6-EM12K	430	510	26	130	100	75	45	66	78	27	76	68
SDX S2Mo-EA2	AW	14171-A: S 46 4 AB S2Mo		A5.23: F7A6-EA2-A4	500	590	24	90	60		73	83	25		69	
	SR <sup>1</sup>			A5.23: F7P6-EA2-A4	490	575	24	90	60	45	68	91	29		44	30
	TR	14171-A: S 4T 3 AB S2Mo						65	40							
SDX S3Si-EH12K*	AW	14171-A: S 46 4 AB S3Si		490	580	27	120	80	50							
	SR <sup>1</sup>			480	570	27	110	70	45							
	TR	14171-A: S 3T 2 AB S3Si					55	30			29					
SubCOR EM12K-S	AW	A5.17: F7A6-EC1									60	70	32		110	
SubCOR EM13K-S	AW	A5.17: F7A8-EC1									58	71	29		105	
	SR <sup>1</sup>	A5.17: F6P8-EC1									51	66	34		143	142
SubCOR EM13K-S MOD	AW	A5.17: F7A10-EC1									72	82	29		161	105
	SR <sup>1</sup>	A5.17: F7P8-EC1									67	80	29	221	134	
SubCOR 92-S	AW	A5.23: F8A10-ECM1-M1									79	93	26		85	52
	SR <sup>2</sup>	A5.23: F8P8-ECM1-M1									71	84	27	103	77	
SubCOR SL 731**	AW	14171-A: S 46 4 AB T3	A5.23: F8A4-ECG	500	600	27	145	125		54	111	121	22		55	48
	SR <sup>1</sup>			480	580	26	140	120		50						

AW: as welded, all weld metal. SR: stress relieved, all weld metal. TR: two-run. \* Use with precaution. In certain applications, the manganese content may reach critical levels, leading to hot cracking.  
 SR<sup>1</sup>: 1150°F (620°C) / 1 h. SR<sup>2</sup>: 1135°F (605°C) / 1 h. \*\* Depends on the type of solid wire used

# SWX 120 (continued)

EN ISO 14174: S A AB 1 57 AC H5

Flux/wire combinations for the submerged arc welding of non-and low-alloyed steels

## Flux SWX 120 - Chemical composition all weld metal, typical values

With wire	%C	%Si	%Mn	%Cr	%Ni	%Mo
SDX-EM13K	0.05	0.2	1.2			
SDX S2	0.07	0.2	1.4			
SDX S2Si-EM12K	0.07	0.3	1.4			
SDX S2Mo-EA2	0.07	0.2	1.4			0.5
SDX S3Si-EH12K	0.10	0.2	2.0			
SubCOR EM12K-S	0.05	0.2	1.2			
SubCOR EM13K-S	0.05	0.2	1.2			
SubCOR EM13K-S MOD	0.08	0.3	1.2			
SubCOR 92-S	0.08	0.2	1.3		1.6	0.2
SubCOR SL 731	0.06	0.5	2.1			

## Materials to be welded

Steel group	Typical examples of steel types	Impact requirement ≥47 J (≥20 ft-lbf)	Flux SWX 120 with wire:
<b>Normal strength steel</b>			
Rel ≤ 355 MPa	S235JR, A106 Gr. B, A333 Gr. 6, P235GH, S275JO, S275JR, P295GH	-30°C	SDX S2Mo-EA2
		-50°C	SDX S2, SDX S2Si-EM12K
Rel ≥ 355 MPa	S355J2, S355N, P355NL1, L360, S355MCD, S355ML, P355GH	-20°C	SDX S3Si-EH12K
		-30°C	SDX S2Mo-EA2
		-50°C	SDX S2, SDX S2Si-EM12K
TS > 58 ksi	A36, A709 Gr. 36	-60°F	SubCOR EM12K-S
		-80°F	SubCOR EM13K-S
		-100°F	SubCOR EM13K-S MOD
TS > 65 ksi	A572 Gr. 50, A709 Gr. 50, A709 Gr. 50S, A992	-60°F	SubCOR EM12K-S
		-80°F	SubCOR EM13K-S
		-100°F	SubCOR EM13K-S MOD
<b>High strength steel</b>			
Rel ≥ 420 MPa	S420N, S460ML, P420ML2, S420MCD, S420G2+M, L450	-30°C	SDX S2Mo-EA2
		-40°C	SDX S3Si-EH12, SubCOR SL 731
Rel ≥ 460 MPa	S460M, S460ML, S460ML2, S460MCD, S460G2+M, L450	-30°C	SDX S2Mo-EA2
		-40°C	SDX S3Si-EH12, SubCOR SL 731
TS > 70 ksi	A588, A516 Gr. 70	-60°F	SubCOR EM12K-S
		-80°F	SubCOR EM13K-S
		-100°F	SubCOR EM13K-S MOD
<b>Creep resistant steel</b>			
0.5% Mo	P295GH, P355GH, 16Mo3, 17Mo3, 14Mo6	-30°C	SDX S2Mo-EA1

## Approvals

With wire	CE	CWB	DB	TÜV
SDX-EM13K				
SDX S2	✓		✓	✓
SDX S2Si-EM12K	✓	F49A4-EM12K*		
SDX S2Mo-EA2	✓	F8A6-EA2-A4*		✓
SDX S3Si-EH12K		F49A6-EH12K*		
SubCOR EM13K-S MOD		F49A6-EC1		

For the complete approval list please see Product Data Sheet or contact the ITW Welding sales office. \*Pending

## Packaging data

Flux unit net weight	Kg	Lbs
Aluminium/PE Bag EAE*	25	55
DoubleBag	1000	2200

\*EAE Excess Air Evacuation



# SWX 130

EN ISO 14174: S A AB 1 67 AC H5

Flux/wire combinations for the submerged arc welding of non-and low-alloyed steels

## Description

HOBART SWX 130 is the welding flux that answers the call from longitudinal pipe mill manufacturers for increased welding speed and good mechanical properties in two-run welding. Thanks to its high current carrying capacity, it is very well suited for multi-wire welding with up to five wires. At high welding speeds, it produces the desired flat and wide bead profile with absence of peaks, which provides savings in pipe coating operations.

Slag is self-detaching. With the right combination of wires, steel grades up to X100 can be welded with matching mechanical properties. The flux is delivered in Hobart humidity proof packaging - EAE bag or DoubleBag - eliminating the need to re-dry the flux.

- Longitudinal pipe mills

## Flux characteristics

Flux type	Aluminate-Basic
Basicity index	1.5 (Boniszewski)
Alloy transfer	Slightly Si and Mn alloying
Density	1.2 kg/litre
Grain size	0.2-2.0 mm / 10-65 mesh
HDM	< 5 ml/100 g weld metal
Current	DC+/AC
Re-drying unopened bag	Not required
Re-drying opened bag	See storage and handling recommendations


## Flux main components

AL <sub>2</sub> O <sub>3</sub> + MnO	CaO + MgO	SiO <sub>2</sub> + TiO <sub>2</sub>	CaF <sub>2</sub>
~ 30%	~ 25%	~ 20%	~ 15%

## Metallurgical behaviour

The diagrams show the typical weld metal analysis in relation to wire analysis for silicon and manganese.

Single wire, ø 4.0 mm (5/32"), DC+, 30 V, 60 cm/min (24"/min)

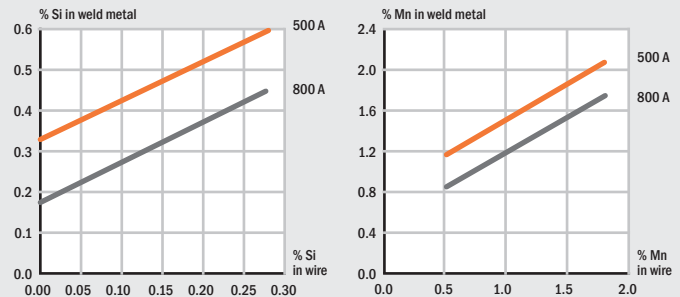

Flux SWX 130 - Classifications				Mechanical properties									
With wire		EN ISO	AWS	Re/Rp0.2 MPa	Rm MPa	A %	CVN J						
				0°C -20°C -30°C -40°C -50°C						YS ksi	TS ksi	E %	CVN ft-lbf
										0°F -20°F -40°F -60°F -80°F -100°F			
SDX S2	AW	14171-A: S 38 4 AB S2		430	520	27	110	75	60				
SDX S2Si-EM12K	AW	14171-A: S 38 4 AB S2Si	A5.17: F7A4-EM12K	430	520	27	100	70	50	69	82	27	23
SDX S3Si-EH12K	AW	14171-A: S 46 6 AB S3Si	A5.17: F7A6-EH12K	490	550	29				81	91	27	46
SDX S2Mo-EA2	AW	14171-A: S 46 2 AB S2Mo	A5.23: F7A4-EA2-A4	520	590	24	100	70	40	80	90	27	39
SDX S2Mo-EA2	SR <sup>1</sup>		A5.23: F7P4-EA2-A4							76	88	28	32
SDX S3Mo-EA4	AW	14171-A: S 50 2 AB S3Mo		580	670	23		55	40				
SubCOR EM12K-S	AW		A5.17: F7A6-EC1							60	71	29	84
SubCOR EM13K-S	AW		A5.17: F7A6-EC1							65	77	31	70 53
	SR <sup>1</sup>		A5.17: F7P6-EC1							58	72	33	84 69
SubCOR EM13K-S MOD	AW		A5.17: F7A6-EC1							77	87	27	50
	SR <sup>1</sup>		A5.17: F7P8-EC1							68	83	29	102 47
Mechanical properties of two-run pipe joint (high dilution)													
SDX S2Mo-EA2	TR			480	550	23		100	80 50				
SDX S3Mo-EA4	TR			510	590	20		70					
SDX S3TiB	TR			560	700	20			45				
SDX S3MoTiB	TR			630	700	25		200	180 120				
SubCOR SL 735-1W-5W*	TR			480	600	24		60	50				

Mechanical properties of pipe welds in the two run technique depend on the chemical composition of the base material. AW: As welded, all weld metal. TR: Two Run  
\* Depends on the type of solid wire used. SR<sup>1</sup>: PWHT 1150°F (620°C)/1 h.

# SWX 130 (continued)

EN ISO 14174: S A AB 1 67 AC H5

Flux/wire combinations for the submerged arc welding of non-and low-alloyed steels

## Flux SWX 130 - Chemical composition all weld metal, typical values

With wire	%C	%Si	%Mn	%Mo	%Ti	%B
SDX S2	0.06	0.2	1.3			
SDX S2Si-EM12K	0.06	0.3	1.3			
SDX S3Si-EH12K	0.08	0.3	1.6			
SDX S2Mo-EA2	0.05	0.4	1.4	0.5		
SDX S3Mo-EA4	0.08	0.4	1.6	0.5		
SubCOR EM12K-S	0.05	0.2	1.2			
SubCOR EM13K-S	0.06	0.4	1.2			
SubCOR EM13K-S MOD	0.06	0.4	1.1			
<b>Weld metal analyses of two-run pipe joint (high dilution)</b>						
SDX S3TiB	0.06	0.5	1.6		0.024	0.0024
SDX S3MoTiB	0.06	0.5	1.4	0.3	0.022	0.0024
SubCOR SL 735-1W-5W	Depends on the type of solid wire used.					

## Materials to be welded

Steel group	Typical examples of steel types	Impact requirement ≥47 J (≥20 ft-lbf)	Flux SWX 130 with wire:
<b>Normal strength steel</b>			
Rel ≤ 355 MPa	X42, X46, L235, L265, L295, L320	-40°C	SDX S2Mo-EA2
		-50°C	SDX S3MoTiB
Rel ≥ 355 MPa	X52, L355, L360, L385L, 390, L415	-40°C	SDX S2Mo-EA2
		-50°C	SDX S3MoTiB
TS > 58 ksi	A36, A709 Gr. 36,	-60°F	SubCOR EM12K-S
		-80°F	SubCOR EM13K-S, SubCOR EM13K-S MOD
TS > 65 ksi	A572 Gr. 50, A709 Gr. 50, A709 Gr. 50S, A992	-60°F	SubCOR EM12K-S
		-80°F	SubCOR EM13K-S, SubCOR EM13K-S MOD
<b>High strength steel</b>			
Rel ≥ 420 MPa	X56, X60, L445, L450	-40°C	SDX S2Mo-EA2
		-50°C	SDX S3MoTiB
Rel ≥ 460 MPa	X65, X70, X80	-20°C	SDX S3Mo-EA4, SubCOR SL 735-1W-5W
		-40°C	SDX S3TiB
		-50°C	SDX S3MoTiB
TS > 70 ksi	A588, A516 Gr. 70	-60°F	SubCOR EM12K-S
		-80°F	SubCOR EM13K-S, SubCOR EM13K-S MOD

## Approvals

With wire	CE
SDX S2Mo-EA2	✓
For the complete approval list please see Product Data Sheet or contact the ITW Welding sales office	

## Packaging data

Flux unit net weight	Kg	Lbs
Aluminium/PE Bag EAE*	25	55
DoubleBag	1000	2200
*EAE Excess Air Evacuation		

# SWX 135

EN ISO 14174: S A AB 1 67 AC H5

Flux/wire combinations for the submerged arc welding of non-and low-alloyed steels

## Description

Hobart SWX 135 is an aluminate-basic flux specifically developed for spiral pipe mills. The flux is suited for two-run applications and can be used with systems with up to 3 wires. It gives flat welds with smooth wetting and absence of so called china hats. This weld appearance is cost saving in later coating operations.

It has a good current carrying capacity. Slag is self-detaching. The flux is delivered in Hobart humidity proof packaging - EAE bag or DoubleBag - eliminating the need to re-dry the flux.

- Spiral pipe mills

## Flux characteristics

Flux type	Aluminate-Basic
Basicity index	1.3 (Boniszewski)
Alloy transfer	Slightly Si and Mn alloying
Density	1.2 kg/litre
Grain size	0.2-2.0 mm /10-65 mesh
HDM	< 5 ml/100 g weld metal
Current	DC+/AC
Re-drying unopened bag	Not required
Re-drying opened bag	See storage and handling recommendations


## Flux main components

AL <sub>2</sub> O <sub>3</sub> + MnO	CaO + MgO	SiO <sub>2</sub> + TiO <sub>2</sub>	CaF <sub>2</sub>
~ 35%	~ 20%	~ 25%	~ 15%

## Metallurgical behaviour

The diagrams show the typical weld metal analysis in relation to wire analysis for silicon and manganese.

Single wire, ø 4.0 mm (5/32"), DC+, 30 V, 60 cm/min (24"/min)

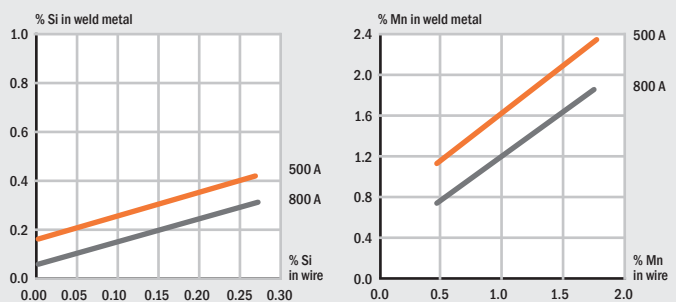

## Flux SWX 135 - Classifications

With wire		EN ISO	AWS	Re/Rp0.2 MPa	Rm MPa	A %	CVN J			YS ksi	TS ksi	E %	CVN ft-lbf
0°C -40°C -50°C										0°F -20°F -40°F -60°F -80°F -100°F			
SDX S2	AW	14171-A: S 38 4 AB S2		430	520	27	110	75	40				
SDX S2Si-EM12K	AW	14171-A: S 38 4 AB S2	A5.17: F7A4-EM12K	410	500	27	150	90	55	65	78	26	42
SDX S2Mo-EA2	AW	14171-A: S 46 2 AB S2Mo	A5.23: F7A4-EA2-A4	510	590	23	90	45	30	71	83	24	43
SDX S2Mo-EA2	SR <sup>1</sup>		A5.23: F7P4-EA2-A4							64	79	28	23
SDX S3Mo-EA4	AW	14171-A: S 50 2 AB S3Mo		570	670	23	70	50					
SubCOR EM12K-S	AW		A5.17: F7A4-EC1							58	71	29	74
SubCOR EM13K-S	AW		A5.17: F7A6-EC1							59	71	28	93
	SR <sup>1</sup>		A5.17: F7P6-EC1							51	66	34	50
SubCOR EM13K-S MOD	AW		A5.17: F7A6-EC1							70	81	28	92 56
	SR <sup>1</sup>		A5.17: F7P8-EC1							62	77	30	94 65
Mechanical properties of two-run pipe joint (high dilution)													
SDX S2Mo-EA2	TR			480	560	23	60	35					
SDX S3Mo-EA4	TR			520	600	22	60	35					
SDX S3TiB	TR			560	700	20	120	80	60				
SDX S3MoTiB	TR			630	700	25	200	180	120				
SubCOR SL 735-1W-5W*	TR			500	580	24	150	100					

Mechanical properties of pipe welds in the two run technique depend on the chemical composition of the base material. AW: As welded, all weld metal. TR: Two Run

\* Depends on the type of solid wire used. SR<sup>1</sup>: PWHT 1150°F (620°C)/1 h.



# SWX 135 (continued)

EN ISO 14174: S A AB 1 67 AC H5

Flux/wire combinations for the submerged arc welding of non-and low-alloyed steels

## Flux SWX 135 - Chemical composition all weld metal, typical values

With wire	%C	%Si	%Mn	%Mo	%Ti	%B
SDX S2	0.05	0.3	1.3			
SDX S2Si-EM12K	0.06	0.5	1.4			
SDX S2Mo-EA2	0.06	0.3	1.4	0.5		
SDX S3Mo-EA4	0.06	0.3	1.5	0.5		
SubCOR EM12K-S	0.06	0.3	1.2			
SubCOR EM13K-S	0.05	0.5	1.2			
SubCOR EM13K-S MOD	0.06	0.3	1.3			
<b>Weld metal analyses of two-run pipe joint (high dilution)</b>						
SDX S3TiB	0.06	0.5	1.6		0.024	0.0024
SDX S3MoTiB	0.06	0.5	1.4	0.3	0.022	0.0024
SubCOR SL 735-1W-5W	Depends on the type of solid wire used.					

## Materials to be welded

Steel group	Typical examples of steel types	Impact requirement ≥47 J (≥20 ft-lbf)	Flux SWX 135 with wire:
<b>Normal strength steel</b>			
Rel ≤ 355 MPa	X42, X46, L235, L265, L295, L320	-40°C	SDX S2, SDX S2Si-EM12K
Rel ≥ 355 MPa	X52, L355, L360, L385L, 390, L415	-40°C	SDX S2, SDX S2Si-EM12K
TS > 58 ksi	A36, A709 Gr. 36,	-40°F	SubCOR EM12K-S
		-80°F	SubCOR EM13K-S, SubCOR EM13K-S MOD
TS > 65 ksi	A572 Gr. 50, A709 Gr. 50, A709 Gr. 50S, A992	-40°F	SubCOR EM12K-S
		-80°F	SubCOR EM13K-S, SubCOR EM13K-S MOD
<b>High strength steel</b>			
Rel ≥ 420 MPa	X56, X60, L445, L450	-20°C	SDX S2Mo-EA2
		-40°C	SDX S3TiB
		-50°C	SDX S3MoTiB
Rel ≥ 460 MPa	X65, X70, X80	-20°C	S2Mo-EA2
		-40°C	SDX S3TiB, SubCOR SL 735-1W-5W
		-50°C	SDX S3MoTiB
TS > 70ksi	A588, A516 Gr. 70	-40°F	SubCOR EM12K-S
		-80°F	SubCOR EM13K-S, SubCOR EM13K-S MOD

## Approvals

With wire	CE
SDX S2	✓
SDX S2Si-EM12K	✓
SDX S2Mo-EA2	✓
For the complete approval list please see Product Data Sheet or contact the ITW Welding sales office	

## Packaging data

Flux unit net weight	Kg	Lbs
Aluminium/PE Bag EAE*	25	55
DoubleBag	1000	2200
*EAE Excess Air Evacuation		

# SWX 140

EN ISO 14174: S A FB 1 57 AC H5

Flux/wire combinations for the submerged arc welding of non-and low-alloyed steels

## Description

SWX 140 is a fluoride-basic flux that combines high welding productivity with good low-temperature impact toughness at -50°C using standard SDX solid wires or at -60°C using specially developed SubCOR wires. It is a multi-purpose flux, suited for multi-layer welds in medium thick and thick materials, but also for efficient two-run welding with multiple wire heads at high travel speed. It performs equally well in single-wire, twin- and tandem welding and features good slag release, even in welds with a high interpass temperature. These characteristics make SWX 140 a versatile "production" flux for a wide range of applications in offshore fabrication, more demanding shipbuilding and pressure vessel fabrication. It is also an excellent flux for double jointing, both onshore and offshore onboard of pipe laying barges.

An extra safety margin on low-temperature impact values can be obtained from SubCOR cored wires. SubCOR SL 840 B HC is intended for single-wire welding, whereas the micro-alloyed SubCOR SL 735 B-1W-5W series represents a range of wires developed for multi-wire welding with up to 5 wires. SWX 140 is also successfully used in hardfacing for the repair of worn rails and rollers, providing consistent weld hardness. A special application is the joining of CRA-clad pipes for aggressive fluids, where the weld in the host pipe needs to retain its toughness after a heat treatment at 1000 and 590°C.

The flux is delivered in Hobart humidity proof packaging - EAE bag or DoubleBag - eliminating the need to re-dry the flux.

- Offshore construction
- Demanding shipbuilding
- Double jointing
- Pressure vessels

## Flux characteristics

Flux type	Fluoride-Basic
Basicity index	2.0 (Boniszewski)
Alloy transfer	Slightly Mn alloying
Density	~ 1.2 kg/litre
Grain size	0.2-1.6 mm / 12-65 mesh
HDM	< 5 ml/100 g weld metal
Current	DC+/AC
Re-drying unopened bag	Not required
Re-drying opened bag	See storage and handling recommendations


## Flux main components

AL <sub>2</sub> O <sub>3</sub> + MnO	CaO + MgO	SiO <sub>2</sub> + TiO <sub>2</sub>	CaF <sub>2</sub>
~ 30%	~ 25%	~ 20%	~ 20%

## Metallurgical behaviour

The diagrams show the typical weld metal analysis in relation to wire analysis for silicon and manganese.

Single wire, ø 4.0 mm (5/32"), DC+, 30 V, 60 cm/min (24"/min)

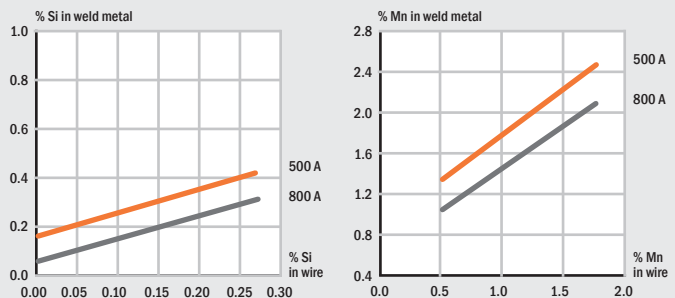

## Flux SWX 140 - Classifications

## Mechanical properties

With wire		EN ISO	AWS	Re/Rp0.2 MPa	Rm MPa	A %	CVN J			YS ksi	TS ksi	E %	CVN ft-lbf
-20°C -40°C -50°C -60°C										0°F -20°F -40°F -60°F -80°F -100°F			
SDX EM13K	AW		A5.17: F7A4-EM13K							77	87	29	40
SDX S2	AW	14171-A: S 38 5 FB S2		420	500	26	120	95	70 45				
SDX S2Si-EM12K	AW	14171-A: S 38 5 FB S2Si	A5.17: F7A6-EM12K	430	510	26	130	100	75 45	66	78	27	76 68
SDX S2Mo-EA2	AW	14171-A: S 46 4 FB S2Mo	A5.23: F7A6-EA2-A4	500	590	24	90	60		73	83	25	69
	SR <sup>1</sup>		A5.23: F7P6-EA2-A4	490	575	24	90	60	45	68	91	29	44 30
SubCOR EM12K-S	AW		A5.17: F7A6-EC1							60	70	32	110
SubCOR EM13K-S	AW		A5.17: F7A8-EC1							58	71	29	105
	SR <sup>1</sup>		A5.17: F6P8-EC1							51	66	34	143 142
SubCOR EM13K-S MOD	AW		A5.17: F7A10-EC1							72	82	29	161 105
	SR <sup>1</sup>		A5.17: F7P8-EC1							67	80	29	221 134
SubCOR 92-S	AW		A5.23: F8A10-ECM1-M1							79	93	26	85 52
	SR <sup>2</sup>		A5.23: F8P8-ECM1-M1							71	84	27	103 77
SubCOR SL 735-1W-5W	AW	14171-A: S 46 4 FB T3		500	580	29	150	120					
SubCOR SL 840 HC	AW	14171-A: S 46 6 FB T3Ni1		520	570	30	140	120	100				
	SR <sup>1</sup>			520	570	30		140	120				
SubCOR SL 741	AW	26304: S 55 6 FB T3 Ni1Mo		560	650	18	100	80	70 60				
	SR <sup>1</sup>			510	560	20	100	80	70 60				
SubCOR 100F3-S	AW		A5.23: F10A10-ECF3-F3							101	109	24	57 44
	SR <sup>1</sup>		A5.23: F10P8-ECF3-F3							98	108	25	59 35

AW: As welded, all weld metal. SR: stress relieved, all weld metal. SR<sup>1</sup>: 1150°F (620°C) / 1 h. SR<sup>2</sup>: 1125°F (605°C) / 1 h.

# SWX 140 (continued)

EN ISO 14174: S A FB 1 57 AC H5

Flux/wire combinations for the submerged arc welding of non-and low-alloyed steels

## Flux SWX 140 - Chemical composition all weld metal, typical values

With wire	%C	%Si	%Mn	%Ni	%Mo
SDX-EM13K	0.05	0.2	1.2		
SDX S2	0.07	0.2	1.4		
SDX S2Si-EM12K	0.07	0.3	1.4		
SDX S2Mo-EA2	0.07	0.2	1.4		0.5
SubCOR EM12K-S	0.05	0.2	1.2		
SubCOR EM13K-S	0.05	0.2	1.2		
SubCOR EM13K-S MOD	0.08	0.3	1.2		
SubCOR 92-S	0.08	0.2	1.3	1.6	0.2
SubCOR SL 735-1W-5W	0.05	0.3	1.4		
SubCOR SL 840 HC	0.10	0.3	1.4	0.9	
SubCOR SL 741	0.06	0.3	1.2	0.9	0.5
SubCOR 100F3-S	0.09	0.3	1.5	0.8	0.5

## Materials to be welded

Steel group	Typical examples of steel types	Impact requirement ≥47 J (≥20 ft-lbf)	Flux SWX 140 with wire:
<b>Normal strength steel</b>			
Rel ≤ 355 MPa	S235JR, A106 Gr. B, A333 Gr. 6, P235GH, S275JO,	-40°C	SDX S2Mo-EA2
	S275JR, P295GH	-50°C	SDX S2, SDX S2Si-EM12K
Rel ≥ 355 MPa	S355J2, S355N, P355NL1, X52, L360, S355MCD,	-40°C	SDX S2Mo-EA2
	S355ML, P355GH	-50°C	SDX S2, SDX S2Si-EM12K
TS > 58 ksi	A36, A709 Gr. 36,	-60°F	SubCOR EM12K-S
		-100°F	SubCOR EM13K-S MOD
TS > 65ksi	A572 Gr. 50, A709 Gr. 50, A709 Gr. 50S, A992	-60°F	SubCOR EM12K-S
		-100°F	SubCOR EM13K-S MOD
<b>High strength steel</b>			
Rel ≥ 420 MPa	S420N, S460ML, P420ML2, S420MCD, S420G2+M,	-40°C	SDX S2Mo-EA2, SDX S3Si-EH12
	X60, L450		
Rel ≥ 460 MPa	S460M, S460ML, S460ML2, S460MCD, S460G2+M	-40°C	SDX S2 Mo-EA2, SDX S3Si-EH12, SubCOR SL 735-1W-5W
	X65, L450	-60°C	SubCOR SL 840 HC
Rel ≥ 500 MPa	S500Q, S500QL, S500QL1, P500QL1, P500QL2,	-50°C	SubCOR 741
	S500G2+M, S55Q, S550QL, S500QL1, X70, X75, X80	-60°C	SubCOR SL 840 HC
TS > 70ksi	A588, A516 Gr. 70	-60°F	SubCOR EM12K-S
		-100°F	SubCOR EM13K-S MOD
TS > 75ksi	A572 Gr. 60, A913 Gr. 60, A871 Gr. 60	-100°F	SubCOR 92-S
TS > 80ksi	A572 Gr. 65, A871 Gr. 65, A537 Class 2	-100°F	SubCOR 92S
TS > 85ksi	A710 Gr. A Class 3 ≤ 2"	-100°F	SubCOR 100F3-S
TS > 90ksi	A710 Gr. A Class 1 ≤ 3/4"	-100°F	SubCOR 100F3-S
TS > 100ksi	A514 >2 1/2"	-100°F	SubCOR 100F3-S
<b>Creep resistant steel</b>			
0.5% Mo	P295GH, P355GH, 16Mo3, 17Mo3, 14Mo6	-40°C	SDX S2Mo-EA1

## Approvals

With wire	CE
SDX S2	✓
SDX S2Si-EM12K	✓
SDX S2Mo-EA2	✓
For the complete approval list please see Product Data Sheet or contact the ITW Welding sales office	

## Packaging data

Flux unit net weight	Kg	Lbs
Aluminium/PE Bag EAE*	25	55
DoubleBag	1000	2200
*EAE Excess Air Evacuation		

# SWX 150

EN ISO 14174: S A FB 1 55 AC H5

Flux/wire combinations for the submerged arc welding of non-and low-alloyed steels

## Description

Hobart SWX 150 is a high basicity, fluoride-basic agglomerated flux for low-temperature, high strength and creep resistant applications, including CTOD requirements. Its neutral character promotes a homogeneous weld chemistry and consistent mechanical properties throughout thick multi-layer welds. It produces low oxygen weld metal (~300ppm), resulting in excellent impact toughness down to -60°C and below. SWX 150 has a very good slag detachability, also in narrow gaps, along with smooth bead finish and tie-in. SWX 150 can be used in single- and multiple-wire operation and performs equally well on AC and DC+.

It is used for normal construction steel, high strength steel, low-temperature steel and creep resistant steel in demanding sectors such as offshore fabrication, pressure vessels and nuclear components. Use of the flux in combination with Hobart cored wires offers further opportunities to improve weld metal quality and productivity, making use of unique cored wire properties.

Typical CTOD test results with SDX S3Si-EH12K solid wire, tested at -20°C: 1.01, 1.01, 1.09 mm.

The flux is delivered in Hobart humidity proof EAE bag, eliminating the need to re-dry the flux.

- Offshore construction
- Offshore wind towers
- Civil construction
- Pressure vessels
- Nuclear applications
- Narrow gap welding
- Double-jointing
- High strength applications

## Flux characteristics

Flux type	Fluoride-basic
Basicity index	3.3 (Boniszewski)
Alloy transfer	None
Density	~ 1.1 kg/litre
Grain size	0.2-1.6 mm / 12-65 mesh
HDM	< 5 ml/100 g weld metal
Current	DC+/AC
Re-drying unopened bag	Not required
Re-drying opened bag	See storage and handling recommendations


## Flux main components

Al <sub>2</sub> O <sub>3</sub> + MnO	CaO + MgO	SiO <sub>2</sub> + TiO <sub>2</sub>	CaF <sub>2</sub>
~ 20%	~ 35%	~ 15%	~ 25%

## Metallurgical behaviour

The diagrams show the typical weld metal analysis in relation to wire analysis for silicon and manganese.

Single wire, ø 4.0 mm (5/32"), DC+, 30 V, 60 cm/min (24"/min)

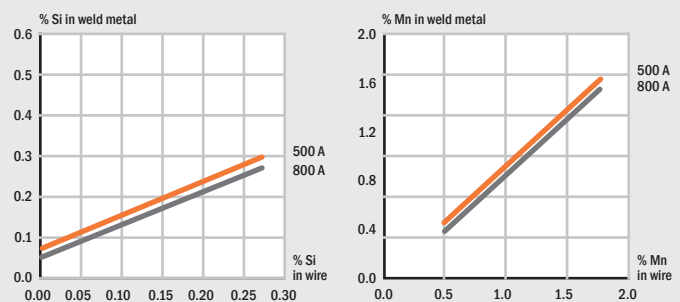

Flux SWX 150 - Classifications				Mechanical properties											
With wire		EN ISO	AWS	Re/ Rp0.2 MPa	Rm MPa	A %	CVN J					YS ksi	TS ksi	E %	CVN ft-lbf
								0°C	-20°C	-30°C	-40°C	-50°C	-60°C	-70°C	0°F -100°F
SDX EM13K	AW		A5.17: F7A4-EM13K									68	74	27	42 28
SDX S2Si-EM12K	AW	14171-A: S 38 5 FB S2Si	A5.17: F7A6-EM12K	420	500	22	130	85	65	35		68	77	31	90 27
SDX S3Si-EH12K	AW	14171-A: S 46 6 FB S3Si	A5.17: F7A8-EH12K	490	550	29	140	115	80	60		74	83	31	142 122
	SR <sup>1</sup>		A5.17: F7P8-EH12K	410	500	29	140	115	80	60		65	80	31	219 129
SDX S4-EH14	AW	14171-A: S 50 4 FB S4		540	630	22	65	55	40						
	SR <sup>1</sup>			450	550	22	60	55	40						
SDX S2Mo-EA2	AW	14171-A: S 46 4 FB S2Mo	A5.23: F7A6-EA2-A2	485	570	23	75	55	40			76	84	27	106 44
	SR <sup>1</sup>		A5.23: F7P6-EA2-A2	460	510	24	70	50	35			72	82	30	109 60
SubCOR EM12K-S	AW		A5.17: F7A4-EC1									60	71	32	97
SubCOR EM13K-S	AW		A5.17: F7A8-EC1									64	73	30	160
	SR <sup>1</sup>		A5.17: F6P8-EC1									52	67	35	154
SubCOR EM13K-S MOD	AW		A5.17: F7A8-EC1									70	79	29	103
	SR <sup>1</sup>		A5.17: F7P8-EC1									65	78	32	36
SubCOR SL 731	AW	14171: S 46 4 FB T3	A5.17: F8A6-EC1	490	600	29	140	110	80			112	122	22	55 36
	SR <sup>1</sup>			460	570	28	110	90	70						
SDX S3Ni1Mo0.2-ENi5	AW	14171-A: S 46 6 FB S2Ni1Mo0.2	A5.23: F8A8-ENi5-Ni5	510	590	29		125	75			82	90	27	146
	SR <sup>1</sup>		A5.23: F8P6-ENi5-Ni5	500	590	28			70			77	89	28	134 100
SDX S3Ni1Mo-EF3	AW	14171-A: S 62 6 FB S3Ni1Mo	A5.23: F10A8-EF3-F3	640	730	22	110	75	60	50		98	107	24	99 72
SDX S3Ni2.5CrMo	AW	26304: S 69 6 FB S3Ni2.5CrMo		710	800	18	95	75	65	55					
SubCOR 92-S	AW		A5.23: F8A10-ECM1-M1									78	88	26	91 78
	SR <sup>1</sup>		A5.23: F8P8-ECM1-M1									76	88	27	123 106

Table continues on next page >>



# SWX 150 (continued)

EN ISO 14174: S A FB 1 55 AC H5

Flux/wire combinations for the submerged arc welding of non-and low-alloyed steels

Flux SWX 150 - Classifications				Mechanical properties																					
With wire		EN ISO	AWS	Re/Rp0.2 MPa	Rm MPa	A %	CVN J						YS ksi	TS ksi	E %	CVN ft-lbf									
								0°C	-20°C	-30°C	-40°C	-50°C	-60°C	-70°C	0°F					-20°F	-40°F	-60°F	-80°F	-100°F	
SubCOR F2-S	AW		A5.23: F10A10-ECF2-F2											95	104	23								86	58
	SR <sup>1</sup>		A5.23: F10P10-ECF2-F2											91	101	25								39	28
SubCOR 100F3-S	AW		A5.23: F10A10-ECF3-F3											101	109	24								57	44
	SR <sup>1</sup>		A5.23: F10P10-ECF3-F3											98	108	25								59	35
SubCOR 120-S	AW		A5.23: F11A10-ECM4-M4											111	118	23								77	52
SubCOR SL 741	AW	26304: S 55 6 FB T3 Ni1Mo		550	700	18			80	60															
SubCOR SL 742	AW	26304: S 69 6 FB T3 Ni2.5CrMo	A5.23: F11A8-ECF5-F5	720	820	20		145	125	100				112	122	22							34	33	
	SR <sup>3</sup>	26304: S 69 6 FB T3 Ni2.5CrMo		700	790	20		135	115	70															
SubCor SL 745	AW	16304: S 89 4 FB T3Ni2.5Cr1Mo		920	1060	15			47																
SDX S2Ni1-ENi1	AW	14171-A: S 42 4 FB S2Ni1	A5.23: F7A8-ENi1-Ni1	440	530	25		130	65	45				70	80	29							135	108	
	SR <sup>1</sup>		A5.23: F7P8-ENi1-Ni1	430	530	25		130	90	60	45			65	77	30							177	135	
SDX S2Ni2-ENi2	AW	14171-A: S 46 7 FB S2Ni2	A5.23: F8A10-ENi2-Ni2	480	570	27		145	115	95	75	60		74	85	27							143	127	
	SR <sup>1</sup>		A5.23: F8P10-ENi2-Ni2	480	580	27		145	115	90	60	40		70	83	28							149	138	
SubCOR Ni1-S	AW		A5.23: F7A8-ECNi1-Ni1											61	73	26							104		
	SR <sup>1</sup>		A5.23: F7P10-ECNi1-Ni1											58	71	33							127	191	
SubCOR W-S	AW		A5.23: F7A6-ECW-W											71	80	28						129	66		
SDX CrMo1-EB2R	SR <sup>4</sup>	24598: S S CrMo1 FB	A5.23: F8P2-EB2R-B2	490	620	22		100	80					80	91	25			129	88					
SDX CrMo2-EB3R	SR <sup>4</sup>	24598: S S CrMo2 FB	A5.23: F8P0-EB3R-B3	530	630	22		110	80					82	97	24	92	20							
SubCOR B2-S	SR <sup>4</sup>		A5.23: F9P2-ECB2-B2											93	96	23			92	18					
SubCOR B3-S	SR <sup>4</sup>		A5.23: F9P2-ECB3-B3											103	117	18			25						
SubCOR SL P1	SR <sup>4</sup>	24598: S T Mo FB		480	560	22	220	200	180																
SubCOR SL P1 MOD	SR <sup>4</sup>	24598: S T MoVFB		420	530	22	70	40																	
SubCOR SL P11	SR <sup>4</sup>	24598: S T CrMo1 FB		510	600	26		200	150																
SubCOR SL P12 MOD	SR <sup>4</sup>	24598: ~S T CrMoV1 FB		540	630	17	+20°C:60																		
SubCOR SL P36	SR <sup>1</sup>	24598: S T Z FB		550	640	18	80	60	50																
SubCOR SL P22	SR <sup>4</sup>	24598: S T CrMo2 FB		560	640	20	180																		
SubCOR SL P24	SR <sup>4</sup>	24598: S T Z FB		650	720	18	120	60																	
SubCOR SL P5	SR <sup>5</sup>	24598: S T CrMo5 FB		470	590	25		200	150																

AW: as welded, all weld metal. SR: stress relieved, all weld metal. SR<sup>1</sup>: 1150°F (620°C) / 1 h. SR<sup>2</sup>: 1125°F (605°C) / 1 h. SR<sup>3</sup>: 1050°F (565°C) / 1 h. SR<sup>4</sup>: 1275°F (690°C) / 1 h. SR<sup>5</sup>: 1375°F (745°C) / 1 h.

## Flux SWX 150 - Chemical composition all weld metal, typical values

With wire	%C	%Si	%Mn	%Cr	%Ni	%Mo	%V
SDX EM13K	0.07	0.2	1.0				
SDX S2Si-EM12K	0.07	0.3	0.9				
SDX S3Si-EH12K	0.09	0.3	1.5				
SDX S4-EH14	0.01	0.15	1.9				
SDX S2Mo-EA2	0.07	0.2	0.9			0.5	
SDX S2Ni1-ENi1	0.07	0.2	0.9		0.9		
SDX S2Ni2-ENi2	0.08	0.2	1.0		2.1		
SDX S3Ni1Mo0.2-ENi5	0.09	0.25	1.4		0.9	0.2	
SDX S3Ni1Mo-EF3	0.09	0.2	1.5		0.9	0.5	
SDX S3Ni2.5CrMo	0.07	0.2	1.4	0.5	2.5	0.5	
SDX CrMo1-EB2R	0.07	0.3	0.9	1.1		0.5	
SDX CrMo2-EB3R	0.07	0.3	0.6	2.2		1.0	
SubCOR EM12K-S	0.05	0.2	0.9				
SubCOR EM13K-S	0.07	0.2	1.0				
SubCOR EM13K-S MOD	0.09	0.3	0.9				
SubCOR 92-S	0.05	0.2	1.0		1.6	0.2	
SubCOR F2-S	0.07	0.35	1.4		0.7	0.4	

Table continues on next page >>

# SWX 150 (continued)

EN ISO 14174: S A FB 1 55 AC H5

Flux/wire combinations for the submerged arc welding of non-and low-alloyed steels

## Flux SWX 150 - Chemical composition all weld metal, typical values

With wire	%C	%Si	%Mn	%Cr	%Ni	%Mo	%V	%Cu
SubCOR 100F3-S	0.09	0.3	1.5		0.8	0.5		
SubCOR 120-S	0.06	0.3	1.5	0.3	2.4	0.4		
SubCOR Ni1-S	0.05	0.2	1.0		1.6	0.2		
SubCOR W-S	0.03	0.4	0.6	0.5	0.5			0.4
SubCOR B2-S	0.07	0.4	0.4	1.2		0.5		
SubCOR B3-S	0.1	0.4	0.4	2.3		1.0		
SubCOR SL 731	0.08	0.6	1.7					
SubCOR SL 741	0.06	0.3	1.2		0.9	0.5		
SubCOR SL 742	0.07	0.35	1.6	0.4	2.1	0.4		
SubCOR SL 745	0.08	0.4	1.6	1.0	2.2	0.5		
SubCOR SL P1	0.06	0.2	1.2			0.5		
SubCOR SL P1 MOD	0.05	0.3	1.0	0.4	0.2	0.55	0.3	
SubCOR SL P11	0.07	0.3	1.1	1.2		0.5		
SubCOR SL P12 MOD	0.10	0.5	0.9	1.1	0.3	1.2	0.25	
SubCOR SL P36	0.05	0.3	1.3			0.5		
SubCOR SL P22	0.09	0.3	1.1	2.3		1.1		
SubCOR SL P24	0.1	0.3	1.2	2.5		1.0	0.2	
SubCOR SL P5	0.05	0.4	1.1	5		0.6		

## Materials to be welded

Steel group	Typical examples of steel types	Impact requirement ≥47 J (≥20 ft-lbf)	Flux SWX 150 with wire:
<b>Normal strength steel</b>			
Rel ≤ 355 MPa	S235JR, A106 Gr. B, A333 Gr. 6, P235GH, S275JO, S275JR	-50°C	SDX S2Si-EM12K
		-60°C	SDX S3Si-EH12K
Rel ≥ 355 MPa	S355J2, S355N, P355NL1, X52, L360, S355MCD, S355ML	-50°C	SDX S2Si-EM12K
		-60°C	SDX S3Si-EH12K
TS > 58 ksi	A36, A709 Gr. 36,	-40°F	SubCOR EM12K-S
		-80°F	SubCOR EM13K-S
		-100°F	SubCOR EM13K-S MOD
TS > 65ksi	A572 Gr. 50, A709 Gr. 50, A709 Gr. 50S, A992	-40°F	SubCOR EM12K-S
		-80°F	SubCOR EM13K-S
		-100°F	SubCOR EM13K-S MOD
<b>High strength steel</b>			
Rel ≥ 420 MPa	S420N, S460ML, P420ML2, S420MCD, S420G2+M, X60, L450	-40°C	SDX S2Mo-EA2, SDX S2Ni1-ENi1
		-60°C	SDX S3Si-EH12K
Rel ≥ 460 MPa	S460M, S460ML, S460ML2, S460MCD, S460G2+M, X65, L450	-40°C	SDX S2Mo-EA2, SubCOR SL 731
		-60°C	SDX S3Si-EH12K, SDX S2Ni1Mo0.2-ENi5
		-70°C	SDX S2Ni2-ENi2
Rel ≥ 500 MPa	S500QL, S500QL1, P500QL1, P500QL2, X70, S500G2+M,	-40°C	SDX S4-EH12
	B1 4NVE 500, X70, X80	-60°C	SubCOR SL 741
Rel ≥ 620 MPa	S550QL, NVE550, S600Q1, S620Q, S620QL, NVE620	-40°C	SDX S3Ni1.5CrMo
		-60°C	SDX S3Ni1Mo-EF3
Rel ≥ 690 MPa	S690Q, S690QL, S690QL1, NVE690, X100	-60°C	SubCOR SL 742, SDX S3Ni2.5CrMo
Rel ≥ 890 MPa	S890QL1, S960QL1, A714, A709, A515, A517	-40°C	SubCOR SL 745

Table continues on next page >>

# SWX 150 (continued)

EN ISO 14174: S A FB 1 55 AC H5

Flux/wire combinations for the submerged arc welding of non-and low-alloyed steels

## Materials to be welded

Steel group	Typical examples of steel types	Impact requirement ≥47 J (≥20 ft-lbf)	Flux SWX 150 with wire:
<b>High strength steel</b>			
TS > 70ksi	A588, A516 Gr.70	-60°F	SubCOR EM12K-S
		-80°F	SubCOR EM13K-S MOD
	A709 Gr. HPS50W, A537 Class 1	-100°F	SubCOR N1-S
TS > 75ksi	A572 Gr. 60, A913 Gr. 60, A871 Gr. 60	-100°F	SubCOR 92-S
TS > 80ksi	A572 Gr. 65, A871 Gr. 65, A537 Class 2	-100°F	SubCOR 92S, SubCOR F2-S
TS > 85ksi	A710 Gr. A Class 3 ≤ 2"	-100°F	SubCOR 100F3-S
TS > 90ksi	A710 Gr. A Class 1 ≤ 3/4"	-100°F	SubCOR 100F3-S
TS > 100ksi	A514 >2 1/2"	-100°F	SubCOR 100F3-S
TS > 110ksi	A517, A514 <2 1/2"	-100°F	SubCOR 120-S
<b>Weathering</b>			
TS > 70ksi	A588	-60°F	SubCOR W-S
<b>Chromium Molybdenum</b>			
TS > 75ksi, 1% Cr, 0.5%Mo	A387 Gr. 11	-20°F	SubCOR B2-S
TS > 75ksi, 2% Cr, 1%Mo	A387 Gr. 22	-20°F	SubCOR B3-S
<b>Creep resistant steel</b>			
<b>EN</b>	<b>ASTM</b>		
P235GH-P355GH, 16Mo3, P235T1/T2-P460NL2, L210-L445MB, S255-S460QL1	A355 P1, A285 Gr. C, A515 Gr. 70, A516 Gr. 70		
14MoV6-3 (1.7715)	A405		
13CrMo4-5, G17CrMo5-5, G22CrMo5-4	A355 P11, A387 Gr. 11		
21CrMoV5-11, GS17CrMoV5-17	A 387 Gr. 11		
15NiCuMoNb5/WB 36, 20MnMoNi4-5, 11NiMoV53, 17MnMoV6-4	A355 P36		
10CrMo9-10, 12CrMo9-10	A355 P22, A387 Gr. 22		
10CrMo9-10, 12CrMo9-10, 7CrMoVTiB10-10 (P24)	A355 P22		
X12CrMo5	A355 P5, A387 Gr. 5		
X12CrMo9-1, X7CrMo9-1	A355 P9, A387 Gr. 9		
X12CrMo9-1, X10CrMoVNb9-1	A355 P91, A387 Gr. 91		
X12CrMo9-1, X10CrMoVNb9-1, X10CrMoVNb9-2, X12CrWVNb12-2-2, X20CrMoWV12-1, X20CrMoV12-1	A355 P92		

## Approvals

With wire	CE	ABS	BV	CWB	DNV	GL	LR	DB	TÜV
SWX 150								✓	
SDX S2	✓	3YM	3YM		II YM	3YM	BF 3YM NR		✓
SDX S2Si-EM12K	✓			F49A6-EM12K*			BF 5Y46M H5		
SDX S2Mo-EA2	✓			F8A4-EA2-A4*					✓
SDX S3Si-EH12K	✓	5YQ460	A5Y46M H5	F49A6-EH12K*	V Y46(H5)	6Y46MH5	BF 5Y46M H5		✓
SubCOR SL 731	✓	3YM	3YM		III YM	3YM	5Y46	✓	✓
SubCOR SL 742	✓	5YQ690M H5	5Y69M H5		IV Y69 MS H5	6Y69 H5	BF 5Y69M H5		✓

For the complete approval list please see Product Data Sheet or contact the ITW Welding sales office. \* Pending

## Packaging data

Flux unit net weight	Kg	Lbs
Aluminium/PE Bag EAE*	22.7	50

\*EAE Excess Air Evacuation

# SWX 220

EN ISO 14174: S A AF 2 DC

Flux/wire combinations for the submerged arc welding of stainless steel

## Description

Hobart SWX 220 an agglomerated neutral basic flux for the single- or multi-run welding of stainless steel in all plate thicknesses. It can be combined with a wide range of SDX subarc wires for the welding of all standard austenitic stainless steel grades, for duplex and super duplex stainless steel, for dissimilar joints and for higher alloyed stainless steel grades. Multi-run welding is favoured by excellent slag detachability and smooth side-wall blending, while the overall weld appearance is very nice. It yields welds with good mechanical properties, including excellent low-temperature impact toughness.

A wide range of applications are found in transport and processing installations in the offshore oil and gas and petrochemical industries, in tanks and appliances of chemical tankers, in paper and pulp processing plants and in nuclear power stations. The flux is delivered in Hobart humidity proof EAE bag, eliminating the need to re-dry the flux.

- Offshore fabrication
- Petrochemical industry
- Chemical tankers
- Duplex grades
- Nuclear applications
- Paper and pulp plants
- Equipment for the food industry

## Flux characteristics

Flux type	Aluminate-Fluoride
Basicity index	1.7 (Boniszewski)
Alloy transfer	none
Density	~ 1.2 kg/litre
Grain size	0.2-1.6 mm /12-65 mesh
Current	DC+
Re-drying unopened bag	Not required
Re-drying opened bag	See storage and handling recommendations

## Flux main components

AL <sub>2</sub> O <sub>3</sub> + MnO	CaO + MgO	SiO <sub>2</sub> + TiO <sub>2</sub>	CaF <sub>2</sub>
~30%	~25%	~20%	~20%

## Flux SWX 220 - Classifications

With wire	EN ISO	AWS	Re/Rp0.2 MPa	Rm MPa	A %	CVN J				YS ksi	TS ksi	E %	CVN ft-lbf				
							-20°C	-40°C	-60°C	-196°C			-4°F	-40°F	76°F	-321°F	
SDX 308L	14343-A: S 19 9 L	A5.9: ER308L	390	550	36	100		60	50		57	80	36	74	44	37	
SDX 347	14343-A: S 19 9 Nb	A5.9: ER347	440	620	36	100		80	20		64	90	36	74	59	15	
SDX 316L	14343-A: S 19 12 3 L	A5.9: ER316L	390	560	36	100		90	40		57	81	36	74	66	30	
SDX 317L	14343-A: S 19 13 4 L	A5.9: ER317L	430	600	30	90		50	40		62	87	30	66	37	30	
SDX 309L	14343-A: S 23 12 L	A5.9: ER309L	420	580	33	90		65	35		61	84	90	66	48	26	
SDX 309LMo	14343-A: S 23 12 2 L		420	620	33	90					61	90	90	66			
SDX 2209	14343-A: S 22 9 3 N L	A5.9: ER2209	620	780	26	130	100	80	55		90	113	26	96	74	59	41
SDX 2594	14343-A: S 25 9 4 N L	A5.9: ER2594	630	830	28	80	60				91	120	28	59	44		

## Flux SWX 220 - Chemical composition all weld metal, typical values

With wire	%C	%Si	%Mn	%Cr	%Ni	%Mo	%Nb	%N	FN	
SDX 308L	0.02	0.6	1.4	19.5	10.0				7	
SDX 347	0.04	0.6	1.0	19.1	9.3		0.5		8	
SDX 316L	0.02	0.6	1.4	18.3	11.3	2.8			8	
SDX 317L	0.02	0.6	1.4	19.5	14.3	3.5			6	
SDX 309L	0.02	0.6	1.4	23.0	14.2	2.8			10	
SDX 309LMo	0.02	0.6	1.4	21.5	14.2	2.8			12	
SDX 2209	0.02	0.7	1.2	22.5	9.0	3.2		0.13	48	
SDX 2594	0.01	0.45	0.6	22.5	9.2	4.0		0.26	42	



# SWX 220 (continued)

EN ISO 14174: S A AF 2 DC

Flux/wire combinations for the submerged arc welding of stainless steel

## Materials to be welded

AISI	EN 10088-1/2	Material nr.	UNS	Flux SWX 220 with wire:
304	X4 CrNi 18 10	1.4301	S30409	SDX 308L
304L	X2 CrNi 19 11	1.4306	S30403	SDX 308L
304LN	X2 CrNiN 18 10	1.4311	S30453	SDX 308L
316	X4 CrNiMo 17 12 2	1.4401	S31600	SDX 316L
316	X4 CrNiMo 17 13 3	1.4436		SDX 316L
316L	X2 CrNiMo 17 12 2	1.4404	S31603	SDX 316L
316L	X2 CrNiMo 18 14 3	1.4435	S31603	SDX 316L
317L	X2 CrNiMoN 17 13 5	1.4439	S31726	SDX 317L
321	X6 CrNiTi 18 10	1.4541	S32100	SDX 347, SDX 308L for service temperatures below 400°C
347	X6 CrNiNb 18 10	1.4550	S34700	SDX 347, SDX 308L for service temperatures below 400°C
	X2 CrNiMoN 22 5 3	1.4462		SDX 2209
		1.4507		SDX 2594
Dissimilar welds, moderate dilution				SDX 309L
Dissimilar welds, high dilution, hot crack resistant				SDX 309LMO

## Packaging data

Flux unit net weight	Kg	Lbs
Aluminium/PE Bag EAE*	25	55
*EAE Excess Air Evacuation		

# SWX 282

EN ISO 14174: S A AF 2 DC

Flux/wire combinations for the submerged arc welding of Ni-base alloys

## Description

Hobart SWX 282 is an agglomerated neutral basic flux for the single- or multi-run welding of Ni-base alloys, such as Alloy 82, Alloy 600 and Alloy 625. This Aluminate-Fluoride flux features excellent slag detachability and very good CVN impact properties at temperatures down to -196°C.

The flux is delivered in Hobart humidity proof EAE bags, eliminating the need to re-dry the flux.

- Offshore oil and gas processing
- Pulp and paper industry

## Flux characteristics

Flux type	Aluminate-Fluoride
Basicity index	1.7 (Boniszewski)
Alloy transfer	none
Density	~ 1.2 kg/litre
Grain size	0.2-1.6 mm /12-65 mesh
Current	DC+
Re-drying unopened bag	Not required
Re-drying opened bag	See storage and handling recommendations

## Flux main components

AL <sub>2</sub> O <sub>3</sub> + MnO	CaO + MgO	SiO <sub>2</sub> + TiO <sub>2</sub>	CaF <sub>2</sub>
~30%	~25%	~20%	~20%

## Flux SWX 282- Classifications

With wire	EN ISO	AWS	Re/Rp0.2 MPa	Rm MPa	A %	CVN J	YS ksi	TS ksi	E %	CVN ft-lbf
-196°C							-321°F			
SDX NiCr-3	18274: S Ni6082	A5.14: ERNiCr-3	420	570	34	70	61	83	34	52
SDX NiCrMo-3	18274: S Ni6625	A5.14: ERNiCrMo-3	470	700	40	60	68	102	40	44

## Flux SWX 282 - Chemical composition all weld metal, typical values

With wire	%C	%Si	%Mn	%Cr	%Ni	%Mo	%Nb	%Fe
SDX NiCr-3	0.01	0.3	0.3	19	Bal.	0.5	2.5	<3
SDX NiCrMo-3	0.01	0.3	0.3	21	Bal.	9	3	<3

## Materials to be welded

	Flux SWX 282 with wire:
Alloy 82	SDX NiCr-3
Alloy 600	SDX NiCr-3
Alloy 625	SDX NiCrMo-3

## Packaging data

Flux unit net weight	Kg	Lbs
Aluminium/PE Bag EAE*	25	55

\*EAE Excess Air Evacuation

# SWX 305

EN ISO 14174: S A AAS 2B DC

Flux/strip combinations for the SAW strip cladding of stainless strips

## Description

Acid aluminium-silicate, agglomerated flux designed for submerged strip cladding with stainless strips on mild or low alloyed steel. It has good welding characteristics and gives a smooth bead appearance and easy slag removal.

SWX 305 is a non-alloying flux. The flux is delivered in Hobart humidity proof EAE bag, eliminating the need to re-dry the flux.

- Offshore fabrication
- Pressure vessels
- Petrochemical industry
- Paper and pulp plants
- Offshore oil and gas processing

## Flux characteristics

Flux type	Acid-Aluminium-Silicate
Basicity index	1.1
Alloy transfer	Non-alloying
Density	~ 1.1 kg/litre
Grain size	0.2-1.6 mm /12-65 mesh
Current	DC+
Re-drying unopened bag	Not required
Re-drying opened bag	See storage and handling recommendations

## Flux main components

AL <sub>2</sub> O <sub>3</sub> + MnO	CaO + MgO	SiO <sub>2</sub> + TiO <sub>2</sub>	CaF <sub>2</sub>
~ 20%	~ 5%	~ 10%	~ 60%

## Flux SWX 305 - Chemical composition all weld metal, typical values

With strip	%C	%Si	%Mn	%Cr	%Ni	%Mo	%Nb	%N	FN
Cromastrip 308L	0.02	0.6	1.0	19.0	10.5	0.1		0.03	~6
Cromastrip 316L	0.02	0.7	1.1	18.0	13.0	2.2		0.02	~7
Cromastrip 347	0.02	0.7	1.1	19.0	10.5	0.1	0.4	0.03	~8

(All analyses in 2nd layer, 1st layer welded with Cromastrip 309L.)

## Packaging data

Flux unit net weight	Kg	Lbs
Aluminium/PE Bag EAE*	25	55

\*EAE Excess Air Evacuation

# SWX 330

EN ISO 14174: ES A FB 2B DC

Flux/strip combinations for electrosag strip cladding

## Description

Hobart SWX 330 is a fluoride-basic, non-alloying agglomerated flux designed for standard speed electrosag strip cladding with austenitic stainless strips of the AWS EQ300 series. It has a high current carrying capacity and can be used for single or multi layer cladding.

It features excellent slag removal, also on preheated surfaces, leaving a bright deposit with smooth overlap between runs. The flux is delivered in Hobart humidity proof EAE bag, eliminating the need to re-dry the flux.

- Pressure vessels
- Petrochemical industry
- Paper and pulp plants
- Offshore oil and gas processing
- Nuclear

## Flux characteristics

Flux type	Fluoride-basic
Basicity index	3.2 (Boniszewski)
Alloy transfer	None
Density	1.1 kg/litre
Grain size	0.2-1.2 mm /12-65 mesh
Current	DC+
Re-drying unopened bag	Not required
Re-drying opened bag	See storage and handling recommendations

## Flux main components

AL <sub>2</sub> O <sub>3</sub> + MnO	CaO + MgO	SiO <sub>2</sub> + TiO <sub>2</sub>	CaF <sub>2</sub>
~ 25%	~ 0%	~ 10%	~ 65%

## Flux SWX 330 - Chemical composition all weld metal, typical values

With strip	%C	%Si	%Mn	%Cr	%Ni	%Mo	%Nb	%N	FN	Deposit type
Cromastrip 21.11 L	0.02	0.5	1.2	20.0	11.0	0.2		0.05	~4	308L
Cromastrip 21.13.3 L	0.02	0.5	1.3	19.0	13.0	3.0		0.05	~6	316L
Cromastrip 21.11 LNb	0.02	0.5	1.2	20.0	11.0	0.2	0.4	0.05	~4	347

(Single layer composition. Parameters: 1350 A, 25 V, v travel 22 cm/min. (9"/min))

## Packaging data

Flux unit net weight	Kg	Lbs
Aluminium/PE Bag EAE*	25	55

\*EAE Excess Air Evacuation



# SWX 382

EN ISO 14174: ES A AF 2B DC

## Flux/strip combinations for electroslag strip cladding

### Description

Hobart SWX 382 is a high basic, non-alloying, agglomerated flux designed for standard speed electroslag strip cladding with Ni-based strips. It has a high current carrying capacity and can be used for single or multi layer cladding with strips.

It features excellent slag removal, also on preheated surfaces, leaving a bright deposit with smooth overlap between runs. The flux is delivered in Hobart humidity proof EAE bag, eliminating the need to re-dry the flux.

- Pressure vessels
- Petrochemical industry
- Paper and pulp plants
- Oil and gas processing

### Flux characteristics

Flux type	Aluminate-fluoride
Basicity index	3.7 (Boniszewski)
Alloy transfer	None
Density	1.1 kg/litre
Grain size	0.2-1.2 mm /16-65 mesh
Current	DC+
Re-drying unopened bag	Not required
Re-drying opened bag	See storage and handling recommendations

### Flux main components

AL <sub>2</sub> O <sub>3</sub> + MnO	CaO + MgO	SiO <sub>2</sub> + TiO <sub>2</sub>	CaF <sub>2</sub>
~ 20%	~5%	~ 10%	~ 60%

### Flux SWX 382 - Chemical composition all weld metal, typical values

With strip	%C	%Si	%Mn	%Cr	%Ni	%Mo	%Nb	%Fe	Deposit type
Cromastrip NiCr-3*	0.03	0.6	2.7	18.0	bal.		2.1	9	
Cromastrip NiCr-3**	0.02	0.5	3.0	19.5	bal.		2.3	4	Alloy 82
Cromastrip NiCrMo-3*	0.03	0.4	0.3	20.0	bal.	9	2.9	9	
Cromastrip NiCrMo-3**	0.02	0.3	0.2	21.5	bal.	9	3.2	4	Alloy 625

(\* 1st layer, 2 mm below surface. Welding parameters: 1200A/23V/18 cm/min. Strip 60 x 0.5 mm.)

(\*\* 2nd layer, 2 mm below surface. Welding parameters: 1200A/23V/18 cm/min. Strip 60 x 0.5 mm. )

### Packaging data

Flux unit net weight	Kg	Lbs
Aluminium/PE Bag EAE*	22.7	50

\*EAE Excess Air Evacuation

# SWX 010

## Powder backing for one-sided welding

### Description

Hobart SWX 010 is an agglomerated backing powder for one-sided welding with the use of copper supports. It contains special components which enhance solidification of the slag to provide a regular and smooth root pass profile. It features excellent slag detachability.

SWX 010 powder backing is non-alloying and has no influence on weld metal properties. Typical applications are the one-sided welding of panel sections in shipbuilding and the joining of strips in spiral pipe mills. Suited for multi-wire operations. It is supplied in moisture proof cans and must be used without re-drying.

- Shipbuilding
- Spiral pipe mills

### Flux characteristics

Flux type	Not applicable
Basicity index	Not applicable
Alloy transfer	None
Density	1.1 kg/litre
Grain size	0.2-1.6 mm /12-65 mesh
Current	Not applicable
Re-drying unopened bag	Shall not be re-dried
Re-drying opened bag	See storage and handling recommendations

### Powder main components

$Al_2O_3 + MnO$	$CaO + MgO$	$SiO_2 + TiO_2$	$CaF_2$
~ 15%	~ 50%	~ 30%	~ 0%

### Storage, recycling and re-drying

Store the powder backing in the sealed can. Reclose lid after opening. Make sure the sealing is in the correct position. The powder backing should not be re-dried.

### Health and safety

Do not breathe the fumes. Use adequate fume extraction system and/or personal protection equipment. Study the Material Safety Data Sheet carefully.

# Approval Certificates

## Certificate of Approval

**Zulassungsbescheinigung**

Certificate no. 1350177 HH

**The Welding Consumables**  
Die Schweißzusätze und -hilfsstoffe  
Electrode/Wire Manufacturer/Supplier  
Electroden-/Draht-Hersteller/Lieferer

Brand: ITW Welding GmbH (ehemals Drahtzug Stein wire & welding GmbH & Co. KG)  
Flux/Shielding Gas Manufacturer/Supplier: SDX S3Si-EH12K  
Schweißpulver-/Schutzgas-Hersteller/Lieferer

Brand: SWX 150  
Marke: ISO 17171-A S 46 6 FB S3Si / SA FB 1 55 AC H5

**Classification**  
Klassifizierung (DIN, EN, ISO o.ä.)  
are approved based upon the approval test as follows \*:  
werden aufgrund der Zulassungsprüfung wie folgt zugelassen\*:

Grade, Suffix(es): 6Y46MH5  
Welding Process: Submerged Arc Welding in Multi-run-technique  
Welding Position(s): (4) PA (d)  
Diameter (mm): 1,6 - 4,0  
Diameter (mm): DC+

**Range of Application:**  
Anwendungsbereich:  
Materials and Heat Treatment:  
Werkstoffe und Wärmebehandlung:  
As welded condition.

Service Temperature:  
Anwendungsbereich:  
Remarks:  
Bemerkungen:

Initial test: 06/2013  
Erstprüfung: 2013-07-10

**Germanischer Lloyd**

Validity: 06/2013

**ISO 9001**

Standard: Certificate Registr. No. 01 100 123

Certificate Holder: TÜV Rheinland

Scope: SWEL S - 42 Indur Calv ul M PL

**HOBART FILLER METALS**

Certificate number 11

In accordance with

Your order: 98852  
Your order date: 27.02.2013  
Your reference: Dimit Rypen

**Invoice address**

Customer no.: 100380  
Customer: ITW Welding Product  
Address: P. O. Box 1551  
3260 LD Oud Beekoven  
The Netherlands  
Contact: Dimit Rypen  
Phone: +31 186 64 148  
Email: d.rypen@itw.nl

**Delivered product**

Description: SWX 155  
Item no.: 1350225  
Quantity kg: 50

**Particle size**  
Cumulative

2.0 mm 0%  
1.6 mm 5%  
0.8 mm 95%  
0.4 mm 100%

**Classification**  
EN ISO 14174-S A AB 1 67 AC H5

**Comments**

This product is supplied under a G+  
This is a computer generated document  
SWELDX AB, Box 2246, S-400 02  
Anna Cymne  
Quality Manager

## TÜVRheinland CERTIFICATE

Approval of a manufacturer of Welding Consumables  
VdTÜV Appl. on the Schweißtechnik 1153:01/200

**DB** Mobility Networks Logistics

**Zulassungsbescheinigung für Schweißzusätze und -hilfsstoffe**

Hersteller: SWELDX AB  
Sisjö Kullegata 11  
42133 Västra Frölunda  
Schweden

Schweißzusatz: Schweißpulver  
Bezeichnung: SWELDX 120  
DIN EN ISO 14174-S A AB 1 57 AC H5

Hersteller: SWELDX AB  
Sisjö Kullegata 11  
42133 Västra Frölunda  
Schweden

**VdTÜV-Kennblatt für Schweißzusätze**

1 Hersteller/Lieferer: SWELDX AB  
S 400 95 Göteborg, Schweden

2 Kennblatt-Nummer: 12401.00  
06.12

3 Schweißzusatz: Draht-Pulver-Kombination

4 Marke: SWELDX S 2

7 Typ: DIN EN ISO 14171 - S2

6 Pulvermarke: SWELDX 120

9 Pulvertyp: DIN EN 760 - SA AB 157 AC H5

10 Pulverkörnung: 0,1 - 1,6 mm

13 Die weitere Gültigkeit wird in der jeweils letzten Ausgabe der CD-ROM 'VdTÜV-eignungsgeprüfte Schweißzusätze' bescheinigt.

15 Wärmebehandlung (Wb) nach dem Schweißen und Werkstoffe

Pos Wb (T) Gruppe 1 (U) Gruppe 1.2

16 Die Werkstofferteilung entspricht ISO 15608:2000

19 Falls unter 32 nicht anders angegeben, ist die Eignungsprüfung in Position waagrecht gültig.

20 Drahtdurchmesser/Bandmessungen [mm] 4,0

Stromstärke [A] 580

Spannung [V] 29

Gerätevorschub [cm/min] 55

Arbeitstemperatur [°C] 150 - 200

22 Draht-Pulver: Nahtaufbau geeignet für: -Mehrlagenschweißung

23 Wanddicke: unbegrenzt

26 Höchste Betriebstemperatur im Kurzzeitbereich wie Grundwerkstoff, jedoch max.: 350 °C

27 Höchste Betriebstemperatur im Langzeitbereich wie Grundwerkstoff, jedoch max.: 350 °C

28 Tiefste Betriebstemperatur im Langzeitbereich wie Grundwerkstoff, jedoch max.: 350 °C

29 Berechnungskennwert: wie Grundwerkstoff

30 Bei Einsatz im Langzeitbereich: 350 °C

31 Korrosionsbeständigkeit nachgewiesen nach: 350 °C

32 Bemerkungen: -50 °C

33 Die Eignungsprüfung erfolgte auf der Grundlage des VdTÜV-Merkblattes 1153. Soweit in Rubrik 32 - Bemerkungen - nicht anders angegeben, ist dieser Schweißzusatz unter Beachtung des Anhangs / Abschnitt 4 der Druckgeräterichtlinie geeignet.

34 Erläuterungen: A - angelassen L - lösungsgeglüht S - spannungsarmgeglüht SL - stabilgeglüht U - ungeglüht N - normalgeglüht V - vergütet W - weichgeglüht

35 Erstellt durch: TÜV Rheinland Group

Die Vervielfältigung, die Verbreitung, der Nachdruck, und die Gesamtwiedergabe auf fotomechanischem oder ähnlichem Wege bleiben, auch bei auszugsweiser Vervielfältigung, dem vorherigen Zustimmung des Herausgebers vorbehalten.

Vertrieb: TÜV-Media GmbH, Am Grauen Stein, 51105 Köln - Unternehmenseinheit TÜV Rheinland Group

**Herausgeber: Verband der TÜV e.V.**

G+ - Gleichstrom Pluspol  
G- - Gleichstrom Minuspol  
W - Wechselstrom  
- - - erscheint im selben Verlag



# Packaging Solutions

## FLUX

Hobart provides fluxes with maximum security related to weld integrity. Hydrogen in the weld metal is the greatest threat to weld integrity. Elevated levels of moisture in the flux must be avoided at any cost. Since fluxes are hygroscopic re-drying is generally recommended. The results of re-drying depends on the use of proper drying parameters and on moisture control. The parameters recommended by flux producers do generally not restore original moisture levels. Consequently, prevention of moisture pick-up is extremely important.

In order to protect the flux against moisture pick-up from the air during storage and transportation, Hobart applies moisture proof packaging as standard.

---

### Packaging - EAE bag

For the standard weight bags, the Hobart solution is a rigidly welded 5 layer polyethylene – aluminium foil bag. The packaging material is resistant to any H<sub>2</sub>O transfer. In addition Hobart applies EAE (Excess Air Evacuation). Each bag passes a process where excess air is evacuated, creating a reduced pressure atmosphere in the bag. As a result moisture pick-up is drastically reduced and products stored un-opened can be used without re-drying.

---

### Packaging - DoubleBag

The Hobart solution for bulk packaging is a polypropylene outer bag with an inside polyethylene-aluminium lining. The packaging material is resistant to any H<sub>2</sub>O transfer. After filling, the opening is welded. The moisture properties of the double bag are basically the same as for the EAE bag. Moisture-pick up is drastically reduced and products stored un-opened can be used without re-drying.

The bottom of the DoubleBag features a 400 mm (16") long discharge spout, equipped with a patented locking device to easily control and stop the flow of flux.

## Two major user benefits

1. Dry flux means safe welding. The elimination of moisture pick-up makes (possibly ineffective) re-drying redundant and ensures moisture close to the levels as produced.
2. Re-drying is a costly procedure considering the administration, energy consumption, operator handling and equipment investment involved. Its elimination from the production chain saves money and time, while supporting the environment by reducing emissions from energy consumption. Moreover, there is no risk of increasing the dust content by handling the flux in a re-drying process.

Finally, the effectiveness of re-drying depends highly on the process. When the re-drying temperature is too low or when the flux stays too short in the oven, the moisture level may not be lowered sufficiently. This is difficult to determine, as sophisticated laboratory equipment is required to test the actual moisture level of the flux.

---

## Wires

Hobart wires are supplied in accordance with the market requirements. Hobart has defined a standard range of spools and weights, where the target is to always supply off the shelf. In addition Hobart wires are available in different special packaging executions for specific customer needs.





# Storage and Handling Recommendations

## Hobart SubCOR cored wires and SDX solid wires for submerged arc welding

Following recommendations are valid for SubCOR and SDX solid submerged arc wires.

### Storage and handling recommendations:

- Store wires under dry conditions in the original sealed packaging.
- Avoid contact between wire and substances such as water or any other kind of liquid or vapour, oil, grease or corrosion.
- Do not touch the wire surface with bare hands.
- Avoid exposure of the wire below dew point.
- Store the wire in its original plastic bag and box when not used.
- Apply first in-first out for stocked wires.

## Hobart submerged arc welding fluxes.

All Hobart fluxes are packed in moisture proof bags. The fluxes are dry and capable of giving a weld metal hydrogen content below 5 ml/100g without costly (and possibly ineffective) re-drying. This can be achieved when fabricators take necessary actions to prevent pick-up of hydrogen by the weld metal from other sources than the welding consumables.

### Following Hobart standard moisture proof welding flux packaging types are available:

- Hobart 20, 22.6 or 25 kg (44, 50 or 55 lbs) EAE (Excess Air Evacuation) flux bags consisting of a 5 layer laminate with an impermeable aluminium foil. The bag weight depends on the flux type.
- Hobart DoubleBags up to 1 ton, lined with an impermeable aluminium foil.

### Following storage and handling procedures are recommended to maintain Hobart fluxes in their original dry condition or to re-dry fluxes that may have absorbed moisture:

- Hobart welding fluxes in their original moisture proof packaging can be safely stored for a period of maximum 5 years. Make sure that the packaging cannot get damaged.
- In case the original moisture proof packaging gets damaged, flux shall be re-packed in sealed containers and stored under controlled climatic conditions of 15-35°C (60-95°F) and max 70% relative humidity, for a period of maximum 1 year.
- At shift end, flux from unprotected flux hoppers and from opened packs shall be stored in a drying cabinet or heated flux hopper at 150 +/- 25°C (300 +/- 45°F).
- During continuous welding operations, unused flux can be recycled and returned to the flux hopper for reuse. Maintain compressed air in the recycling system free from moisture and oil. Remove slag and mill scale from the recycled flux. Add at least one part of new flux to three parts of recycled flux.
- For hydrogen critical applications, any flux suspected of having picked-up hydrogen must be re-dried at a temperature of 300 – 350 °C (570 – 660 °F) for a minimum of 2 hours. Re-drying time starts when the entire quantity of flux has reached 300 °C (570 °F). Re-dried flux must be stored at 150 +/- 25°C (300 +/- 45°F) before use.



# Full performance submerged arc welding pays back

Successful submerged arc welding is not restricted to choosing the correct flux and wire to achieve the required mechanical properties, but also deals with setting-up the process in the best possible manner to leverage the investment optimally.

Below, we will show examples of submerged arc process optimization and the benefits it brings to fabricators. To understand these, it is first needed to define the different cost components. Together they make up the basic cost structure of any manufacturing company.

Cost component	Abbreviation	Examples of cost included
Direct Material	DM	Raw materials, components, packaging material, material losses in the process such as scrap
Variable Overhead	VOH	Energy costs for manufacturing process, process consumables, wear parts, cost of temporary workers.
Variable cost	VC	The sum of DM+VOH. Also called Direct costs as they are zero if nothing is manufactured.
Direct Labor	DL	Wages or salaries, social charges, work clothes, production bonuses, free meals, transport to and from work etc. for blue collar operators in the work shop.
Fixed Overhead	FOH	Rental of premises, leasing of equipment, white collar personnel including production management, indirect blue collar personnel such as truck drivers and repair men, costs for heating and lighting, connection fees for utilities and communication. Sometimes also called Period Costs.
Capital costs	CCC	Capital costs for equipment, owned premises. Typically both calculated interests and depreciation are included.
Manufacturing cost	MC	Sometimes denominated Fully absorbed manufacturing costs
Sales and Administration	SG&A	Sales and Administration, typically abbreviated S&A or SG&A. General Management, Sales, Accounting, Logistics, R&D, Engineering etc. Everything from salaries to company cars, from office stationeries to outbound transport costs.
Total cost	TC	Also called Cost of Goods Sold.

## Direct labor (DL)

DL is traditionally considered a direct cost, but in reality it is not possible to influence short to medium term for the vast majority of companies. Therefore Direct Labor is regarded as a fixed cost in the Hobart benefit assessment.

## Variable contribution


Variable contribution = Revenue - Direct Costs. This is a key measurement, as it tells how much the sales of an item contribute to cover fixed overheads. Because fixed costs in principle do not change with the sales volume, one could argue that the incremental variable contribution is all profit, as soon as the total fixed costs have been covered. When the concept Variable Margin is used, it means the Variable Contribution in % of the Revenues.

## Impact of welding

Welding consumables for SAW joining typically stand for between 0.5 – 2% of the total cost of the welded object. However, with a less feasible choice of consumables or set-up of the welding process, the impact on manufacturing cost will be far higher than this.

During our efforts to support our clients with SAW process optimization, we have achieved significant improvements with productivity gains of over 20%. When welding is the bottleneck, selling the additional capacity significantly improves the profit.

The diagram on the right is based on what we would call typical distribution of the costs and revenues for companies working with submerged arc welding of mild and low-alloyed steels. Based on our experience the majority of companies will not be too far off from this estimation.

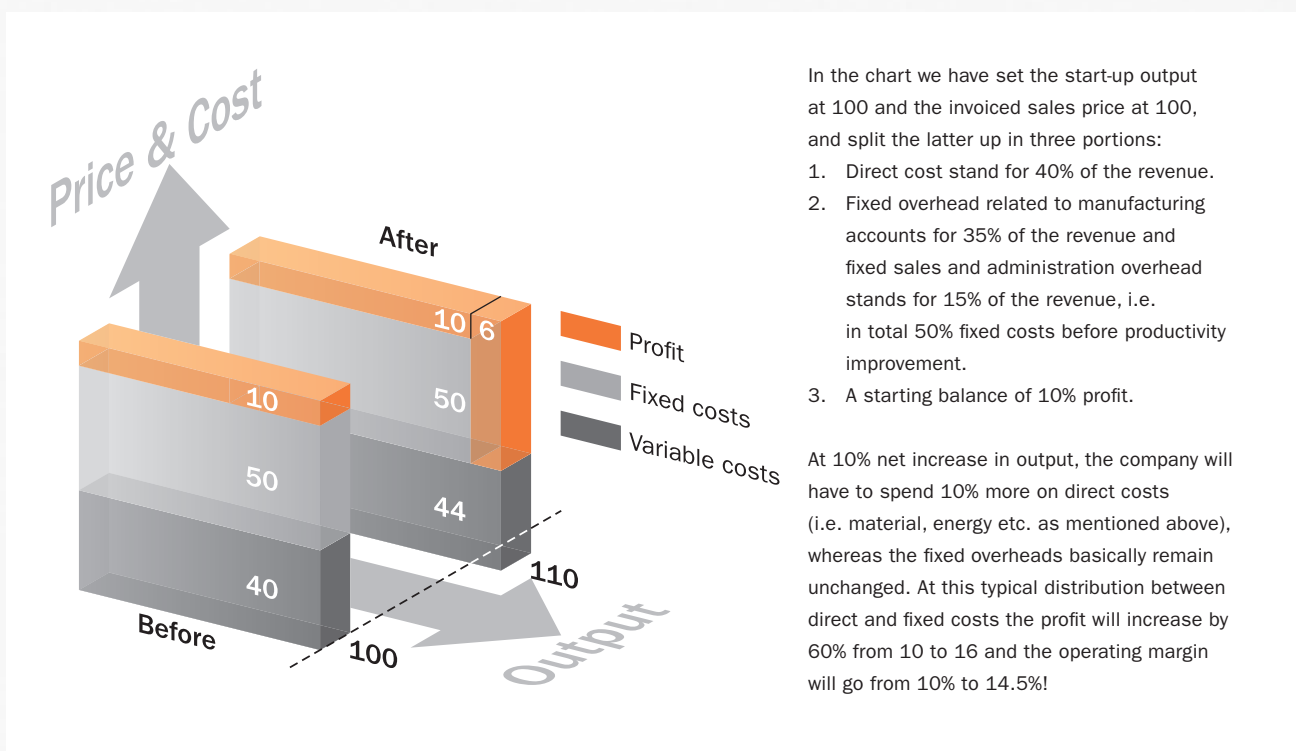

ITW Welding has the intention to support clients to improve productivity and quality. All businesses are different. Hence an individual assessment has to be conducted to identify the potential. Sometimes it is possible to come up with improvements with the same leverage as above, sometimes the result is mainly savings in the direct cost area. Here is a real example of what such activities could mean to a client in monetary terms:

Company:	Spiral pipe mill			
	<b>Action</b>	<ul style="list-style-type: none"> <li>• Change of flux to Hobart SWX 135 and change of wire setup</li> <li>• Traveling speed increased by 18% from 2.0 to 2.4 m/min (79 to 94 inches/min)</li> <li>• Net cycle time improvement 9.6%</li> </ul>		
	Output of pipes before improvement	150.000 tons per annum	330.000 lbs per annum	
	Output of pipes after improvement	164.400 tons per annum	361.680 lbs per annum	
	Increased output	14.400 tons per annum	361.680 lbs per annum	
	Difference	9.6 %		
	Operating margin before improvement	9,9 %		
	<b>Operating margin after improvement</b>	<b>14.1 %</b>		
	Improved operating income in relation to flux consumption	14.87 EUR/kg flux used	8,77 USD/lb flux used	

*This case involves a company being in the fortunate situation where demand is higher than their output capabilities. Hobart regards the outcome of the work done in co-operation with the client quite successful, with an improvement of the operating margin by 4.2 %-units. To express the value in another sense, it accounted 14.87 EUR/kg (8.77 USD/lb) for every kg (lb) of flux consumed in the pipe manufacturing.*

It is Hobart's objective to be not only a supplier of welding consumables and equipment, but to support its clients in improving their total welding operations. Aware that our customer's success equals our own, we regard this a continuous effort to be repeated frequently.

# HOBART SubCOR Cored Wires for Submerged Arc Welding

The use of SubCOR flux cored wires in submerged arc welding provides interesting options to influence weld metal chemistry and thereby microstructure and mechanical properties of the weld. In the same way as submerged arc welding fluxes, the flux formulation of these wires promotes a microstructure with a low level of inclusions. This translates in superior low-temperature impact toughness. A high crack resistance is further promoted by the

combination of very low-hydrogen weld metal and a favorable, fine microstructure of mainly acicular ferrite. An example is SubCOR SL 731, a basic cored wire for the submerged arc welding of non-alloyed and fine grain steels. When used in combination with a universally applied low basicity flux, such as SWX 110, it yields superior low-temperature impact toughness over S2Mo-EA2 solid wire, at comparable yield strength levels (*table 1*).

**Typical mechanical properties in the as welded condition obtained with universally applied welding flux SWX 110.**

Product name	EN	AWS	Cond.	Rp 0.2		Rm		CVN	
				(MPa)	(ksi)	(MPa)	(ksi)	(J)	(ft-lbf)
								-40°C	-40°F
SDX S2Mo-EA2	S 46 2 AB S2Mo	F7A4-EA2-A2	AW	510	74	590	85	35	26
SubCOR SL 731	S 46 4 AB T3		AW	490	71	600	87	115	85

(Table 1.)

Another example is SubCOR SL 742, a cored wire for the submerged arc welding of high strength steel for low-temperature service. When used with SWX 150, a high basicity flux for demanding multi-layer applications, it gives comfortable safety margins for impact toughness at

low-temperatures compared with its solid wire equivalent SDX S3Ni2.5CrMo (table 2). The same is valid for SDX CrMo1-EB2R solid wire and SubCOR SL P11 in the creep resistant range.


**Typical mechanical properties in the as welded condition obtained with high basic flux SWX 150**

Product name	EN	AWS	Cond.	Rp 0.2		Rm		CVN	
				(MPa)	(ksi)	(MPa)	(ksi)	(J)	(ft-lbf)
								-60°C	-76°F
SDX S3Ni2.5CrMo	S 69 6 FB S3Ni2.5CrMo		AW	710	103	800	116	55	40
SubCOR SL 742	S 69 6 FB T3 Ni2.5CrMo	F11A8-ECF5-F5	AW	720	104	820	119	100	74
								-20°C	-4°F
SDX CrMo1-EB2R	S S CrMo1 FB	F8P2-EB2R-B2	SR	490	71	620	90	100	74
SubCOR SL P11	S T CrMo1 FB		SR	510	74	600	90	200	147

## Additional benefits of SubCOR SL type cored wires

- A higher safety margin on low-temperature impact toughness.
- Weld metal hydrogen <4 HDM can be reached.
- Totally insensitive for moisture pick-up, regardless climatic conditions.
- No special storage requirements. Can be stored as solid wires.
- Improved current transfer from contact tip, due to copper coating.
- Low contact tip wear.
- Greater crack resistance due to a favorable rounded bead shape with reduced depth-width ratio.
- Wide cast and low helix and moderate stiffness give consistent wire feeding and straight wire delivery from the contact tip.
- Available for a wide range of non- and low-alloyed steel grades.
- Any technically relevant alloy can be produced in small production units.

Steel category	Hobart SubCOR cored wire	Application
Unalloyed	SL 731	General purpose AW/SR
	SL 840 HC	Mech. Engineering, pipelines, vessels AW/SR/N/N+A
	SL 735-1W-5W	Single run/two run
High strength	SL 741	Re 315-550 MPa AW/SR
	SL 742	Re >690 MPa AW/SR
	SL 745	Re > 890 MPa AW
Weather resistant	SL 281 Cr	Re 255 - 460 MPa
Creep resistant	SL P1	0.5Mo, P1
	SL P1 MOD	0.5Mo + V (14MoV6-3)
	SL P11	1.25Cr/0.5Mo, P11
	SL P12 MOD	1.00Cr/0.5Mo, P12
	SL P36	0.5 Mo, P36
	SL P22	2.25 Cr/1Mo, P22
	SL P24	2.5Cr/1Mo +V, P24
	SL P5	5Cr/0.5Mo, P5
	SL P9	9Cr/1Mo, P9
	SL P91	9Cr/1Mo + Nb, V, P91
	SL P92	10Cr/1Mo + V, W, P91

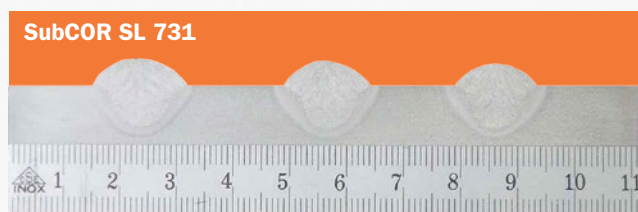

*Difference in weld profile between SubCOR SL 731 cored wire and S2 solid wire SDX S2. The cored wire gives a more crack resistant rounded bead shape with reduced depth-width ratio. Welded with SWX 120 at 600A and 25 mm (1") stickout length. Wire diameter 2.4 mm (1/10").*




# Improved productivity from SubCOR metal-cored wires

SubCOR metal-cored wires for submerged arc welding offer a number of advantages over the use of solid wires – in terms of welding efficiency, weldability and weld quality.

- Potential for higher deposition rates than solid wires at the same amperage.
- Potential to increase deposition without increasing heat input, or to decrease heat input without sacrificing deposition.
- Often better impact toughness and CTOD properties.
- A more favorable, broader shaped penetration and fusion pattern.
- Greater tolerance to gaps, poor fit up, and burn through.

Metal-cored wires are composite tubular electrodes consisting of a metal sheath and a core of metallic and/or non-metallic ingredients. An example of a metallic ingredient is iron powder. The deposition efficiency will increase with the amount of metallic ingredients in a composite tubular wire. Non-metallic ingredients can, for instance, be agents that clean and deoxidize the weld or slag forming components. In a metal cored wire, the current travels only through the sheath, whereas in a solid

wire the current travels through the entire cross-section of the wire (Figure 1). Therefore, at an equivalent amperage setting, a metal-cored wire will experience higher current densities. The resulting increased melt-off rates, in combination with a high percentage of metallic particles, offers increased deposition rates. The effect is most prominent at higher welding currents, as can be seen from Figures 2 and 3.

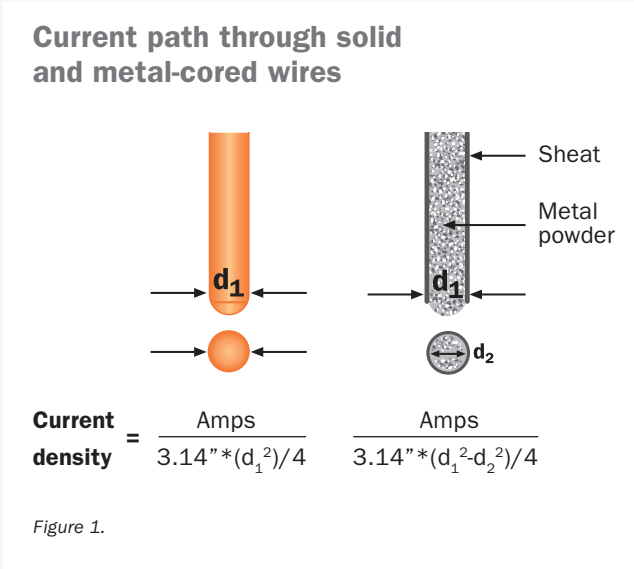

3.2 mm (1/8") Diameter wire Comparisons (DCEP)

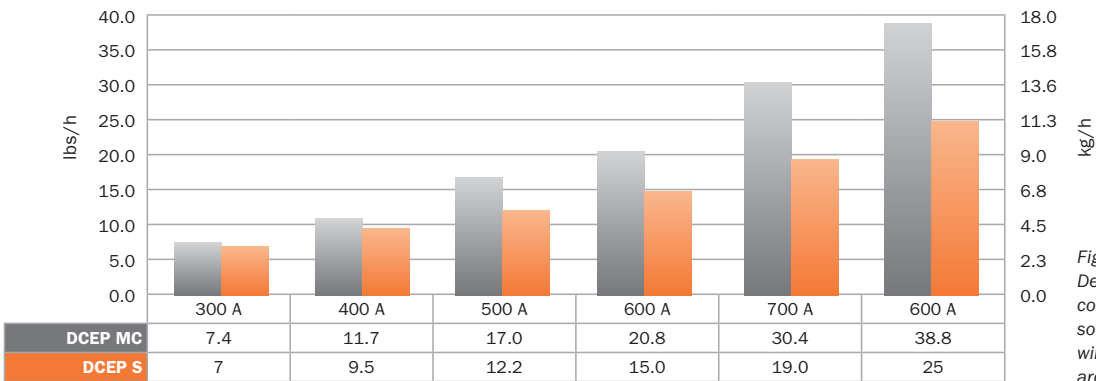


Figure 2.  
Deposition rate comparison between solid and metal-cored wires for submerged arc welding.

4.0 mm (5/32") Diameter wire Comparisons (DCEP)

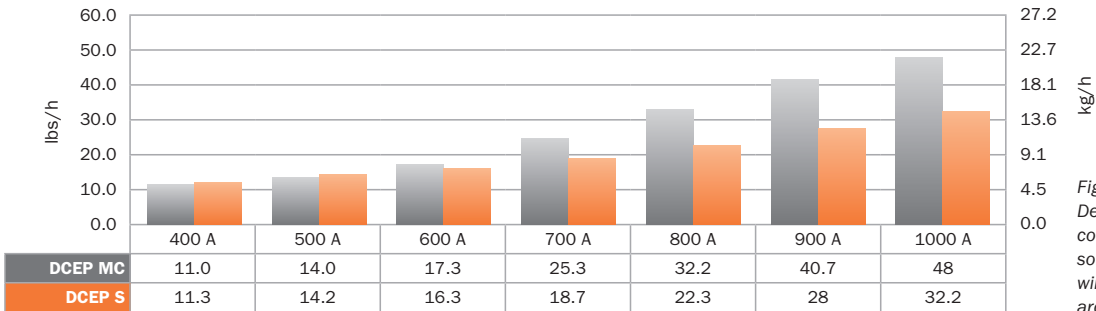


Figure 3.  
Deposition rate comparison between solid and metal-cored wires for submerged arc welding.

Following data results from a qualification test performed in offshore fabrication. The steel used was an offshore grade with a minimum yield strength of 460 MPa (67 ksi) in 32 mm (1.25") plate thickness. The joint preparation was a 60° V-joint. The root pass was done by GMAW with an S2Ni1-ENi1 solid wire. For the submerged arc welding, variable balance power sources were used in a triple wire set up.

	Metric		Imperial		MC vs Solid
	Solid wire	Metal cored wire	Solid wire	Metal cored wire	
<b>Submerged arc wire</b>	<b>Hobart SDX S3Ni1Mo.2-ENi5</b>	<b>Hobart SubCOR 92-S</b>	<b>Hobart SDX S3Ni1Mo.2-ENi5</b>	<b>Hobart SDX S3Ni1Mo.2-ENi5</b>	
Flux	Hobart SWX 150	Hobart SWX 150	Hobart SWX 150	Hobart SWX 150	
Wire class EN ISO 14171/AWS A5.23	S3Ni1Mo0.2/ENi5	-/ECM1	S3Ni1Mo0.2/ENi5	-/ECM1	
Wire set up	3 x 4.0 mm	3 x 4.0 mm	3 x 5/32"	3 x 5/32"	
Process description	AC/AC/AC	AC/AC/AC	AC/AC/AC	AC/AC/AC	
Parameters	30-35 V, 550-700 A	28-36 V, 600-700 A	30-35 V, 550-700 A	28-36 V, 600-700 A	
Wire feed speed	125-190 cm/min	190-250 cm/min	50-75 inch/min	75-100 inch/min	
Travel speed	107 cm/min	120 cm/min	42 inch/min	47 inch/min	+12%
No. of passes	12	11	12	11	-1
Max interpass temperature	260 °C	260 °C	500 °F	500 °F	
Peak heat input	3.3 kJ/mm	3.2 kJ/mm	84 kJ/inch	82 kJ/inch	
Average heat input	3.1 kJ/mm	3.0 kJ/mm	79 kJ/inch	77 kJ/inch	
AW yield strength	497 MPa	490 MPa	72.1 ksi	71.1 ksi	
Cross weld tensile	500 MPa	498 MPa	72.6 ksi	72.1 ksi	
CVN @ -40 °C (-40 °F) - Root	102 J	103 J	75 ft-lbs	76 ft-lbs	
CVN @ -40 °C (-40 °F) - Cap	88 J	121 J	65 ft-lbs	89 ft-lbs	+37%
CTOD @-10 °C (+14 °F)	1.27 mm	1.61 mm	0.050 inch	0.063 inch	
<b>Deposition rate</b>	<b>24.9 kg/h</b>	<b>30.6 kg/h</b>	<b>54.8 lbs/h</b>	<b>67.3 lbs/h</b>	<b>+23%</b>

This case represents well the difference between a metal-cored and a solid wire in a 4.0 mm (5/32") wire diameter application. You will typically see both a productivity gain as well as improved mechanical properties.

Productivity is, of course, always important in any business. Metal-cored wires provide this. However, sometimes the required mechanical properties are the limiting factor and, in most cases, these can be met by exchanging solid to MC wires, without sacrificing productivity. There are also cases, mainly in high strength and high temperature applications, where the mechanical properties cannot be met without exchanging the solid wire with a cored wire.

#### Estimating deposition rates for metal-cored and solid wires

An efficiency of 99% is used when calculating the deposition rates of solid wires when used in the SAW process. In comparison, metal-cored wires use a 97% efficiency rate for calculating deposition rates, whereas efficiency rates of 92% can be realized with flux-cored wire. It should also be noted that metal-cored wires for SAW are formulated

differently than those metal-cored wires formulated to run with shielding gas. They show differences in deposition efficiency, as well as in the weight of the wire. By using the numbers below one can create a simple spread sheet to calculate deposition rates based off of wire feed rates and deposition efficiency.

Net weld metal deposition for metal cored and solid SAW wires				
Efficiency	MC 97% efficiency		Solid 99% efficiency	
Weight	g/m		lbs/inch	
Wire diameter	MC	Solid	MC	Solid
2.4 mm (3/32")	30	35	0.0017	0.0020
3.2 mm (1/8")	50	60	0.0028	0.0034
4.0 mm (5/32")	80	95	0.0045	0.0053

Tabel 1

#### Approximate deposition rate:

Wfs = Wire feed speed cm/min (inches/min)

**Metric:** Deposition rate kg/h =

Wire weight g/m \* Wfs cm/min \* 0.0006

**Imperial:** Deposition rate lbs/h =

Wire weight lbs/inch \* Wfs inches/min \* 60

# Flux Cored Micro Injection


Flux cored micro injection (FMI) is a special application of Hobart SubCOR SL cored wires. In single- and two-run welding, micro-alloying through the cored wire is an effective way to counteract the formation of a coarse microstructure and to promote good impact toughness. In single- or two-run applications, recrystallization by subsequent layers does not occur, or not to the same extent as with multi-layer welds. As a consequence, the microstructure maintains its solidification structure with high amounts of coarse ferrite and limited impact toughness. Micro-alloying through the core of flux cored wires, provides nuclei in the solidifying weld metal that act as initiation points for a fine microstructure of favourable acicular ferrite giving high impact toughness. Typical single- and two-run applications are found in the welding of ship panels and in the production of line pipe in pipe mills. For productivity reasons, multi-layer welds

are avoided as much as possible and as high as possible plate thickness is covered with the single- or two-run techniques, mostly with multi-wire welding heads. Flux cored micro injection with SubCOR SL cored wires are developed to give good weld metal impact toughness in such applications.

SubCOR SL 735 -1W (1 wire) is developed for single wire welding. Increasing levels of micro-alloying are applied in the multi-wire versions - 2W, 3W, 4W and 5W - which are developed for respectively two, three, four and five wire welding. It is important to note that only a single cored wire is needed in multi-wire applications to obtain the desired effect. With the 2W, 3W, 4W and 5W versions, cored wire formulations are adapted to obtain the same weld chemistry as with the 1W version. All other wires on the same welding head are standard solid wire types.

## The benefits of FMI applied in high deposition submerged arc welding are:

- A finer microstructure and associated higher weld metal impact toughness.
- Thicker plate thicknesses can be covered.
- Good weld metal impact toughness is maintained at higher deposition rates.

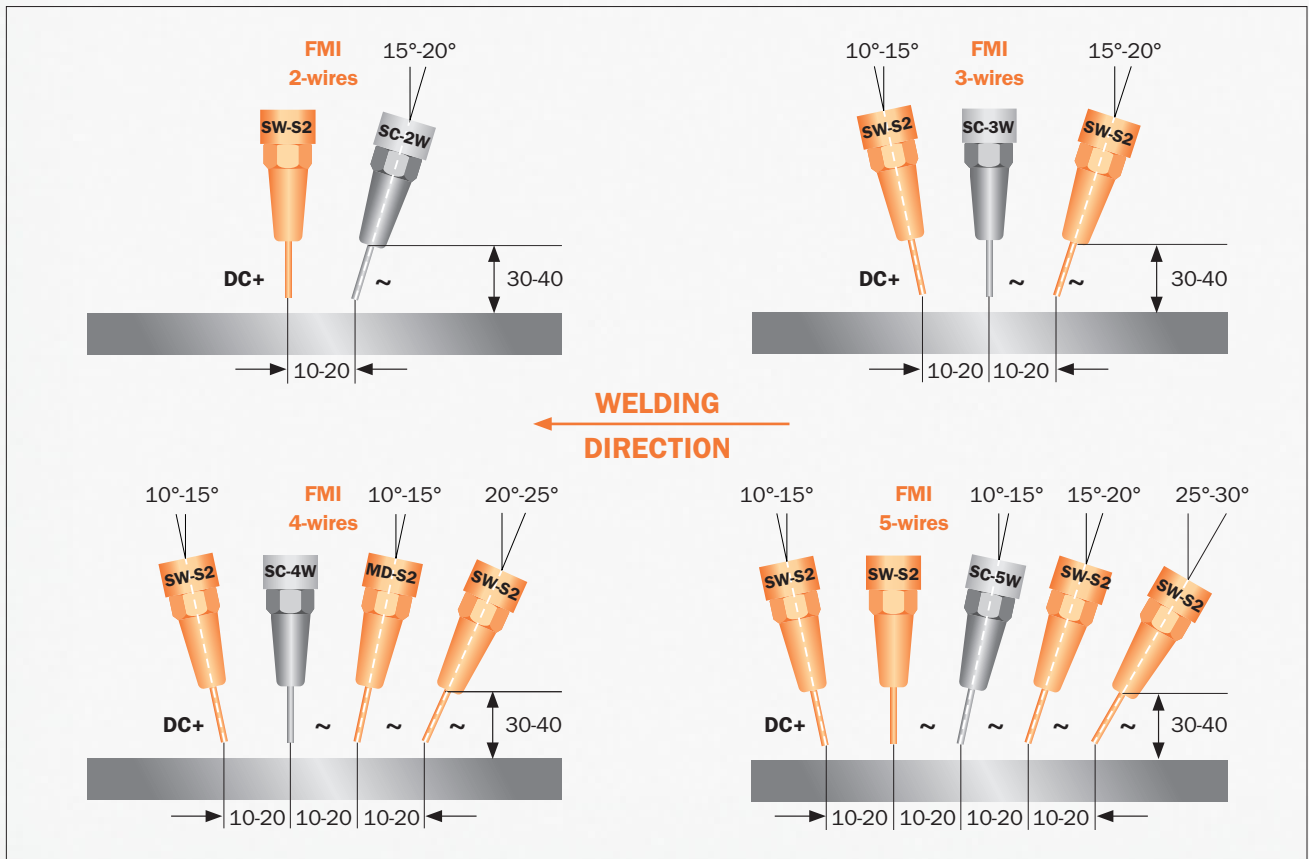


Position of wire electrodes and welding heads in the FMI-process. SW: solid wire. SC: SubCOR. Measures are in mm.

### Macro cross section, impact toughness values


CVN (J)	0°C	-20°C	-40°C	-60°C
1st layer (bottom)	156	132	75	52
2nd layer	165	153	126	88

Macro cross section of a two-run weld in 22 mm thick plate welded with a three-wire system: 2 x SDX S2Mo-EA2 and 1 x SubCOR 735 -3W. Travel speed 1st layer 90 cm/min (35"/min). Travel speed 2nd layer 130 cm/min (51"/min.). Impact toughness values are average of three.

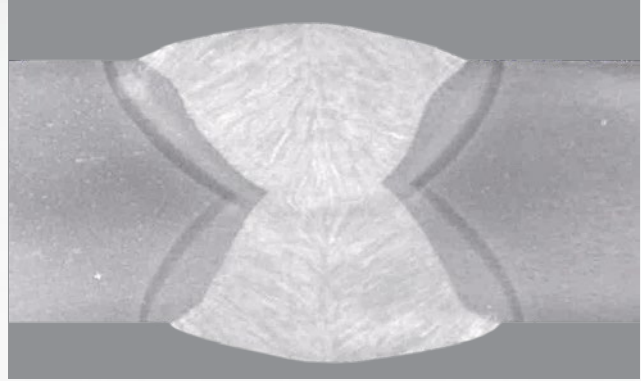

### FMI applied in the welding of X65 line pipe for sour gas service.

Flux cored micro injection has been successfully applied in the production of 685,000 tons of longitudinally welded large diameter line pipe for sour gas service. This involved material grade X65, in wall thicknesses of 19.05 and 25.4 mm. The CVN impact requirement was 85J at 0 °C. SubCOR SL 735 -4W was combined with three S2Mo wires in a four wire welding head. The table shows the welding parameters applied in the two-run technique for welding 25.4 mm (1") thick X65 grade pipe.

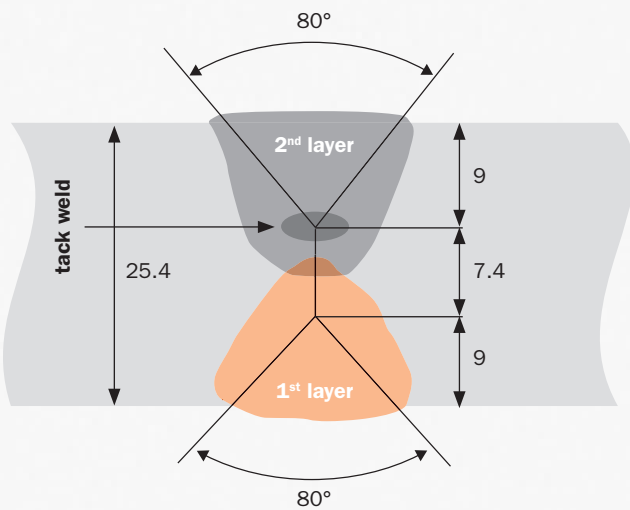


FMI process parameters for a sheet thickness of 25.4mm (1").

2 <sup>nd</sup> layer	All wires in Ø 4 mm	1 <sup>st</sup> head S2Mo	2 <sup>nd</sup> head 735 -4W	3 <sup>rd</sup> head S2Mo	4 <sup>th</sup> head S2Mo
Current [A]	1150	900	800	750	
Voltage [V]	35	38	38	40	
speed [cm/min]			155 (61"/min)		

1 <sup>st</sup> layer	All wires in Ø 4 mm	1 <sup>st</sup> head S2Mo	2 <sup>nd</sup> head 735 -4W	3 <sup>rd</sup> head S2Mo	4 <sup>th</sup> head S2Mo
Current [A]	850	750	650	600	
Voltage [V]	35	35	36	37	
speed [cm/min]			115 (45"/min)		


In total, 25 batches of SubCOR SL 735 -4W were manufactured for the production of 62,000 pipes. In addition to the approval welds, production tests were performed on original X65 for each batch under the same circumstances as in actual production. The diagram shows the statistic evaluation of the CVN impact toughness over 25 batches. The requirement of 85J at 0 °C (63 ft-lbf at 32 °F) is consistently met with a substantial safety margin for all areas of the weld, including heat

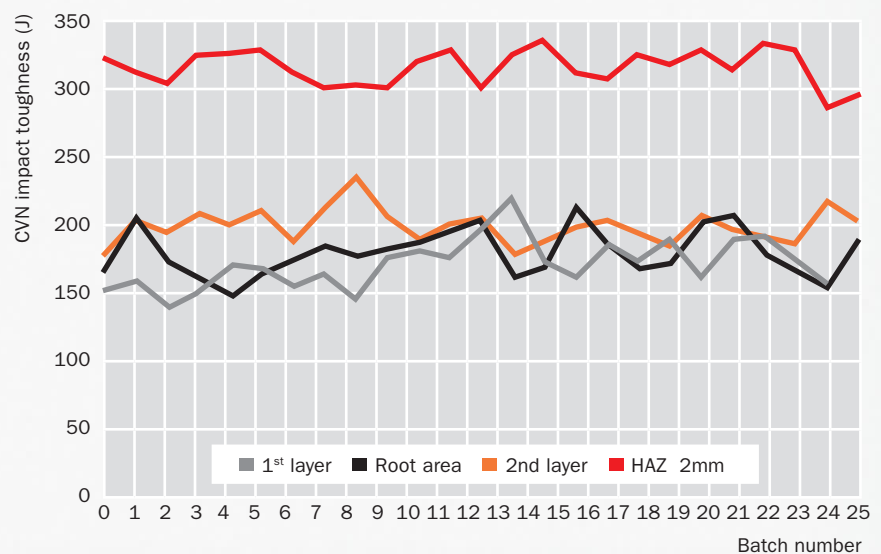

Statistic evaluation of CVN test results. Requirement: 85J at 0 °C (63 ft-lbf at 32 °F)

## EN 14174: Fluxes for submerged arc welding

Example:

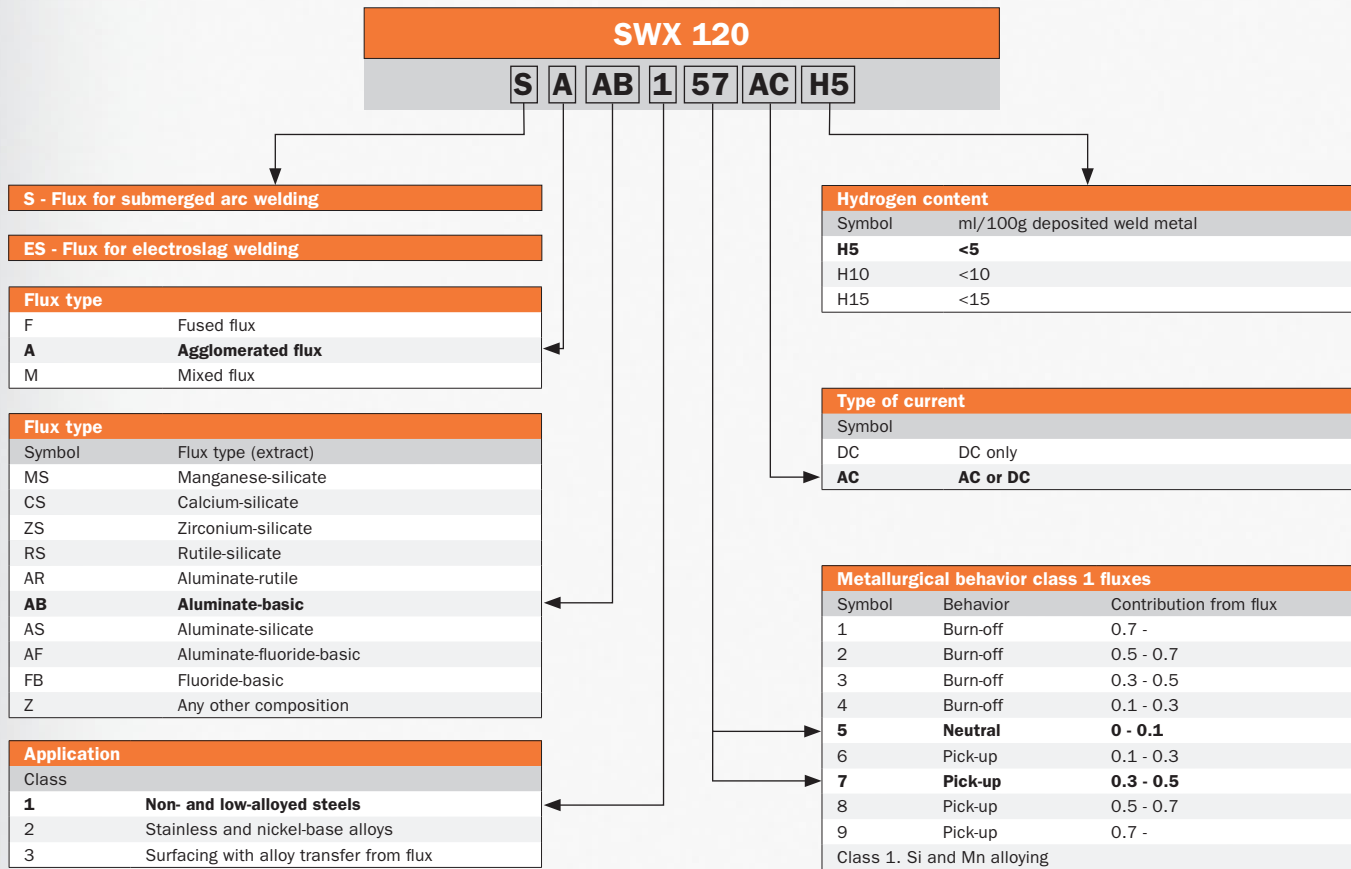

Metallurgical behavior class 2 fluxes (weight %)						
Symbol	Behavior	C	Si	Cr	Nb	
1	Burn-off	> 0.020	> 0.7	> 2.0	> 0.20	
2	Burn-off	-	0.5-0.7	1.5-2.0	0.15-0.20	
3	Burn-off	0.010-0.020	0.3-0.5	1.0-1.5	0.05-0.15	
4	Burn-off	-	0.1-0.3	0.5-1.0	0.05-0.10	
5	Neutral	0.000-0.010	0.0-0.1	0.0-0.5	0.00-0.05	
6	Pick-up	-	0.1-0.3	0.5-1.0	0.05-0.10	
7	Pick-up	0.010-0.020	0.3-0.5	1.0-1.5	0.10-0.15	
8	Pick-up	-	0.5-0.7	1.5-2.0	0.15-0.20	
9	Pick-up	>0.020	>0.7	>2.0	> 0.20	

Class 2 and 2B. Chemical symbols pick-up



**EN ISO 14171-A: Solid wires, cored wires and wire/flux combinations for submerged arc welding of non-alloyed and fine grain steels.**

Solid wire example:

**SWX 110 / SDX S2Si-EM12K**

**S 38 4 AB S2Si**

**S - Flux for SAW**

**Tensile properties**

Symbol	Rel/Rp0.2 min. (MPa)	Rm (MPa)	A min. (%)
35	355	440-570	22
<b>38</b>	<b>380</b>	<b>470-600</b>	<b>20</b>
42	420	500-640	20
46	460	530-680	20
50	500	560-720	18

**Min. tensile properties two-run technique**

Symbol	Parent material Rel/Rp0.2 (MPa)	Welded joint Rm (MPa)
2T	275	370
3T	355	470
4T	420	520
5T	500	500

**Diffusible hydrogen in weld metal (optional)**

Hydrogen content	
Symbol	ml/100g weld metal
H5	5
H10	10
H15	15

**Impact properties**

Symbol	Min. 47J at °C
Z	
A	+20
0	0
2	-20
3	-30
<b>4</b>	<b>-40</b>
5	-50
6	-60
7	-70
8	-80
9	-90
10	-100

**Flux type according to EN ISO 14174**

Symbol	Flux type (extract)
MS	Manganese-silicate
CS	Calcium-silicate
ZS	Zirconium-silicate
RS	Rutile-silicate
AR	Aluminate-rutile
<b>AB</b>	<b>Aluminate-basic</b>
AS	Aluminate-silicate
AF	Aluminate-fluoride-basic
FB	Fluoride-basic
Z	Any other composition

**EN ISO 14171: cored wire type and all weld metal chemical composition (%) \***

Symbol	Mn	Ni	Mo	Cu
T2	1.4			0.3
T3	1.4-2.0			0.3
T2Mo	1.4		0.3-0.6	0.3
T3Mo	1.4-2.0		0.3-0.6	0.3
T2Ni1	1.4	0.6-1.2		0.3
T2Ni1.5	1.6	1.2-1.8		0.3
T2Ni2	1.4	1.8-2.6		0.3
T2Ni3	1.4	2.6-3.8		0.3
T3Ni1	1.4-2.0	0.6-1.2		0.3
T2Ni1Mo	1.4	0.6-1.2	0.3-0.6	0.3
T2Ni1Cu	1.4	0.8-1.2		0.3-0.6

\* Single values are maximum.

**EN ISO 14171: chemical composition solid wire (%) \***

Symbol	C	Si	Mn	Mo	Ni	Cr	Cu**
S1	0.05-0.15	0.15	0.35-0.60	0.15	0.15	0.15	0.30
S2	0.07-0.15	0.15	0.80-1.30	0.15	0.15	0.15	0.30
S3	0.07-0.15	0.15	1.30-1.75	0.15	0.15	0.15	0.30
S4	0.07-0.15	0.15	1.75-2.25	0.15	0.15	0.15	0.30
S1Si	0.07-0.15	0.15-0.40	0.35-0.60	0.15	0.15	0.15	0.30
<b>S2Si</b>	<b>0.07-0.15</b>	<b>0.15-0.40</b>	<b>0.80-1.30</b>	<b>0.15</b>	<b>0.15</b>	<b>0.15</b>	<b>0.30</b>
S2Si2	0.07-0.15	0.40-0.60	0.80-1.30	0.15	0.15	0.15	0.30
S3Si	0.07-0.15	0.15-0.40	1.30-1.85	0.15	0.15	0.15	0.30
S4Si	0.07-0.15	0.15-0.40	1.85-2.25	0.15	0.15	0.15	0.30
S1Mo	0.05-0.15	0.05-0.25	0.35-0.60	0.45-0.65	0.15	0.15	0.30
S2Mo	0.07-0.15	0.05-0.25	0.80-1.30	0.45-0.65	0.15	0.15	0.30
S2MoTiB***	0.05-0.15	0.15-0.35	1.00-1.35	0.40-0.65			0.30
S3Mo	0.07-0.15	0.05-0.25	1.30-1.75	0.45-0.65	0.15	0.15	0.30
S4Mo	0.07-0.15	0.05-0.25	1.75-2.25	0.45-0.65	0.15	0.15	0.30
S2Ni1	0.07-0.15	0.05-0.25	0.80-1.30	0.15	0.80-1.20	0.15	0.30
S2Ni1.5	0.07-0.15	0.05-0.25	0.80-1.30	0.15	1.20-1.80	0.15	0.30
S2Ni2	0.07-0.15	0.05-0.25	0.80-1.30	0.15	1.80-2.40	0.15	0.30
S2Ni3	0.07-0.15	0.05-0.25	0.80-1.30	0.15	2.80-3.70	0.15	0.30
S2Ni1Mo	0.07-0.15	0.05-0.25	0.80-1.30	0.45-0.65	0.80-1.20	0.20	0.30
S3Ni1.5	0.07-0.15	0.05-0.25	1.30-1.70	0.15	1.20-1.80	0.20	0.30
S3Ni1Mo	0.07-0.15	0.05-0.25	1.30-1.80	0.45-0.65	0.80-1.20	0.20	0.30
S3Ni1Mo0.2	0.07-0.15	0.10-0.35	1.20-1.60	0.15-0.30	0.80-1.20	0.15	0.30
S3Ni1.5Mo	0.07-0.15	0.05-0.25	1.20-1.80	0.30-0.50	1.20-1.80	0.20	0.30
S2Ni1Cu	0.06-0.12	0.15-0.35	0.70-1.20	0.15	0.65-0.90	0.40	0.40-0.65
S3Ni1Cu	0.05-0.15	0.15-0.40	1.20-1.70	0.15	0.60-1.20	0.15	0.30-0.60
SZ	Any other agreed analysis						

\* Single values are maximum. \*\* Cu, including copper layer. Al < 0.030. \*\*\* Ti: 0.10-0.20

## SFA/AWS 5.17: Specification for carbon steel electrodes and fluxes for submerged arc welding

Cored wire example:

**SWX 150 / SubCOR SL 731**

**F 7 A 4 - EC1**

**F - Submerged arc welding flux**

### Tensile properties (multi-run)

	Tensile strength		Min. yield strength		Elongation
	psi	(MPa)	psi	(MPa)	%
6	60,000 - 80,000	(414 - 551)	48,000	(331)	22
<b>7</b>	<b>70,000 - 95,000</b>	<b>(483 - 655)</b>	<b>58,000</b>	<b>(400)</b>	<b>22</b>

### Heat treatment

<b>A</b>	<b>As welded</b>
P	Post weld heat treated (PWHT) 620°C / 1h

### Impact properties

	Temperature		Charpy-V impact min.	
	'F	(°C)	ft-lb	(J)
0	0	(-18)	20	(27)
2	-20	(-29)	20	(27)
<b>4</b>	<b>-40</b>	<b>(-40)</b>	<b>20</b>	<b>(27)</b>
5	-50	(-46)	20	(27)
6	-60	(-51)	20	(27)
8	-80	(-62)	20	(27)
Z	No requirements			

### Chemical composition for solid electrodes (%) (extract)

Classification	C	Mn	Si	S	P	Cu
EL8	0.10	0.25-0.60	0.07	0.030	0.030	0.35
EL8K	0.10	0.25-0.60	0.10-0.25	0.030	0.030	0.35
EL12	0.04 - 0.14	0.25 - 0.60	0.10	0.030	0.030	0.35
EM12	0.06 - 0.15	0.80 - 1.25	0.10	0.030	0.030	0.35
EM12K	0.05 - 0.15	0.80 - 1.25	0.10-0.35	0.030	0.030	0.35
EH12K	0.06 - 0.15	1.50 - 2.00	0.25-0.65	0.025	0.025	0.35
EH14	0.10 - 0.20	1.70 - 2.20	0.10	0.030	0.030	0.35

### Chemical composition for composite electrode weld metal (%)

Classification	C	Mn	Si	S	P	Cu
<b>EC1</b>	<b>0.15</b>	<b>1.80</b>	<b>0.90</b>	<b>0.35</b>	<b>0.035</b>	<b>0.35</b>
ECG	Not specified					
Single values are maximum						

# SFA/AWS 5.23: Specification for low-alloy steel electrodes and fluxes for submerged arc welding

Solid wire example:

**SWX 150 / SDX S2Ni2-ENi2**

**F 8 A 10 - ENi2 - Ni2**

## F - Submerged arc welding flux

### Tensile properties (multi-run)

	Tensile strength		Min. yield strength		Elongation
	psi	(MPa)	psi	(Mpa)	%
7	70,000 - 95,000	(483 - 655)	58,000	(400)	22
<b>8</b>	<b>80,000 - 100,000</b>	<b>(552 - 698)</b>	<b>68,000</b>	<b>(469)</b>	<b>20</b>
9	90,000 - 110,000	(621 - 758)	78,000	(538)	17
10	100,000 - 120,000	(689 - 827)	88,000	(607)	16
11	110,000 - 130,000	(758 - 896)	98,000	(676)	15
12	120,000 - 140,000	(827 - 965)	108,000	(745)	14
13	130,000 - 150,000	(896 - 1034)	118,000	(814)	14

### Heat treatment

<b>A</b>	<b>As welded</b>
<b>P</b>	Post weld heat treated (PWHT) depending on alloy

### Impact properties

	Temperature		Charpy-V impact min.	
	°F	(°C)	ft-lb	(J)
Z				
0	0	(-18)	20	(27)
2	-20	(-29)	20	(27)
4	-40	(-40)	20	(27)
5	-50	(-46)	20	(27)
6	-60	(-51)	20	(27)
8	-80	(-62)	20	(27)
<b>10</b>	<b>-100</b>	<b>(-73)</b>	<b>20</b>	<b>(27)</b>
15	-150	(-101)	20	(27)
Z	No requirements			

### Chemical composition for solid electrodes (%) \* (extract)

Classification	C	Mn	Si	S	P	Cr	Ni	Mo	Cu	Other
EA2	0.05 - 0.17	0.95 - 1.35	0.20	0.025	0.025			0.45 - 0.65	0.35	
EA3	0.05 - 0.17	1.65 - 2.20	0.20	0.025	0.025			0.45 - 0.65	0.35	
EA4	0.05 - 0.15	1.20 - 1.70	0.20	0.025	0.025			0.45 - 0.65	0.35	
EB2	0.07 - 0.15	0.45 - 1.00	0.05 - 0.30	0.025	0.025	1.00 - 1.75		0.45 - 0.65	0.35	
EB2R	0.07 - 0.15	0.45 - 1.00	0.05 - 0.30	0.010	0.010	1.00 - 1.75		0.45 - 0.65	0.15	As: 0.005 Sn: 0.005 Sb: 0.005
EB3	0.05 - 0.15	0.40 - 0.80	0.05 - 0.30	0.025	0.025	2.25 - 3.00		0.90 - 1.10	0.35	
EB3R	0.05 - 0.15	0.40 - 0.80	0.05 - 0.30	0.010	0.010	2.25 - 3.00		0.90 - 1.00	0.15	As: 0.005 Sn: 0.005 Sb: 0.005
EF2	0.10 - 0.18	1.70 - 2.40	0.20	0.025	0.025		0.40 - 0.80	0.40 - 0.65	0.35	
EF3	0.10 - 0.18	1.50 - 2.40	0.30	0.025	0.025		0.70 - 1.10	0.40 - 0.65	0.35	
EF5	0.10 - 0.17	1.70 - 2.20	0.20	0.015	0.010	0.25 - 0.50	2.30 - 2.80	0.45 - 0.65	0.50	
EM4	0.10	1.40 - 1.80	0.20 - 0.60	0.015	0.015	0.60	2.30 - 2.80	0.30 - 0.65	0.25	Ti: 0.10 Zr: 0.10 Al: 0.10
ENi1	0.12	0.75 - 1.25	0.05 - 0.30	0.020	0.020	0.15	0.75 - 1.25	0.30	0.35	
<b>ENi2</b>	<b>0.12</b>	<b>0.75 - 1.25</b>	<b>0.05 - 0.30</b>	<b>0.020</b>	<b>0.020</b>		<b>2.10 - 2.90</b>		<b>0.35</b>	
ENi5	0.12	1.20 - 1.60	0.05 - 0.30	0.020	0.020		0.75 - 1.25	0.10 - 0.30	0.35	
ENi3	0.13	0.60 - 1.20	0.05 - 0.30	0.020	0.020	0.15	3.10 - 3.80		0.35	
EG	Not specified									

\* Single values are maximum.

### Chemical composition of weld metal (%) \* (extract)

Classification	C	Mn	Si	S	P	Cr	Ni	Mo	Cu	Other
A2	0.12	1.40	0.80	0.030	0.030			0.40 - 0.65	0.35	
A3	0.15	2.10	0.80	0.030	0.030			0.40 - 0.65	0.35	
A4	0.15	1.60	0.80	0.030	0.030			0.40 - 0.65	0.35	
B2	0.05 - 0.15	1.20	0.80	0.030	0.030	1.00 - 1.50		0.40 - 0.65	0.35	
B2R	0.05 - 0.15	1.20	0.80	0.010	0.010	1.00 - 1.50		0.40 - 0.65	0.15	As: 0.005 Sn: 0.005 Sb: 0.005
B3	0.05 - 0.15	1.20	0.80	0.030	0.030	2.00 - 2.50		0.90 - 1.20	0.35	
B3R	0.05 - 0.15	1.20	0.80	0.010	0.010	2.00 - 2.50		0.90 - 1.20	0.15	As: 0.005 Sn: 0.005 Sb: 0.005
F2	0.17	1.25 - 2.25	0.80	0.030	0.030		0.40 - 0.80	0.40 - 0.65	0.35	
F3	0.17	1.25 - 2.25	0.80	0.030	0.030		0.70 - 1.10	0.40 - 0.65	0.35	
F5	0.17	1.20 - 1.80	0.80	0.020	0.020	0.65	2.00 - 2.80	0.30 - 0.80	0.50	
M4	0.10	1.30 - 2.25	0.80	0.020	0.020	0.80	2.00 - 2.80	0.30 - 0.80	0.30	Ti+V+Zr: 0.03
Ni1	0.12	1.60	0.80	0.025	0.030	0.15	0.75 - 1.10	0.35	0.35	Ti+V+Zr: 0.05
<b>Ni2</b>	<b>0.12</b>	<b>1.60</b>	<b>0.80</b>	<b>0.025</b>	<b>0.030</b>		<b>2.00 - 2.90</b>		<b>0.35</b>	
Ni5	0.12	1.60	0.80	0.025	0.030		0.70 - 1.10	0.10 - 0.30	0.35	
Ni3	0.12	1.60	0.80	0.025	0.030	0.15	2.80 - 3.80		0.35	
EG	Not specified									
EC	Composite electrode									

\* Single values are maximum.

# EN ISO 24598-A: Solid wire electrodes, tubular cored electrodes and electrode-flux combinations for submerged arc welding of creep resisting steels

Solid wire example:

**SWX 150 / SDX CrMo1-EB2R**

**S S CrMo1 FB**

**S - Submerged arc welding process**

**S - Solid wire**

**T - Cored wire**

## Mechanical properties all weld metal flux / (cored) wire combinations

Symbol	min. yield strength	Tensile strength	Elongation	CVN impact toughness at +20°C		Heat treatment		
	MPa	MPa	%	Average of 3 min.	Min. single value	Preheat and interpass temperature °C	Post weld heat treatment °C	Time min.
Mo / MnMo	355	510	22	47	38	<200		
MoV	355	510	18	47	38	200-300	690-730	60
<b>CrMo1</b>	<b>355</b>	<b>510</b>	<b>20</b>	<b>47</b>	<b>38</b>	<b>150-250</b>	<b>660-700</b>	<b>60</b>
CrMoV1	435	590	15	24	21	200-300	680-730	60
CrMo2/CrMo2Mn	400	500	18	47	38	200-300	690-750	60
CrMo2L	400	500	18	47	38	200-300	690-750	60
CrMo5	400	590	17	47	38	200-300	730-760	60
CrMo9	435	590	18	34	27	200-300	740-780	120
CrMo91	415	585	17	47	38	250-350	750-760	180
CrMoWV12	550	690	15	34	27	250-350 or 400-500	740-780	120

## Chemical composition all weld metal for flux / (cored) wire combinations

Symbol	C	Si	Mn	P	S	Cr	Ni	Mo	Cu	V	Other
Mo	0.15	0.80	1.4	0.030	0.030	0.2	0.3	0.40 - 0.65	0.35	0.03	Nb: 0.01
MnMo	0.15	0.80	2.0	0.030	0.030	0.2	0.3	0.40 - 0.65	0.35	0.03	Nb: 0.01
MoV	0.15	0.80	1.4	0.030	0.030	0.20 - 0.60	0.3	0.45 - 1.00	0.35	0.20 - 0.45	Nb: 0.01
<b>CrMo1</b>	<b>0.15</b>	<b>0.80</b>	<b>1.20</b>	<b>0.030</b>	<b>0.030</b>	<b>0.80 - 1.30</b>	<b>0.25</b>	<b>0.35 - 0.65</b>	<b>0.40</b>	<b>0.03</b>	<b>Nb: 0.01</b>
CrMoV1	0.15	0.80	1.40	0.030	0.030	0.80 - 1.30	0.3	0.80 - 1.30	0.35	0.10 - 0.35	Nb: 0.01
CrMo2	0.15	0.80	1.20	0.030	0.030	2.0 - 2.8	0.3	0.80 - 1.50	0.35	0.03	Nb: 0.01
CrMo2Mn	0.10	0.80	1.40	0.030	0.020	1.8 - 2.5	0.3	0.80 - 1.20	0.35	0.03	Nb: 0.01
CrMo2L	0.05	0.80	1.20	0.030	0.030	2.0 - 2.8	0.3	0.80 - 1.15	0.35	0.03	Nb: 0.01
CrMo5	0.10	0.80	1.20	0.030	0.030	4.50 - 6.50	0.3	0.45 - 0.80	0.35	0.03	Nb: 0.01
CrMo9	0.10	0.80	1.20	0.030	0.030	8.0 - 10.0	1.0	0.70 - 1.20	0.35	0.15	Nb: 0.01
CrMo91	0.15	0.80	1.80	0.030	0.030	8.0 - 10.5	1.0	0.70 - 1.20	0.35	0.10 - 0.30	Nb: 0.02 - 0.10
CrMoWV12	0.24	0.80	1.4	0.030	0.030	9.5 - 12.0	0.80	0.70 - 1.20	0.35	0.15 - 0.40	Nb: 0.01

Z Any other agreed composition

\* Single values are maximum.

## Flux type according to EN ISO 14174

Symbol	Flux type
MS	Manganese-silicate
CS	Calcium-silicate
ZS	Zirconium-silicate
RS	Rutile-silicate
AR	Aluminate-rutile
AB	Aluminate-basic
AS	Aluminate-silicate
AF	Aluminate-fluoride-basic
<b>FB</b>	<b>Fluoride-basic</b>
Z	Any other composition

**ISO 26304-A: Solid wire electrodes, tubular cored electrodes and electrode-flux combinations for submerged arc welding of high strength steels**

Cored wire example:

**SWX 150 / SubCOR SL 742**

**S 69 6 FB T3 Ni2.5CrMo**

**S - Submerged arc welding**

**Tensile properties**

Symbol	Rel/Rp0.2 min. MPa	Rm MPa	A min. %
55	550	640-820	18
62	620	700-890	18
<b>69</b>	<b>690</b>	<b>770-940</b>	<b>17</b>
79	790	880-1080	16
89	890	940-1180	15

**Impact properties**

Symbol	Min. 47J at °C
Z	No requirement
A	+20
0	0
2	-20
3	-30
4	-40
5	-50
<b>6</b>	<b>-60</b>

**Flux type according to EN ISO 14174**

Symbol	Flux type
MS	Manganese-silicate
CS	Calcium-silicate
ZS	Zirconium-silicate
RS	Rutile-silicate
AR	Aluminate-rutile
AB	Aluminate-basic
AS	Aluminate-silicate
AF	Aluminate-fluoride-basic
<b>FB</b>	<b>Fluoride-basic</b>
Z	Any other composition

**Diffusible hydrogen in weld metal (optional)**

Hydrogen content

Symbol	ml/100g weld metal
H5	5
H10	10
H15	15

**Chemical composition wire (%) \***

Symbol	C	Si	Mn	P	S	Cr	Ni	Mo	Cu	Other
S2Ni1Mo	0.07 - 0.15	0.05 - 0.25	0.80 - 1.30	0.020	0.020	0.20	0.80 - 1.20	0.45 - 0.65	0.30	
S3Ni1Mo	0.07 - 0.15	0.05 - 0.35	1.30 - 1.80	0.020	0.020	0.20	0.80 - 1.20	0.45 - 0.65	0.30	0.50
S3Ni1.5Mo	0.07 - 0.15	0.05 - 0.25	1.20 - 1.80	0.020	0.020	0.20	1.20 - 1.80	0.30 - 0.50	0.30	0.50
S2Ni2Mo	0.05 - 0.09	0.15	1.10 - 1.40	0.015	0.015	0.15	2.00 - 2.50	0.45 - 0.60	0.30	0.50
S2Ni3Mo	0.08 - 0.12	0.10 - 0.25	0.80 - 1.20	0.020	0.020	0.15	2.80 - 3.20	0.10 - 0.25	0.30	0.50
S3Ni1.5CrMo	0.07 - 0.14	0.05 - 0.15	1.30 - 1.50	0.020	0.020	0.15 - 0.35	1.50 - 1.70	0.30 - 0.50	0.30	0.50
S3Ni2.5CrMo	0.07 - 0.15	0.10 - 0.25	1.20 - 1.80	0.020	0.020	0.30 - 0.85	2.00 - 2.60	0.40 - 0.70	0.30	0.50
S1Ni2.5CrMo	0.07 - 0.15	0.10 - 0.25	0.45 - 0.75	0.020	0.020	0.50 - 0.85	2.10 - 2.60	0.40 - 0.70	0.30	0.50
S4Ni2CrMo	0.08 - 0.11	0.30 - 0.40	1.80 - 2.00	0.015	0.15	0.85 - 1.00	2.10 - 2.60	0.55 - 0.70	0.30	0.50
TZ	Any other agreed analyses									

\* Single values are maximum.

**All weld metal chemical composition flux / cored wire combination (%) \***

Symbol	C	Si	Mn	P	S	Cr	Ni	Mo	V
T3NiMo	0.05 - 0.12	0.20 - 0.60	1.30 - 1.90	0.02	0.02		0.60 - 1.00	0.15 - 0.45	
T3Ni1Mo	0.03 - 0.09	0.10 - 0.50	1.39 - 1.80	0.02	0.02		1.00 - 1.50	0.45 - 0.65	
T3Ni2MoV	0.03 - 0.09	0.20	1.20 - 1.70	0.02	0.02		1.60 - 2.00	0.20 - 0.50	0.05 - 0.15
T3Ni2Mo	0.03 - 0.09	0.40 - 0.80	1.30 - 1.80	0.02	0.02		1.80 - 2.40	0.20 - 0.40	
T3Ni3Mo	0.03 - 0.09	0.20 - 0.70	1.60 - 2.10	0.02	0.02		2.70 - 3.20	0.20 - 0.40	
<b>T3Ni2.5CrMo</b>	<b>0.03 - 0.09</b>	<b>0.10 - 0.50</b>	<b>1.20 - 1.70</b>	<b>0.02</b>	<b>0.02</b>	<b>0.40 - 0.70</b>	<b>2.20 - 2.60</b>	<b>0.30 - 0.60</b>	
T3Ni2.5Cr1Mo	0.04 - 0.10	0.20 - 0.70	1.20 - 1.70	0.02	0.02	0.70 - 1.20	2.20 - 2.60	0.40 - 0.70	
TZ	Any other agreed analyses								

\* Single values are maximum.

# EN ISO 14343-A: Welding consumables - Wire electrodes, strip electrodes, wires and rods for arc welding of stainless and heat resisting steels - Classification according to nominal composition

Solid wire example:

**SWX 220 / SDX 309LMo**

**S 23 12 2 L**

## Symbol for the arc welding process

G	Gas metal arc welding
W	Gas tungsten arc welding
P	Plasma welding
<b>S</b>	<b>Submerged arc welding</b> or electroslag strip cladding
L	Laser beam welding

Extract	Chemical composition (%)											
Austenitic types	C	Si	Mn	P	S	Cr	Ni	Mo	N	Cu	Nb	Others
19 9 L (308L)	0.03	0.65	0.8	0.03	0.02	19.0-21.0	9.0-11.0	0.5		0.5		
23 12 L (309L)	0.03	0.65	1.0-2.5	0.03	0.02	22.0-25.0	11.0-14.0	0.5		0.5		
<b>23 12 2 L (309LMo)</b>	<b>0.03</b>	<b>1.0</b>	<b>1.0-2.5</b>	<b>0.03</b>	<b>0.02</b>	<b>21.0-25.0</b>	<b>11.0-15.5</b>	<b>2.0-3.5</b>		<b>0.5</b>		
19 12 3 L (316L)	0.03	0.65	1.0-2.5	0.03	0.02	18.0-20.0	11.0-14.0	2.5-3.0		0.5		
19 13 4 L (317L)	0.03	1.0	1.0-1.5	0.03	0.02	17.0-20.0	12.0-15.0	3.0-4.5		0.5		
19 9 Nb (347)	0.08	0.65	1.0-2.5	0.03	0.02	19.0-21.0	9.0-11.0	0.5		0.5	10xC-1.0	
Austenitic ferritic types												
22 9 3 N L (2209)	0.03	1.0	2.5	0.03	0.02	21.0-24.0	7.0-10.0	2.5-4.0	0.10-0.20	0.5		
25 9 4 N L (2594)	0.03	1.0	2.5	0.03	0.02	24.0-27.0	8.0-10.5	2.5-4.5	0.20-0.30	1.5		W: 1.0

Single values are maximum

## SFA / AWS A5.9: Bare stainless steel welding electrodes and rods (extract)

Example:

**SDX 316L**

**ER 316L**

**ER - Solid wire**


Chemical composition wire												
AWS	C	Si	Mn	P	S	Cr	Ni	Mo	N	CU	Others	
ER308L	0.03	0.30 - 0.65	1.0 - 2.5	0.03	0.03	19.5 - 22.0	9.0 - 11.0	0.75		0.75		
ER308H	0.04 - 0.08	0.30 - 0.65	1.0 - 2.5	0.03	0.03	19.5 - 22.0	9.0 - 11.0	0.50		0.75		
ER309L	0.03	0.30 - 0.65	1.0 - 2.5	0.03	0.03	23.0 - 25.0	12.0 - 14.0	0.75		0.75		
ER309LMo	0.03	0.30 - 0.65	1.0 - 2.5	0.03	0.03	23.0 - 25.0	12.0 - 14.0	2.0 - 3.0		0.75		
ER310	0.08 - 0.15	0.30 - 0.65	1.0 - 2.5	0.03	0.03	25.0 - 28.0	20.0 - 22.5	0.75		0.75		
<b>ER316L</b>	<b>0.03</b>	<b>0.30 - 0.65</b>	<b>1.0 - 2.5</b>	<b>0.03</b>	<b>0.03</b>	<b>18.0 - 20.0</b>	<b>11.0 - 14.0</b>	<b>2.0 - 3.0</b>		<b>0.75</b>		
ER317L	0.03	0.30 - 0.65	1.0 - 2.5	0.03	0.03	18.5 - 20.5	13.0 - 15.0	3.0 - 4.0		0.75		
ER347	0.08	0.30 - 0.65	1.0 - 2.5	0.03	0.03	19.0 - 21.5	9.0 - 11.0	0.75		0.75	Nb=10xCmin/1.0max	
ER2209	0.03	0.90	0.50 - 2.0	0.03	0.03	21.5 - 23.5	7.5 - 9.5	2.5 - 3.5	0.08 - 0.20	0.75		



# Submerged Arc Welding Process

## From fundamentals to the latest technology

In submerged arc welding, the arc is “submerged” in flux and is not visible when parameters are correctly set and the layer of flux is sufficiently thick. The wire is automatically fed through a welding head that moves along the weld joint. The arc heat melts a portion of wire, flux and parent metal to form a molten weld pool. In this area all important functions of the flux - such as degassing, deoxidizing and alloying - take place. Behind the arc, molten flux and metal freeze to form a slag-covered weld bead.

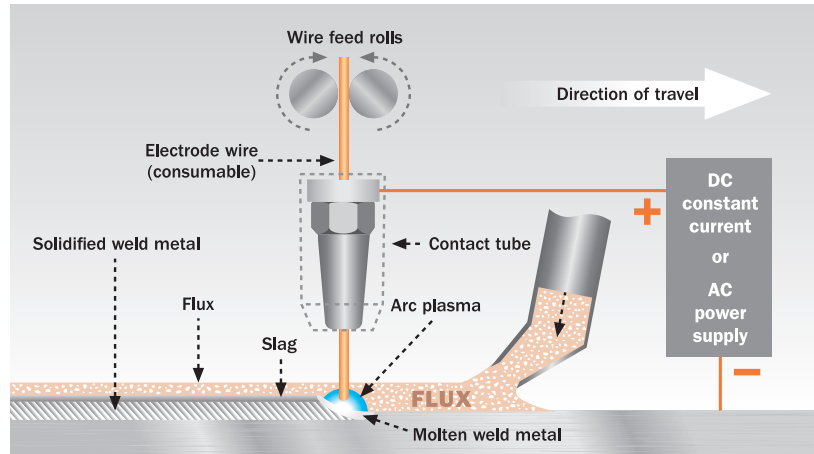

Single wire submerged arc welding

When the welding process is correctly set the slag should come off without any particular effort. The process is normally mechanized or automated. Key components of the process welding head, flux feeding and recovery system, wire spool, wire feeders and control unit are mounted on a carrier such as a tractor or column and boom. Power sources are usually positioned anywhere near the carrier, along with bulk wire supply.

1. Power source
2. Welding head
3. Flux hopper
4. Control unit
5. Wire spool
6. Carrier
7. Manipulator

ITW Welding as First Tier Member, has installed an advanced Miller SAW and ESC welding and strip cladding system at the Nuclear AMRC (Nuclear Advanced Manufacturing Research Centre) in the UK. The equipment has enabled both organisations to carry out research and development work in advancing the SAW process for nuclear, renewable energy and oil and gas related projects.



# Submerged Arc Welding Process

## Pros and cons of the process

Submerged arc welding has a number of distinct advantages in terms of welding economy and weld quality, but also some limitations compared with other arc welding processes.

### Advantages:

- Clean automatic process without UV radiation and spatter and minimal fume.
- Superior deposition rates of up to 100 kg/h (220 lbs/h) in multiple-wire welding.
- Very high travel speeds of up to 250 cm/min (100"/min).
- From a few millimetres to unlimited plate thickness.
- Excellent mechanical properties and X-ray quality welds.
- No spatter - high weld metal recovery.
- Reliable process with secure weld penetration and reduced risk of lack of fusion.
- Weld metal chemical composition and mechanical properties can be controlled via the flux/wire combination.

### Limitations:

- Capital investment.
- Only suited for flat and horizontal fillet positions (PA/1G, PB/2F). PC/2G possible with flux support.
- Requires first class joint preparation.
- Requires precise parameter setting and positioning of the wire electrode.
- Adjustments not easily determined because of the invisible arc.
- Requires disposal of the slag.


## Welding flux - A critical process component

In submerged arc welding, the flux performs a number of essential functions, enabling a stable arc at the high welding currents characteristic for this productive process:

- Creation of a slag that forms a cavity for the arc to establish in.
- Improvement of arc conductivity and droplet transfer.
- Shielding droplets, weld pool and solidifying weld from the surrounding air.
- Deoxidization of the weld metal and removal of impurities.
- Supports deep penetration by preventing heat to escape.
- Meets different chemical and mechanical weld requirements, depending on the wire electrode.

### To enhance the submerged arc welding process the flux must:

- have the right particle mix to allow degassing and facilitate high welding currents.
- have the right slag properties to allow high travel speeds.
- create a slag that releases easily.
- provide the lowest possible flux consumption.
- have good grain strength to limit the forming of dust in recycling.

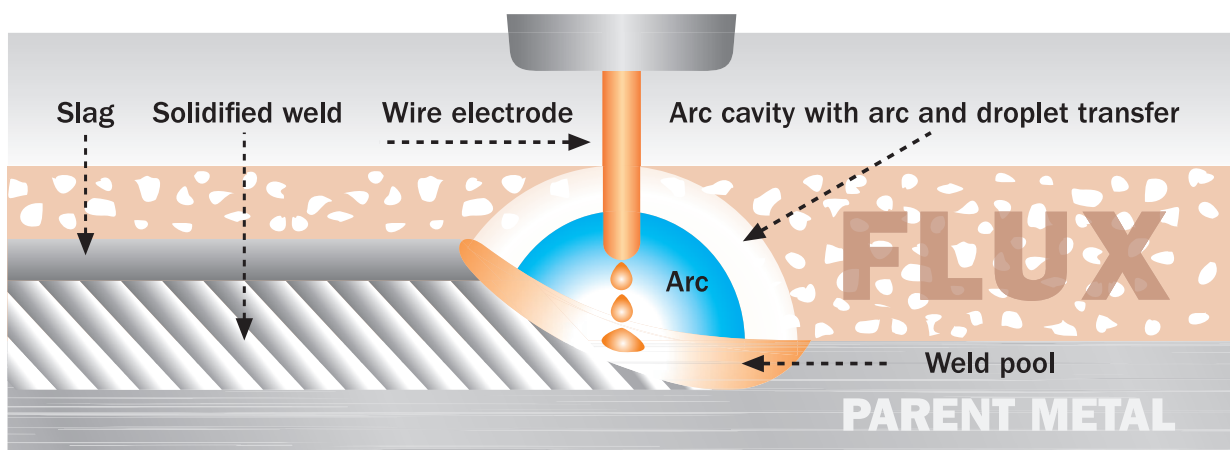

## Submerged arc welding fluxes and manufacturing methods

There are basically two types of welding fluxes characterized by their manufacturing method; agglomerated and fused.

Fused fluxes have long been used universally in submerged arc welding, but have widely been replaced by agglomerated fluxes – even in countries with a tradition in the use of fused fluxes.

In the production of agglomerated fluxes, powder raw materials with specified grain size are mixed with a bonding agent to form chemically homogeneous grains. Subsequently, the flux is baked at high temperature to remove moisture and sieved to the desired grain size distribution. Agglomerated fluxes provide the following advantages compared to fused fluxes to the submerged arc welding process:

- The lower temperature in the manufacturing process allows addition of a higher level of deoxidizers and alloying elements. This results in cleaner welds with significantly improved mechanical properties; most notably with better low-temperature impact toughness.
- In the vast majority of applications agglomerated fluxes allow higher travelling speed, typically meaning lower manufacturing costs.
- Agglomerated fluxes are available for all steel grades and applications.
- Lower flux consumption due to lower arc voltage.

### Hydrogen classes

The hydrogen class of a flux, as manufactured, is embedded in the classification according to EN ISO 14174, AWS A5.17 and AWS A5.23.

EN ISO 14174: e.g. S A AB 1 67 AC **H5**. H5 indicates that the flux is capable of producing a weld metal with less than 5 ml diffusible hydrogen per 100 g weld metal.

AWS A5.17: e.g. F7A4-EM12K-**H4**. H4 indicates that the flux is capable of producing a weld metal with less than 4 ml diffusible hydrogen per 100 g weld metal.

Hydrogen class		ml/100 g deposited weld metal
EN ISO 14174	AWS A5.17 and AWS A5.23	
	H2	<2
	H4	<4
H5		<5
	H8	<8
H10		<10
H15		<15
	H16	<16

## Hobart fluxes and packaging

The Hobart welding fluxes reviewed in this catalogue are all agglomerated, low-hydrogen types. The various SWX fluxes, in combination with the appropriate SDX or SubCOR wire electrode, cover a wide range of grades within normal strength, high strength, low-temperature, creep resistant and stainless steel, as well as nickel base alloys. They feature extremely low moisture contents and are all supplied standard in moisture proof EAE (Excess Air Evacuation) bags or DoubleBag bulk packaging, both giving maximum security against moisture absorption and hydrogen cracking.

### Flux types and standards

Submerged arc welding fluxes and flux/wire combinations are named, standardized and categorized in various European/international (EN ISO) and United States (AWS) standards. The standards referred to in this catalogue are:

- **EN ISO 14171:**  
Solid wire electrodes, tubular cored electrodes and electrode/flux combinations for submerged arc welding of non-alloy and fine grain steels.
- **EN ISO 14174:**  
Fluxes for submerged arc welding.
- **EN ISO 24598:**  
Solid wire electrodes, tubular cored electrodes and electrode-flux combinations for submerged arc welding of creep resisting steels.

>>

# Submerged Arc Welding Process

- **EN ISO 26304:**  
Solid wire electrodes, tubular cored electrodes and electrode-flux combinations for submerged arc welding of high strength steels.
- **EN ISO 14343:**  
Wire electrodes, strip electrodes, wires and rods for arc welding of stainless and heat resisting steels.
- **SFA/AWS 5.17:**  
Specification for carbon steel electrodes and fluxes for submerged arc welding.
- **SFA/AWS 5.23:**  
Specification for low-alloy steel electrodes and fluxes for submerged arc welding.
- **SFA/AWS A5.9:**  
Bare stainless steel welding electrodes and rods.

Fluxes are categorized in different ways. Agglomerated versus fused fluxes is one of them, but within these categories there is a variety of flux compositions possible. A refined method is given in the EN ISO 14174 flux classification standard where fluxes are marked with a symbol for their main chemical constituents, for example: S A **AB** 1 67 AC H5

Here **AB** signifies that it is an aluminate-basic flux. The most frequently used symbols are given in the following table together with their main chemical constituents. All relevant EN ISO standards use these symbols to typify the flux within classifications of flux/wire combinations. All relevant classification standards are explained in detail elsewhere in this catalogue.

Symbol	Flux type	Characteristic chemical constituents	% of total flux
FB	Fluoride-basic	CaO+MgO+CaF <sub>2</sub> +MnO	>50
		SiO <sub>2</sub>	<20
		CaF <sub>2</sub>	>15
AF	Aluminate-fluoride-basic	Al <sub>2</sub> O <sub>3</sub> + CaF <sub>2</sub>	>70
AB	Aluminate-basic	Al <sub>2</sub> O <sub>3</sub> + CaO + MgO	>40
		Al <sub>2</sub> O <sub>3</sub>	>20
		CaF <sub>2</sub>	<22
AR	Aluminate-rutile	Al <sub>2</sub> O <sub>3</sub> + TiO <sub>2</sub>	>40

## Flux basicity index (BI)

Basicity is commonly used to describe the relation between basic flux ingredients and acidic flux ingredients.

$$BI = \frac{\% \text{ basic oxides}}{\% \text{ acidic oxides}}$$

The most commonly applied method to calculate the basicity index is according to Boniszewski's formula:


$$BI = \frac{CaO + MgO + SrO + BaO + Li_2O + Na_2O + K_2O + CaF_2 + 0.5 (FeO + MnO)}{SiO_2 + 0.5 (Al_2O_3 + TiO_2 + ZrO_2)}$$

A high basicity index leads to lower oxygen levels and thereby to fewer micro inclusions in the weld metal, which is beneficial for the microstructure and improves impact toughness. However, a higher basicity generally gives a slag with lower viscosity and hence a lower current carrying capacity of the flux, leading to lower productivity. It is recommended to look for the lowest possible basicity flux in order to achieve the required impact toughness.

Basicity index	Type of flux	Weld metal O content (wt.-%)
BI < 0.9	Low basicity flux	> 700 ppm
BI 0.9-1.2	Neutral basicity flux	500 – 700 ppm
BI 1.2-2.5	Basic flux	350 – 500 ppm
BI >2.5	High basic flux	<350 ppm

## Hobart fluxes basicity vs. CVN impact toughness

The diagram below gives a schematic view of the relationship between basicity index of the flux and impact toughness with a given wire. It is also indicated where Hobart fluxes are positioned according to their basicity index.

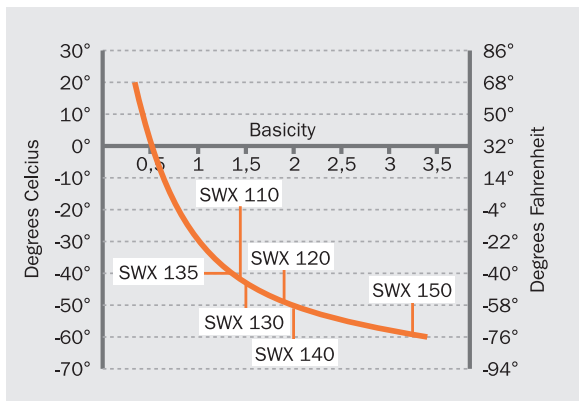

Basicity index vs 47J impact toughness

## Alloying behavior

EN ISO 14174 classifies the flux according to its pick up behaviour of Si and pick up /burn off behavior of Mn according to the table below.

Metallurgical behavior class 1 fluxes		
Symbol	Behavior	Contribution from flux
1	Burn-off	0.7 -
2	Burn-off	0.5 - 0.7
3	Burn-off	0.3 - 0.5
4	Burn-off	0.1 - 0.3
<b>5</b>	<b>Neutral</b>	<b>0 - 0.1</b>
6	Pick-up	0.1 - 0.3
7	Pick-up	0.3 - 0.5
8	Pick-up	0.5 - 0.7
9	Pick-up	0.7 -
Class 1. Si and Mn alloying		

Si and Mn alloying effects according to EN ISO 14174 determined using S2 wire and welded at standardized parameters of 580 A/29 V/ 55 cm/min.

In the EN ISO 14174 designation S A AB 1 **57** AC H5 the number **57** indicates that this flux is not adding any Si but adds 0.3-0.5 % of Mn under the given circumstances. Si acts as a deoxidizer and makes the weld pool more fluid, while Mn increases weld metal strength and impact toughness.

The higher the number for metallurgical behavior is, the more Si and/or Mn is alloyed through the flux. A high alloying flux can be beneficial for welding and / or mechanical properties especially in high dilution applications. However, it must be used with caution in multi-run welds and when using high Si and/or Mn alloyed wires, due to the risk of excessive alloy build up in the weld metal that can lead to deteriorated mechanical properties and an increased risk of cracks. The high alloying fluxes are also sensitive to welding parameters as the alloying increases with increasing arc voltage.

AWS A5.23 gives an indication of the metallurgical behaviour of the flux in the second and third part of the flux-wire designation. F8A2-**EA2** (wire classification)-**A4** (weld metal classification).

AWS also has another way to classify the chemical interaction of the flux and that is the Wall Neutrality Number (N). N is measured by making one weld pad using a specified set of parameters. Then another weld pad is made using the same set of parameters except for arc voltage, which is increased by 8 V. The Mn and Si content of the two weld pads are analyzed and the Wall Neutrality Number is then calculated according to the formula below.

$$N = 100 \times (|\Delta \text{Mn}| + |\Delta \text{Si}|)$$


A flux is considered neutral when having a Wall Neutrality Number of 35 or lower.



# Submerged Arc Welding Process

## Hobart metallurgical behavior diagrams

For each flux Hobart gives the appropriate classification according to EN ISO 14174 with the two digit identification of metallurgical behaviour. In addition, diagrams are provided to show the typical weld metal analyses in relation to the wire analyses for silicon and manganese. Values are determined at both 500 and 800 A to provide guidance.

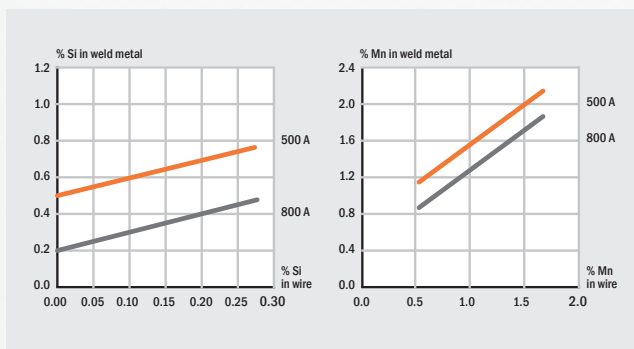

Metallurgical behavior diagram for flux SWX 110, a slightly Si and Mn alloying flux.

## Alloying fluxes

Alloying fluxes add chromium, nickel and/or molybdenum to obtain a specific high alloy weld metal composition when using lower alloyed wires or strips.

Voltage control is important, as it has an influence on the amount of flux taking part in the chemical reaction. Alloying fluxes are mostly applied in stainless and high alloy cladding applications.

## Grain size

Flux grain size is important because it influences current carrying capacity and flux feeding and recovery:

- A correct grain size allows gases to escape from the molten weld pool.
- Grain size determines the current carrying capacity of the flux. Coarser particle size is needed for higher currents.
- For high travel speeds in thin materials a fine-grained flux is preferred.
- Fluxes with excessive high amounts of fine particles could segregate in flux feeding and recovery systems.

Grain size is commonly expressed by a minimum and maximum particle size. The grain size can be expressed either in mm (size of the openings in the sieve cloth in mm) or in mesh (the number of openings/inch in the sieve cloth)


A grain size of 0.2-1.6 mm means that the grains of the flux are larger than 0.2 mm (~65 mesh) and smaller than 1.6 mm (~12 mesh).

A grain size of 12-65 mesh means that the grains of the flux are smaller than 12 mesh (~1.6 mm) and larger than 65 mesh (~0.2 mm).

Hobart states grain size in both millimeters and mesh in product data.

## Submerged arc welding process options


Submerged arc welding even in its simplest form is already a highly productive process. Deposition rates in single wire welding, the most widely applied method, can amount to 12 lbs/h when applications allow the use of large diameter wires at high welding currents. A variety of process options has evolved over the years with the objective to further increase the welding productivity; often developed to meet the challenges of specific industries. The following process options are observed in today's submerged arc welding.

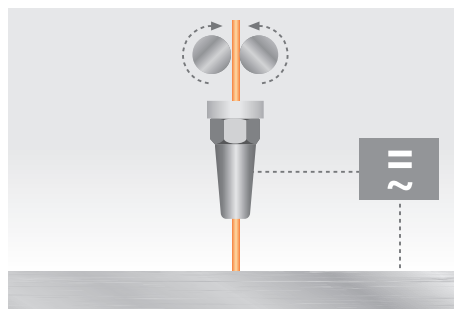

### Single wire SAW

- One wire, one feeder, one welding head
- One power source, one control unit
- Wire diameter 1.6-5.0 mm (1/16" - 3/16")
- Welding current 200-1000 A
- Generally applied across industries


**Deposition rate up to 12 kg/h (26 lbs/h)**

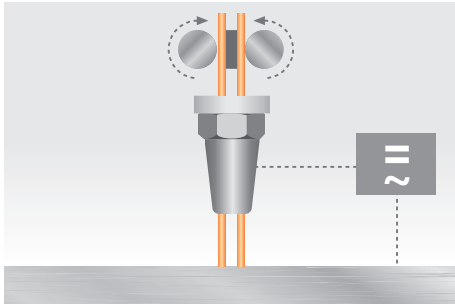

### Twin wire SAW

- Two wires, one 2-rolls wire feeder, one 2-wire contact nozzle
- One power source, one control unit
- Wire diameter 1.2-3.2 mm (0.045"-1/8")
- Total welding current 400-1200 A
- Generally applied across industries
- Moderate investment to upgrade from single wire SAW


**Deposition rate up to 20 kg/h (44 lbs/h)**

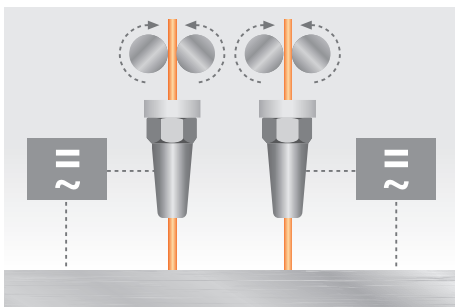

### Tandem wire SAW

- Two wires, two feeders, two welding torches
- Two power sources, two control units
- Wire diameter 3.2-5.0 mm (1/8"-3/16")
- Total welding current 1200-2000 A
- Shipbuilding, pressure vessels, heavy beams, bridges, offshore fab.
- Relatively high investment compared to single wire SAW


**Deposition rate up to 25 kg/h (55 lbs/h)**

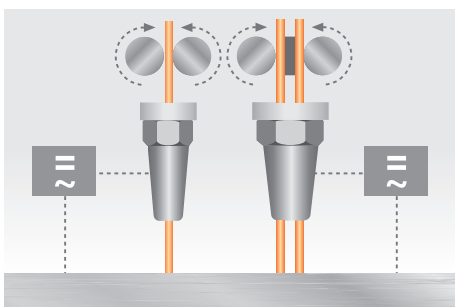

### Tandem single-twin wire SAW

- 3 wires, one 1-roll feeder, one 2-roll feeder, one 1-wire head, one 2-wire head.
- Two power sources, two control units
- Wire diameter 2.4-4.0 mm (3/32"-5/32")
- Total welding current 1100-1700 A
- Wind towers, pressure vessels
- Small incremental investment compared to Tandem SAW


**Deposition rate up to 30 kg/h (66 lbs/h)**

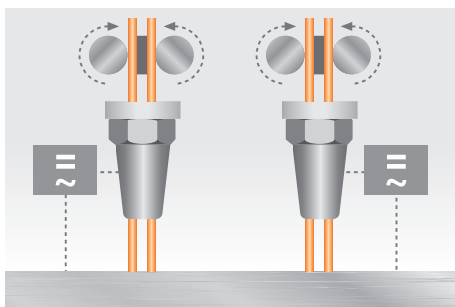

### Tandem twin wire SAW

- 4 wires, two 2-rolls feeders, two 2-wire heads
- Two power sources, two control units
- Wire diameters 1.6-3.2 mm (1/16"-1/8")
- Total welding current 1500-2200 A
- Wind towers, pressure vessels
- Small incremental investment compared to Tandem SAW

**Deposition rate up to 35 kg/h (77 lbs/h)**

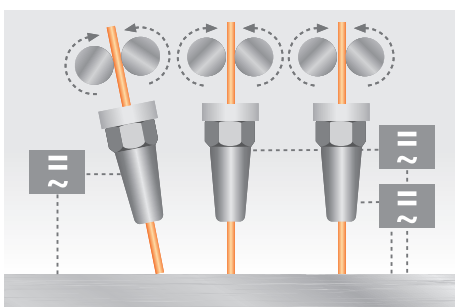

### Multi wire SAW

- Up to five wires, feeders, heads, power sources and control units
- Wire diameters 3.2-5.0 mm (1/8"-3/16")
- Total welding current 2000-5500 A
- Pipemills, offshore, shipbuilding.
- High investment

**Deposition rate up to 125 kg/h with five wires (220 lbs/h)**

# Submerged Arc Welding Process

## Effects of welding parameters

The welding parameters in submerged arc welding - arc voltage, welding current, travel speed, stick-out, torch angle, wire diameter, wire feed speed and polarity - all influence the shape and quality of the weld, and productivity. It is important to be aware of their individual and combined influence. In this chapter we do not discuss

welding defects that result from incorrect parameters – mostly set too low or too high. These are discussed in the trouble shooting section of this catalog. The table reviews the effects when individual welding parameters are increased, while all other parameters remain unchanged. Decreasing them will have opposite effects.

Effects of increased current	Effects on weld profile
Higher deposition rate Higher heat input Larger heat affected zone Increased penetration Increased bead height Higher dilution with parent metal	
Effects of increased voltage	Effects on weld profile
Higher heat input Larger heat affected zone No change of penetration Wider beads, lower bead height Increased flux consumption	
Effects of increased travel speed	Effects on weld profile
Lower heat input Smaller beads Less penetration Less dilution	
Effects of increased stick-out	Effects on weld profile
Higher deposition rate Less penetration Higher bead Lower arc voltage	
Effects of increased wire diameter	Effects on weld profile
Possibility of increased deposition rate Less penetration Wider bead	

Effects of type of current and polarity	Effects on weld profile
<b>DC+</b> Deepest penetration Highest dilution Lowest deposition rate	
<b>AC</b> Lower penetration Lower dilution Higher deposition rate than DC+	
<b>DC-</b> Higher deposition rate than AC Lowest dilution Lowest penetration Mainly used for cladding	
	Max. penetration Slow travel speed
	Less penetration Higher travel speed
	Least penetration Highest travel speed


Effects of electrode angle in butt welds			
	<b>Pulling</b>	<b>Neutral</b>	<b>Pushing</b>
<b>Penetration:</b>	<b>Deep</b>	<b>Moderate</b>	<b>Shallow</b>
<b>Reinforcement:</b>	<b>Maximum</b>	<b>Moderate</b>	<b>Minimum</b>
<b>Risk of hot cracking:</b>	<b>High</b>	<b>Low</b>	<b>Low</b>

# Submerged Arc Power Sources

The performance of power sources is essential in mechanized or fully automated submerged arc welding, where they are often subjected to high duty cycles at high welding currents. A power source needs to be able to operate at welding currents as low as 300 A for thin materials and over 1000 A for thick materials, at up to 100% duty cycle. Robustness and durability are primary requirements, along with advanced electronic submerged arc functionality giving full control over the arc and its effects on the weld.

## Power source characteristics

Constant current (CC) and constant voltage (CV) are two important principles. They used to be applied in separate submerged arc power source types, but are nowadays available in a single machine and can be switched on and off when needed.

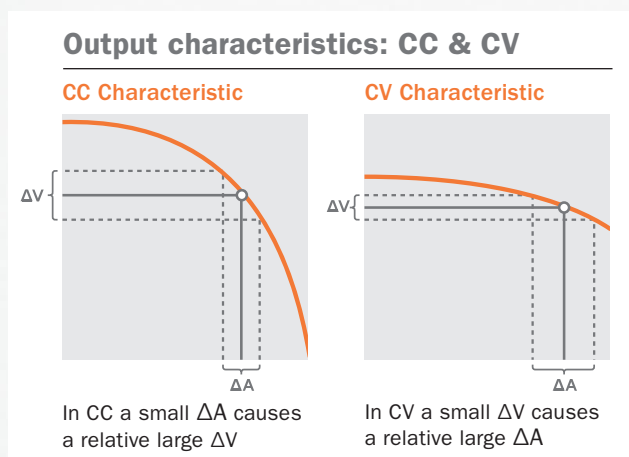

A CC characteristic shows a relatively steep downward slope in the volt/ampere curve. The welding current is the primary parameter set on the machine. Fluctuations in arc length/arc voltage ( $\Delta V$ ) - which are inevitable during welding - will only cause small variations in amperage ( $\Delta A$ ). To obtain a stable process, arc voltage sensing wire feeders constantly adapt the wire feed speed to maintain the

welding current at the set value. CC is best applicable with larger diameter wires fed at comparatively low wire feed speeds, because this places lower demands on the wire feed speed range and acceleration of the motors. However, with today's (tacho controlled) wire feed motors, CC can be applied with smaller diameter wires as well. The constant current provides stable and dependable weld penetration when welding materials with medium or high wall thickness.

A CV characteristic allows the use of thin welding wires while maintaining a stable arc. The volt/ampere curve is relatively flat. The arc voltage is the primary parameter set on the power source. Small fluctuations in arc voltage ( $\Delta V$ ) will cause relatively big changes in amperage ( $\Delta A$ ), while the wire feed speed remains the same. A higher voltage gives lower amperage and consequently a lower melt-off rate of the wire. A lower voltage gives higher amperage and accelerated wire melt-off. In this self-regulating way, the process balances around the set voltage/arc length.

CV can be applied with all wire diameters, but performs best below  $\varnothing 2.4$  mm (3/32"), due to the self-regulating effect. It is best suited for welding thin materials up to 12 mm (1/2") and for strip cladding. The constant voltage gives straight welds with constant bead width.

## Making use of polarity

As listed under "Effects of welding parameters" polarity has an effect on penetration, deposition, dilution, heat input and arc stability. Use of this is being made in different SAW processes and process variants.

DC+ gives the deepest weld penetration and highest parent metal dilution, because most heat is developed at the surface of the weld pool (minus pole).

**The table summarises the most important features of CC and CV applied in subarc power sources.**

Feature	CC	CV
Open circuit voltage	60-80 V	25-55 V
Parameter setting	By welding current	By arc voltage
Polarity	AC / DC	AC / DC
Arc stability	Fluctuations	Stable
Arc regulation	Through wire feed speed	Self-regulating
Application (best practice)	Larger diameter wires	Smaller and larger diameter wires



# AC wave balance

It also gives a stable arc, an optimal weld appearance, a good weld profile and reduced risk of porosity. For these reasons, DC+ is commonly used for single and twin-wire welding and for the leading wire in tandem and multi-wire operations.

Traditional sinusoidal AC gives ~15% higher deposition rate than DC+, shallower weld penetration and lower dilution. It is commonly used for trailing wires in tandem and multi-wire systems to counteract magnetic arc blow and provides increased deposition. A drawback of conventional sinusoidal wave AC is poor arc ignition and stability, because the current passes through the zero point with a certain delay, due to the wave form. This disadvantage is taken away by modern AC square wave power sources.

DC- gives the highest deposition rate (~35% higher than DC+), because most heat is developed at the tip of the wire electrode. The main applications, however, make use of the reduced penetration and lower weld metal dilution. Examples are difficult to weld materials and strip cladding, where dilution with the parent metal needs to be limited.


Modern AC square wave power sources provide interesting possibilities to vary the DC+ / DC- ratio and their frequencies in AC welding, giving full control over deposition rate and penetration.

## AC square wave technology

AC square wave technology applied in welding offers useful opportunities to shape the form of the AC sinus and influence essential welding characteristics such as penetration, deposition rate and travel speed, without changing the volt/ampere setting. It was one in a series of power source innovations to bring submerged arc welding at a higher performance level:

- AC square wave replacing sinusoidal AC
- AC/DC with CC&CV replacing AC with CC characteristic only
- Variable AC frequency
- Variable balance of electrode positive and negative instead of fixed 50/50

Square wave technology in welding power sources is based on either inverter or thyristor technology to control the wave form. Both technologies enable to change the AC+/AC- ratio (= AC wave balance), but there are differences in the way this is realized. In general, inverters offer total freedom in AC+/AC- ratio and AC wave frequencies settings, while Thyristor controlled wave frequency settings are derived from the mains net frequency.

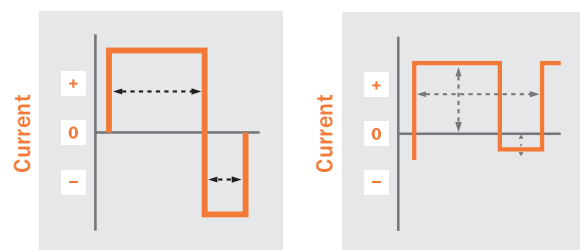

Left: Thyristor controlled square wave.  
Right: inverter square wave.  
The arrows indicate in which directions the square wave form can be altered.

## Why apply AC square wave

Both DC+ and conventional sinusoidal AC are widely applied in submerged arc welding systems, offering weld quality and productivity in any type of fabrication. The use of AC wave balance must be seen as a next step in the optimization of submerged arc welding, overcoming specific constraints while opening up new possibilities.

### Constraints of conventional sinusoidal AC are:


- Time spent in the zero crossover area affects arc starts and arc stability negatively
- Lower percentage of time spent at set amperage lowers productivity
- AC+/AC- ratio is fixed at 50/50

### Constraints of traditional DC+ are:

- Penetration can be too deep for the root pass causing burn through
- Low heat input and high deposition not obtainable at the same time without sacrificing bead appearance
- Sensitive to magnetic arc blow


# AC wave balance

AC square wave technology has two main advantageous properties - the AC wave block form and the variable AC wave balance. Due to the block form, the current passes through the crossover area in milliseconds resulting in good arc starts and stability and more dwell time at set current.

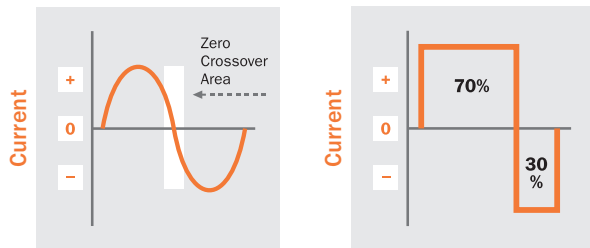

Left: Conventional sinusoidal AC.  
Right: Wave balance shifted to 70% AC+ and 30% AC-.

## Effects of Wave Balance

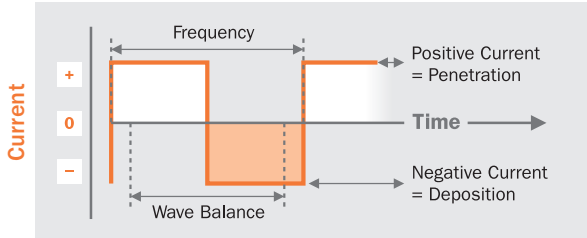

Wave Balance = Adjustable ratio between penetration/deposition

The variable AC wave balance makes it possible to alter the share of AC+ versus AC- to any desired ratio and thereby to influence penetration and deposition rate. Increasing the + share will give deeper penetration and reduced deposition, while increasing the minus share will do the opposite.

## Test data

The table reviews results of test welds with a variety of balance settings. Deposition rate and wire feed speed were measured for each setting. Welding parameters remained the same for all balance settings.


Balance setting	Actual wfs (m/min)	(inches/min)	Deposition (kg/h)	(lbs/h)
DC+	2.1	83	7.9	17.4
80/20	2.3	90	8.7	19.2
70/30	2.5	98	9.4	20.7
76/33	2.6	102	9.8	21.6
60/40	2.7	106	10.2	22.5
50/50	2.8	110	10.5	23.1
40/60	2.9	114	10.9	24.0
33/67	3.0	118	11.3	24.9
30/70	3.1	122	11.7	25.8
20/80	3.1	122	11.7	25.8
DC-	3.2	126	12.0	26.5
Difference DC+, DC-			34%	

Solid wire 3.2 mm (1/8"), 600 A, 31 V, 50 cm/min (20"/min), 30 mm (1.2") ESO.

## Effect on penetration



## Effect on travel

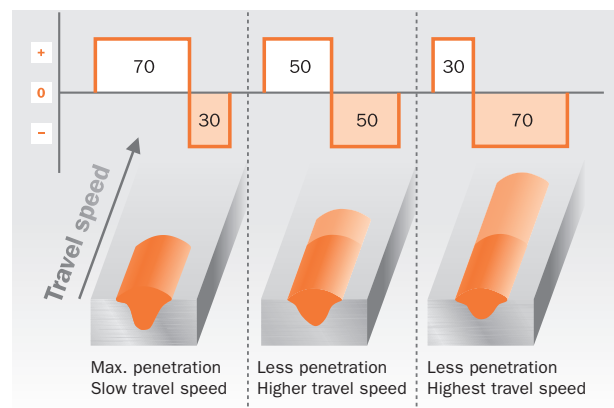

The images above show the effects of AC wave balance on penetration and on the adapted travel speed needed to accommodate increased deposition. Note that an increase in travel speed with other parameters remaining the same will result in a lower heat input and reduced plate deformation.

## AC wave balance options summarized

AC wave balance offers the following options in single and multi-wire submerged arc welding:

- Fine tuning of root penetration and deposition rate from single or lead wires
- Increase of deposition rate from trailing wires
- Increase of travel speed and reduction of heat input
- Reduction of deformation
- Elimination of arc blow

### Miller AC wave balance

The SubArc AC/DC 1000/1250 Digital is Miller's latest AC power source with variable square wave balance (VBAC) for submerged arc welding. It is based on the proven SCR phase shift technology which Miller implemented in welding equipment as early as 1999 – years ahead of the first inverter square wave power source.

#### SubArc AC/DC 1000/1250 Digital features:

- Reliability. Like all Miller welding machines it is built for operations under heavy conditions, with low maintenance and long lifetime. Only one PC board is used for the entire machine.
- DC or VBAC + CC/CV characteristics, three-phase primary. 1000 A at 100% duty cycle/1250 A at 60% duty cycle.
- A preset choice of 14 wave balance/frequency settings – easy to use, tested to work and covering the majority of applications. This avoids complicated setting and testing with freely adjustable wave balance parameters. **An optional software upgrade provides up to 81 optimized balance settings.**
- No special equipment needed to connect power sources for multi-arc operation.



#### Miller Subarc System Interface Digital

Compatible with AC/DC-CC/CV power sources offers remote balance settings.


#### Standard wave balance/frequency settings

available from the Subarc System Interface Digital.


Balance	Frequency	
	60 Hz line	50 Hz line (US)
<b>Electrode positive</b>	--	--
80/20	18	15
75/25	22.5	18.8
70/30	18	15
67/33	30	25
60/40	18	15
50/50	30	25
50/50	18	15
40/60	18	15
33/67	30	25
30/70	18	15
25/75	22.5	18.8
20/80	18	15
<b>Electrode negative</b>	--	--

# SAW and ESW strip cladding

Strip cladding is used to create corrosion or wear resistant overlays on large non- or low-alloyed steel components used in, for example, the chemical, petrochemical, nuclear, steel mills and paper and pulp industries. It provides a cost efficient solution over using components in full stainless steel or Ni-alloys.

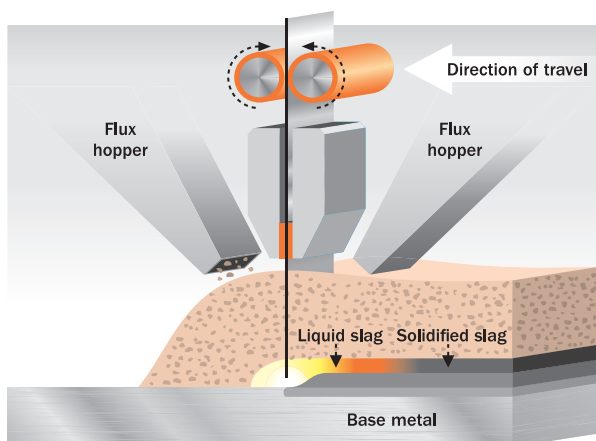

SAW strip cladding

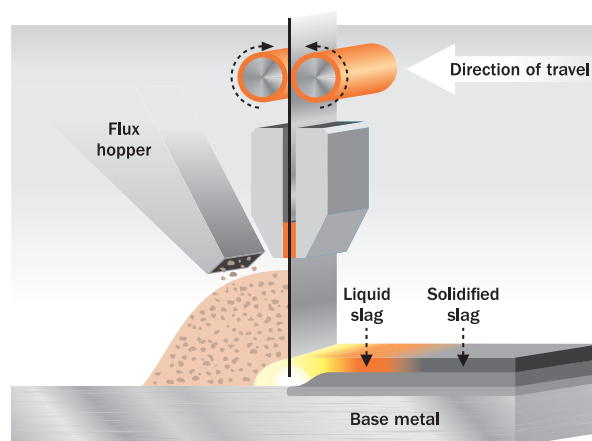

ESW strip cladding

## Two process technologies

One technology is submerged arc strip cladding, formally denominated SASC, but normally referred to as SAW strip cladding. The other method is electroslag strip cladding. The formal designation is ESSC, but is mostly called ESW Strip cladding.

The SAW and ESW strip cladding processes use a strip electrode to cover a wide area with each run. Strip dimensions are typically 30, 60 or 90 x 0.5 mm, but there is an increasing interest in 120 mm wide strip. Specially developed welding fluxes are needed to obtain the right characteristics for each process.

SAW strip cladding is an arc welding process. The function of the flux is basically the same as in standard submerged arc welding. It forms a slag to protect the weldpool and supports the formation of the weld bead.

In ESW strip cladding there is no arc between the strip and the parent metal and the flux is fed from only one side. The molten slag is electrically conductive and the heat needed to melt the strip and the parent metal surface is generated by the electrical resistance in the weld pool. Because of this, penetration and thus dilution is lower than with SAW cladding. Due to the high temperature of the weld pool and the high welding current a heavy duty welding head is necessary. The high welding current may cause weld defects such as uneven weld bead. This can be prevented by using a magnetic steering device for larger strip widths ( $\geq 60$  mm / 2.4"). Moreover the ESW strip cladding process burns off some elements from the strip at a higher rate than SAW. The implication is that the strip for ESW cladding has to have a slightly different chemistry than SAW to achieve the desired chemistry of the deposit.

#### Comparison between the SAW and ESW cladding methods:

Strip 60x0.5mm	SAW	ESW
Deposition rate	12-15 kg/h (26-33 lbs/h)	20-27 kg/h (44-59 lbs/h)
Travel speed	10-12 cm/min (4-5 inch/min)	18-24 cm/min (7-10 inch/min)
Arc voltage	26-28 V	24-26 V
Current	700-800 A	1200-1450 A
Dilution	~20%	~10%
Penetration	>0.8 mm (>0.03")	<0.5 mm (<0.02")
Heat input	~12 kJ/mm	~12 kJ/mm
No. of layers	Min 2	Min 1
Deposit thickness	~8.5 mm (~1/3")	~4.5 mm (3/16")
Flux consumption	0.8 kg/kg strip (0.8 lbs/lbs strip)	0.6 kg/kg strip (0.6 lbs/lbs strip)

#### ESW strip cladding has the following benefits over SAW strip cladding:

- Increased deposition rate.
- High travel speed
- Low dilution
- Less penetration
- Comparable heat input
- Lower flux consumption.
- Weld deposit obtainable in one layer

For both SAW and ESW strip cladding, standard SAW DC power sources are used. However, the current capacity has to be more or less doubled for ESW strip cladding, meaning that the investment cost for power sources will be at least doubled compared to SAW strip cladding. Furthermore ESW requires water cooling and in many cases magnetic steering devices increasing the difference in investment costs further. However, when ESW strip cladding is technically feasible in the application, the incremental investment costs for ESW compared to SAW are typically easily off set by the increased deposition rate and the fact that it is possible to reach the desired weld metal chemistry in one layer.

The current Hobart flux programme features one flux for SAW strip cladding and two fluxes for ESW strip cladding.

#### SWX 305

SAW strip cladding with austenitic stainless steel strip


#### SWX 330

ESW strip cladding with austenitic stainless steel strip

#### SWX 382

ESW cladding with Ni-base strip

#### Deposition rate SAW - ESW Strip cladding

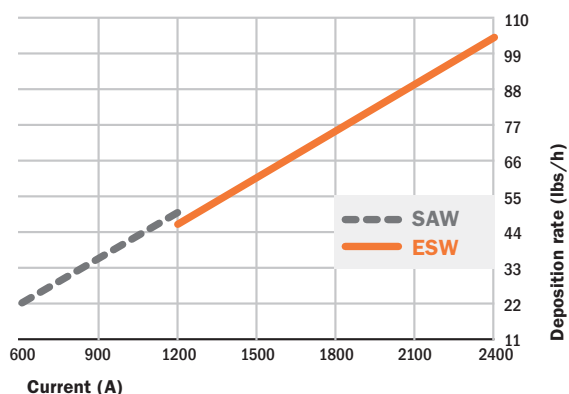

ITW Welding is a total solution provider; also for SAW and ESW strip cladding. An overview of our offerings for submerged arc welding, submerged arc strip cladding and ESW strip cladding is presented in the back of this catalogue.

# Trouble shooting

## Porosity




### Probable cause

Rusty plate	Wire brush or grind
Oily plate	Degrease or preheat
Wet plate	Preheat
Wet flux	Redry flux
Primer in welding zone	Remove primer
Flux layer too thin	Increase flux bed height
Contaminated joint	Clean joint
Arc blow	Reposition ground

### Solution

## Undercut

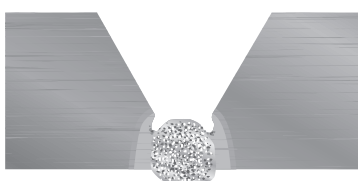

### Probable cause


Voltage too high	Adjust parameters
------------------	-------------------

### Probable cause

Travel speed too high	Adjust travel speed
-----------------------	---------------------

### Solution

## Tight slag

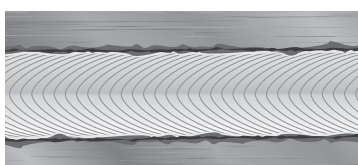

### Probable cause

Voltage too high	Adjust parameters
Incorrect wire size	Adjust parameters
Irregular weld	Adjust parameters
Welding zone too hot	Cool down
Joint prep too narrow	Adapt joint design

### Solution

## Burn through




### Probable cause

Current too high	Adjust parameters
Voltage too low	Adjust parameters
Travel speed too low	Adjust parameters
Root face too small	Adjust parameters
Poor fit-up	Improve fit-up

### Solution

## Longitudinal cracks

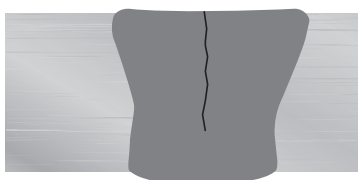


### Probable cause

Concave bead profile	Adjust parameters and torch position
Weld depth/width ratio > 1	Adjust parameters
Poor fit-up	Improve fit-up
Rigid construction	Preheat
Excessive length of weld pool	Adjust parameters

### Solution

## Transverse cracks

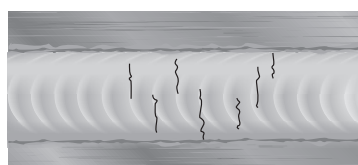
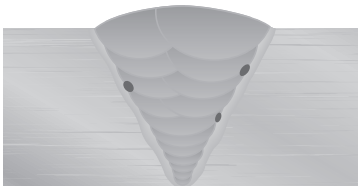
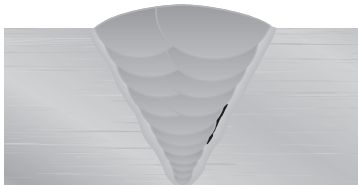
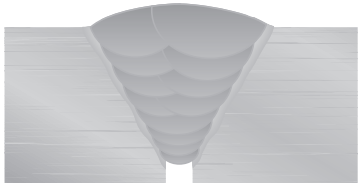
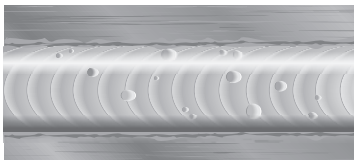


### Probable cause

Cooling rate too high	Preheat, increase interpass temperature, use preheated flux
Excessive restraint	Preheat or adapt design
Moisture in flux	Redry flux

### Solution



Poor weld appearance	Probable cause	Solution
	Travel speed too high	Adjust parameters
	Voltage too low	Adjust parameters
	Current too high	Adjust parameters
	Poor fit-up	Improve fit-up
Slag inclusions	Probable cause	Solution
	Flux trapped in joint	Adjust torch angle and parameters. Change joint angle/design
	Joint opening angle too small	Adapt joint design
	Insufficient penetration	Adjust parameters
Cold lap	Probable cause	Solution
	Plate temperature too low	Preheat
	Heat input too low	Adjust parameters
	Travel speed too high	Adjust parameters
	Negative polarity	Adjust parameters
Lack of penetration	Probable cause	Solution
	Current too low	Adjust parameters
	Travel speed too high	Adjust parameters
	Root face too large	Adapt joint design
Pock marks	Probable cause	Solution
	Excessive flux bed depth	Reduce flux bed depth
	Dirty wire	Use new wire
	Dirty plate	Clean plate or change flux / wire combination
	Moisture	Preheat plate
	Wrong flux / wire combination	Change to higher deoxidising wire and more active flux

Magnetic Steering Device

The magnetic steering device is intended for use with the ESW process. When used with stainless steel and nickel-base strip and fluxes, it ensures that the cladding process achieves uniformity, in terms of level and uniform weld bead edge formation. Additionally it controls the weld bead ripple formation which maintains the consistency of both bond integrity and appearance.



CHARACTERISTICS

- Weight 15 kg (33 lbs)
- Dimension 530 x 280 x 400 mm (21 x 11 x 16")
- Power 220V /110V 50 - 60 Hz
- Solenoid 10 A 24 VDC (red) / strip 90-120 mm (3.5 - 4.7")

Strip De-Reeler



Strip spool holder from 150 to 1.000 Kg (330 - 2200 lbs.) with adjustable inner diameter.



ProHeat™ Rolling Inductor Induction Heating System


The ProHeat 35 Induction Heating System with the Rolling Inductor is a simple and cost-effective heating process that can solve many preheating problems and deliver fast, consistent heat for pipe fabrication shops that weld pipe spools for the refinery, petrochemical, power and HVAC industries.

APPLICATIONS

- Process piping
- Refinery
- Petrochemical
- Power piping
- Pressure vessels

BENEFITS

- **Maximum productivity**
  - Quick time to temperature
  - Heating while rolling allows continuous fabrication
  - No coiling of cable
  - Compact and portable for use throughout the pipeshop
- **Improved safety**
  - Eliminates open flames
  - Cooler shop environment and reduced operator fatigue
- **Optimal consistency and quality**
  - Even distribution of heat
  - Eliminates quality issues

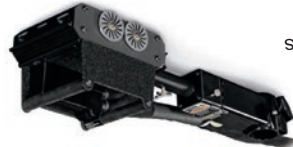

Specialty designed for preheating rolled pipe



ProHeat 35 Liquid-Cooled System with Rolling Inductor. (Pipe stands sold separately.)

Rated Output	350 Amps at 100% Duty Cycle	Ambient Temperature Range	0° C to 60° C (32° F to 140° F)	Maximum Part Preheat Temperature	315° C (600° F) *	Required Cooler	Miller Heavy-Duty Induction Cooler (#195 406) with coolant (#300 355)	Dimensions	H: (133 mm) 5.25 in. W: (168 mm) 6.6 in. D: (203 mm) 8 in.	Shipping Weight	18.1 kg (40 lb)
--------------	-----------------------------	---------------------------	---------------------------------	----------------------------------	-------------------	-----------------	---	------------	--	-----------------	-----------------


# Cladding Heads

## For Standard Application

It is recommended that all cladding SAW/ESW heads are used in conjunction with the Miller RAD 100/400 drive motor.


## 8" Diameter Head

- CHARACTERISTICS**
- Minimum inside diameter pipe clad 203 mm - 8"
  - Max current 750 A (100% duty cycle)
  - Dimension 1349 x 150 x 150 mm (58 1/8 x 6 x 6")
  - Weight 26.5 kg (59 lbs)
  - Water cooled
  - Strip width 30 mm (1-3/16")

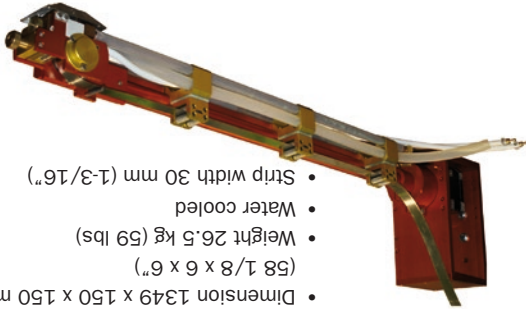


## 60 mm Cladding Head

- CHARACTERISTICS**
- Max current 2000 A (100% duty cycle)
  - Dimension 200 x 230 x 360 mm (8 x 9 x 14")
  - Weight 13.5 kg (29.7 lbs)
  - Water cooled
  - Strip width 30 - 60 mm (1/32" - 2 3/8")

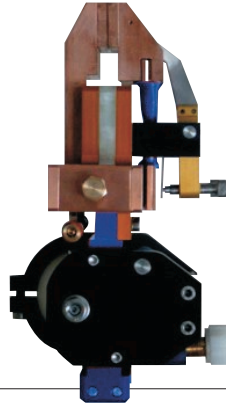


## 90 mm Cladding Head

- CHARACTERISTICS**
- Max current 3000 A (100% duty cycle)
  - Dimension 220 x 230 x 400 mm (8 x 9 x 16")
  - Weight 19 kg (41.8 lbs)
  - Water cooled
  - Strip width 30 - 60 mm (1/32" - 2 3/8")

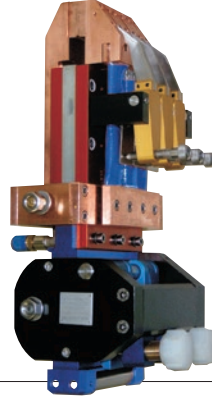


## 120 mm Cladding Head

- CHARACTERISTICS**
- Max current 3600 A (100% duty cycle)
  - Dimension 230 x 230 x 470 mm (8 x 9 x 19")
  - Weight 25 kg (55 lbs)
  - Water cooled
  - Strip width 60 - 90 - 120 mm (2 3/8" - 3 1/2" - 4 3/4")

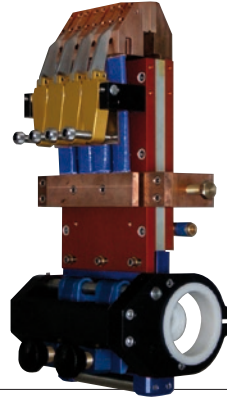


## 12" Diameter Head

- CHARACTERISTICS**
- Minimum inside diameter pipe clad 310 mm - 12"
  - Max current 1000 A (100% duty cycle)
  - Dimension 1349 x 240 x 225 mm (58 1/8 x 9 1/2 x 9")
  - Weight 27.5 kg (61 lbs)
  - Water cooled
  - Strip width 30 mm (1-3/16")

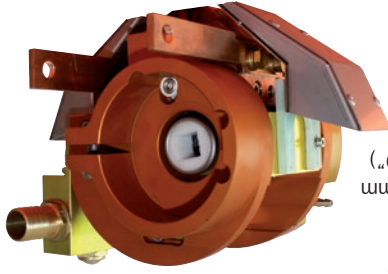

## 10" Diameter Head

- CHARACTERISTICS**
- Minimum inside diameter pipe clad 260 mm - 10"
  - Max current 850 A (100% duty cycle)
  - Dimension 1349 x 200 x 200 mm (58 1/8 x 8 x 8")
  - Weight 27 kg (60 lbs)
  - Water cooled
  - Strip width 30 mm (1-3/16")

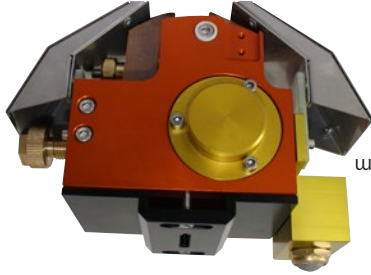

## For Nozzle and Pipe Application

The following head is designed for SAW/ESW both circumferential and longitudinal cladding.


## OBT 600



600 Amp,  
100% duty  
cycle torch  
with concentric  
flux flow nozzle.

### PROCESS

- Submerged arc welding (SAW)
- Wire diameter 1.6 - 5.5 mm (1/16 - 7/32")

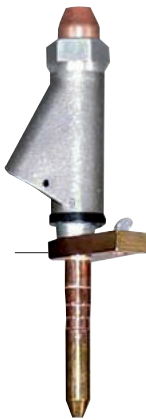

### PROCESS

- Submerged Arc Welding (SAW)
- Wire diameter 1.6 - 5.5 mm (1/16 - 1/4")



## OBT 1200

1200 Amp,  
100% duty  
cycle torch  
with concentric  
flux flow nozzle.



- Submerged Arc Welding (SAW)
- Wire diameter 1.6 - 5.5 mm (1/16 - 1/4")

## Single Wire Torch Short / Long



1200 Amp, 100% duty  
cycle torches

### PROCESS

- Submerged arc welding (SAW)
- Wire diameter 1.6 - 5.5 mm (1/16 - 7/32")



**Short model:** single wire welding nozzle with an effective length of 220mm (8.6").

**Long model:** single wire welding nozzle with an effective length of 360 mm (14.2").


## Twin Arc Torch Short / Long



1200 Amp, 100% duty cycle twin torches with concentric flux flow nozzle

### PROCESS

- Submerged arc welding (SAW twin)
- Wire diameter 1.2 - 2.4 mm x 2 (0.47 - 3/32")

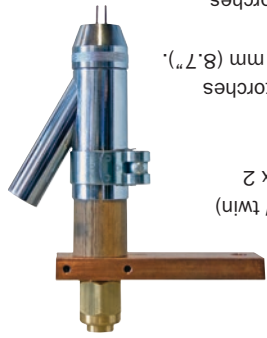

**Short model:** twin arc welding torches with an effective length of 220 mm (8.7").

**Long model:** twin arc welding torches with an effective length of 360 mm (14.2").

## Single Wire Narrow Gap Torch



1200 Amp, 100% duty cycle  
torch for narrow gap

### PROCESS

- Submerged arc welding (SAW)
- Wire diameter 2.4 - 4.0 mm (3/32 - 5/32")
- For depth 50 - 350 mm (2-14")
- PTFE insulation up to 200° C (390°F)
- Insulation type Ceramic up to 350° C (660°F)



## Tandem Wire Narrow Gap Torch



800 Amp, 100% duty cycle  
torches for narrow gap

### PROCESS

- Submerged arc welding (SAW)
- Wire diameter 2.4 - 4.0 mm (3/32 - 5/32")
- For depth 50 - 350 mm (2-14")
- PTFE insulation up to 200° C (390°F)
- Ceramic insulation up to 350° C (660°F)



## Single Wire Narrow Gap Flat Torch



800 Amp, 100% duty cycle  
torch for narrow gap

### PROCESS

- Submerged arc welding (SAW)
- Wire diameter 2.4 - 4.0 mm (3/32 - 5/32")
- For depth 100 - 250 mm (4 - 10")
- Ceramic insulation up to 350° C (660°F)





## Miller Tractor MT 1500

A motorized, highly flexible tractor designed to produce, high quality submerged arc welds.




### PROCESSES

- Submerged arc (SAW)
- Recommended

- Miller power supplies
- SubArc DC 800 Digital
- SubArc DC 1250 Digital
- SubArc AC/DC 1250 Digital

### PACKAGE INCLUDES

- Tractor
- Digital system interface
- RAD-400 drive motor
- Subarc Flux hopper Digital Low Voltage
- Wire reel
- Torch
- Remote start/stop control
- Tractor guide rolls
- Wire straightener

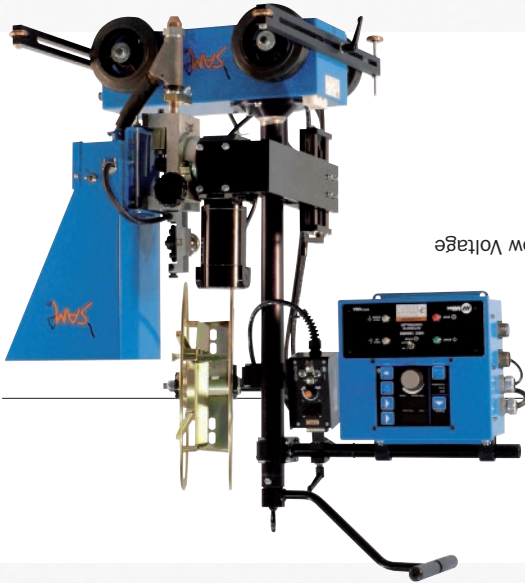

## Wire Drive Assemblies



### CHARACTERISTICS

- SubArc Strip Drive 100 Digital Low Voltage (ESW)
- Low speed, right-angle wire drive assembly
- SubArc Wire Drive 400 Digital Low Voltage
- Standard speed, right-angle wire drive assembly
- SubArc Wire Drive 780 Digital Low Voltage
- High speed, right-angle wire drive assembly

Miller offers either standard or high-speed 24 V Heavy-duty wire assemblies.

## SubArc Flux Hopper Digital Low Voltage

Automatic flux valve will carry 11.3 kg (25 lbs) of flux. The opening is sized to allow hook-up of any flux-hopper mounted recovery system. A slag screen is also provided.



### DESCRIPTION

- 11.3 kg (25 lbs) capacity
- Power supply 24 V



## Compressed Air Flux Feeder




### CHARACTERISTICS





- Storage capacity from 120 - 205 l (32 - 205 gal).
- Working temperature 100°C (212°F)
- Voltage supply 220 V
- Max input power 2800 W
- Max air pressure 6 bar (87 psi)

The automatic air compressed flux feeding system is electronically controlled to enable pre-heated flux to be kept at a constant temperature.

## Subarc DC 650/800 and Subarc 1000/1250 Digital Submerged Arc Welding

Three-phase, CC/CV DC power sources are designed to provide a superior arc for the SAW/ESW welding process as well as air carbon arc gouging plus the endurance to handle demanding industrial applications.





**PROCESSES**

- Submerged arc welding (SAW/ESW)
- Flux cored (FCAM)

**CHARACTERISTICS**

- CC/CV
- DC
- Requires three phase power
- 24 VAC low voltage control power
- Easy to integrate, Mod-bus digital interface

**Subarc DC 650 / 800 Digital**


- Amperage 50 - 815 A
- Voltage 10-65 V
- Rated output 650 A at 44 V (100% duty cycle)





**Subarc DC 1000 / 1250 Digital**

- Amperage 100-1250 A
- Voltage 10-60 V
- Rated output 1000 A at 44 V (100% duty cycle)

## Subarc AC/DC 1000/1250 Digital Submerged Arc Welding Power Source

Three-phase squarewave AC/DC machine with phase-shifting capability with steps to refine arc. AC/DC square wave provides excellent quality of penetration/bead profile and high performance in deposition rate with low heat input (increased mechanical properties and reduced distortion).





**PROCESSES**


- Submerged arc welding (SAW/ESW)



**CHARACTERISTICS**

- CC/CV
- AC/DC Variable squarewave
- Requires three phase power
- Frequencies 10 to 90Hz
- Amperage 250 - 1250 A
- Voltage 25 - 44V (71 OCV)
- Rated output 1000 A at 44 VDC (100% duty cycle)
- Easy to integrate, Mod-bus digital interface

## Subarc Interface Digital Automatic Weld Control

Automatic digital weld controllers offer reliability, flexibility and performance with their ability to interface with AC or DC, CC/CV power sources having remote contactor and output control capabilities.





**PROCESSES**

- Submerged arc welding (SAW)
- Electroslag (ESW)
- GMAW spray (with customer-supplied solenoid)

**CHARACTERISTICS**

- Supply single phase 24VAC 20A
- Welding power source CV, AC or DC
- Set up/menu
- flux valve control
- burnback/crater time
- wire feeder speed setting
- amperage/voltage/WFS range look
- memory for up to 15 programs
- arc time and arc cycles
- preflow/postflow
- start time/run-in
- digital setting of AC wave balance and frequency
- Terminal block for easy integration of hard automation or remote control



**Subarc AC/DC 1000/1250 Digital** Submerged Arc Welding Power Source


Variable balance AC/DC squarewave submerged arc welding (SAW) technology from Miller overcomes the traditional problems or limitations of SAW with all other processes including DC electrode positive (DCEP), DC electrode negative (DCEN) and traditional AC.

- The Subarc AC/DC 1000/1250 Digital gives full control over AC wave balance and frequency**
- Maximized deposition rate. 30% higher or more is feasible, using the same parameters.
  - Smaller angles and lower filler metal consumption
  - Reduced heat input, minimized distortion and increased mechanical properties
  - Penetration control to minimize the risk of lack of fusion
  - Minimized magnetic arc blow
  - Reduced arc interactions in multi-wire processes
  - Control of bead shape
  - Excellent arc start
  - Improved arc stability compared to traditional AC
  - Substantially lower power consumption
  - Reduced weld over thickness





The Subarc AC/DC 1000/1250 Digital has a choice of 14 most commonly used balance/frequency combinations and user-friendly setting.

Balance selection, indicated by BL.FR in the upper display, adjusts the AC balance and frequency, shown on the lower balance value two digits indicate the positive balance value followed by a decimal point. The two digits after the decimal point indicate frequency. Balance and frequency are dependent on one another, and cannot be individually adjusted.

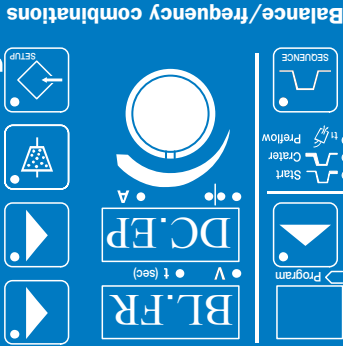

Balance		Electrode positive		Electrode negative	
Frequency	50hz line	--	--	--	--
15	18	80/20	18	20/80	15
18.8	22.5	75/25	18	25/75	15
15	18	70/30	18	30/70	15
25	30	67/33	18	33/67	25
15	18	60/40	18	40/60	15
15	18	50/50	18	50/50	15
25	30	50/50	18	40/60	15
15	18	60/40	18	33/67	25
15	18	70/30	18	30/70	15
18.8	22.5	75/25	18	25/75	15
15	18	80/20	18	20/80	15

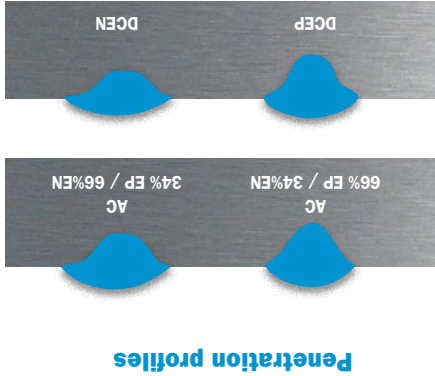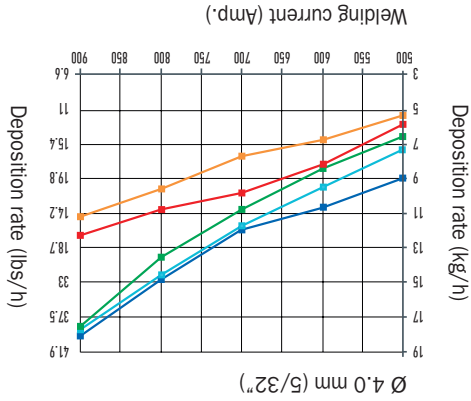

# Table of Contents

<b>Technology Increases SAW Deposition Rates</b> .....	4
<b>Miller Submerged Arc System</b> .....	5
Subarc DC 650 / 800 Digital and Subarc 1000 / 1250 Digital .....	5
Subarc AC/DC 1000 / 1250 Digital .....	5
Subarc System Interface Digital .....	5
<b>SAW Accessories</b> .....	6
Miller Tractor MT 1500 .....	6
Wire Drive Assemblies .....	6
Subarc Flux Hopper Digital Low Voltage .....	6
Compressed Air Flux Feeder .....	6
<b>Submerged Arc Torches System</b> .....	7
OBT 600 .....	7
OBT 1200 .....	7
Single Wire Torch Short / Long .....	7
Twin Arc Torch Short / Long .....	7
Single Wire Narrow Gap Torch .....	7
Tandem Wire Narrow Gap Torch .....	7
Single Wire Narrow Gap Flat Torch .....	7
<b>Cladding Heads (external and internal)</b> .....	8
60 mm Cladding Head .....	8
90 mm Cladding Head .....	8
120 mm Cladding Head .....	8
8" Diameter Head .....	8
10" Diameter Head .....	8
12" Diameter Head .....	8
<b>Accessories</b> .....	9
Magnetic Steering Device .....	9
Strip De-Reeler .....	9
ProHeat™ Rolling Inductor .....	9

**Disclaimer:** The information contained herein is furnished for reference purposes only and is believed to be accurate and reliable. Typical data are those obtained when welding and testing are performed in accordance with prescribed standards and guidelines. Other tests may produce different results and typical data should not be assumed to yield similar results in a particular application or weldment. ITW Welding does not assume responsibility for any results obtained by persons over whose methods it has no control. It is the user's responsibility to determine the suitability of any products or methods mentioned herein for a particular purpose. In light of the foregoing, ITW Welding specifically disclaims all warranties, express or implied, including warranties of merchantability and fitness for a particular purpose, and further disclaims any liability for consequential or incidental damages of any kind, including lost profits.

# Professional Technical Support for You

Process improvement - whether to increase output, reduce rejects or meeting structural requirements - are always profit boosting initiatives.

ITW Welding has assigned a dedicated expert team aiming at improving submerged arc operations. The team has access to a number of SubArc weld centers where welding procedures are developed, weld issues resolved and welding performances improved. Our application experts share their time between field support and development work and are available for advanced consultations.

## **A unique offering**

We can examine your submerged arc welding processes and together review options for improvements which will give real financial benefits. Contact us and discover ways to optimize your submerged arc processes to their full potential.





# Submerged Arc Welding Equipment



**HOBART**  
FILLER METALS

